



# OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Machine Id  
**SHUTTLELIFT 3339 CD1525**

Component  
**Hydraulic System**

Fluid  
**{not provided} (--- GAL)**

## RECOMMENDATION

No corrective action is recommended at this time. Resample at the next service interval to monitor. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		HPL0005098	---	---
Sample Date		Client Info		08 May 2024	---	---
Machine Age	hrs	Client Info		1324	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		N/A	---	---
Filter Changed		Client Info		N/A	---	---
Sample Status				ABNORMAL	---	---

## WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>20	2	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	2	---	---
Lead	ppm	ASTM D5185m	>10	<1	---	---
Copper	ppm	ASTM D5185m	>75	15	---	---
Tin	ppm	ASTM D5185m	>10	<1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

## CONTAMINATION









There is a high amount of silt (particulates < 14 microns in size) present in the oil.

Silicon	ppm	ASTM D5185m	>20	8	---	---
Potassium	ppm	ASTM D5185m	>20	2	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	▲ 21436	---	---
Particles >6µm		ASTM D7647	>1300	● 2267	---	---
Particles >14µm		ASTM D7647	>160	137	---	---
Particles >21µm		ASTM D7647	>40	35	---	---
Particles >38µm		ASTM D7647	>10	3	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ 22/18/14	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

## FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		0	---	---
Boron	ppm	ASTM D5185m		97	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		<1	---	---
Manganese	ppm	ASTM D5185m		0	---	---
Magnesium	ppm	ASTM D5185m		11	---	---
Calcium	ppm	ASTM D5185m		2540	---	---
Phosphorus	ppm	ASTM D5185m		941	---	---
Zinc	ppm	ASTM D5185m		1111	---	---
Sulfur	ppm	ASTM D5185m		6251	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045		0.97	---	---
Visc @ 40°C	cSt	ASTM D445		53.4	---	---

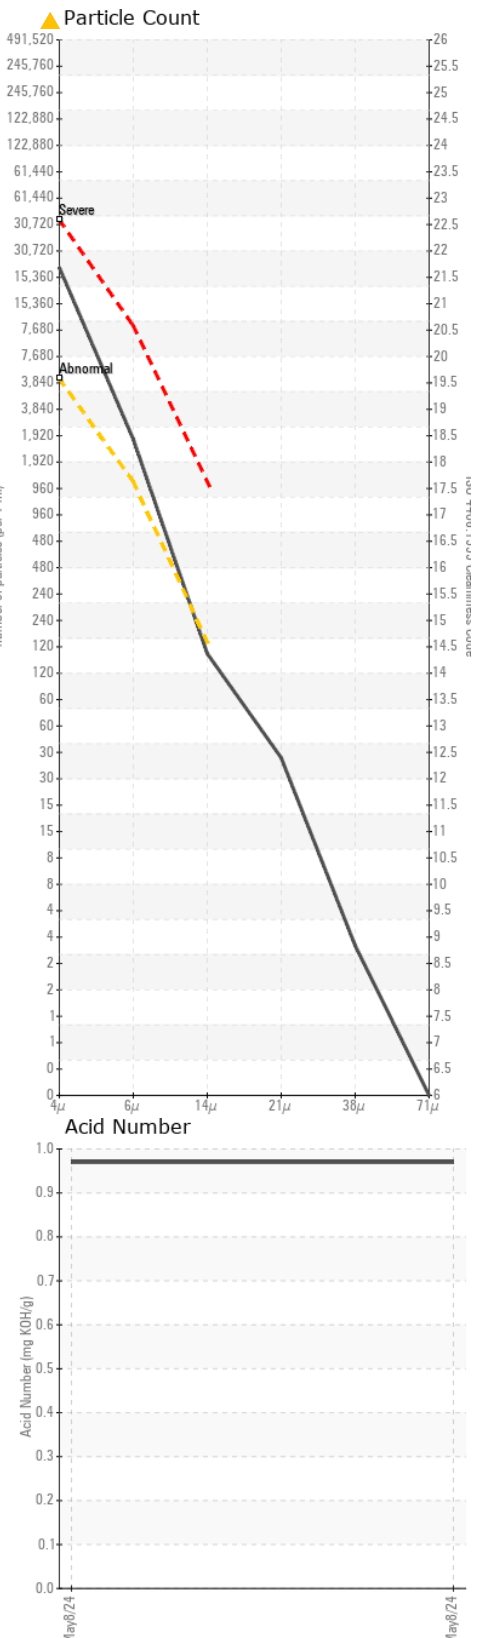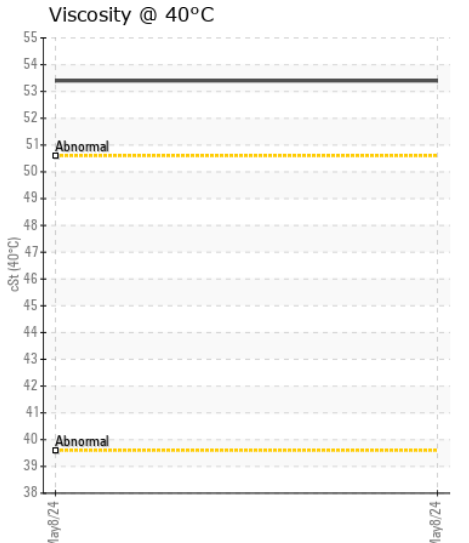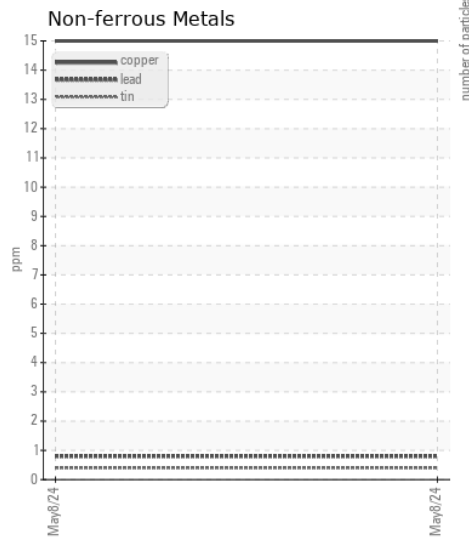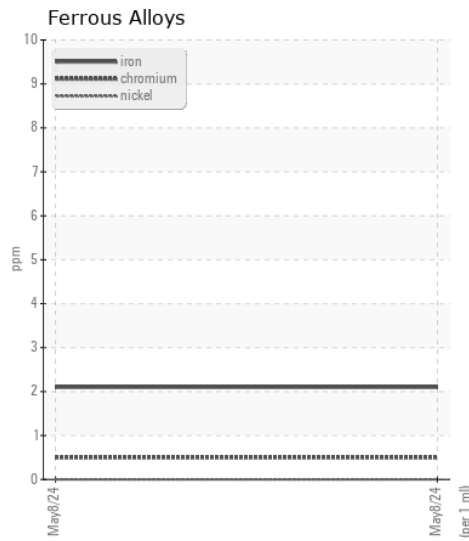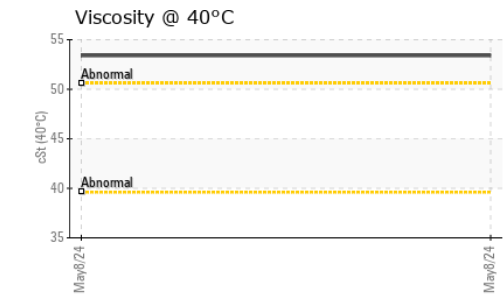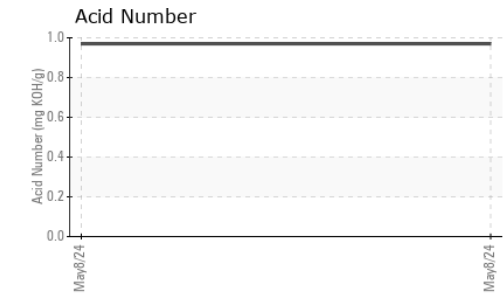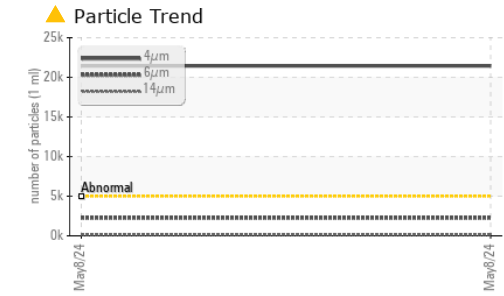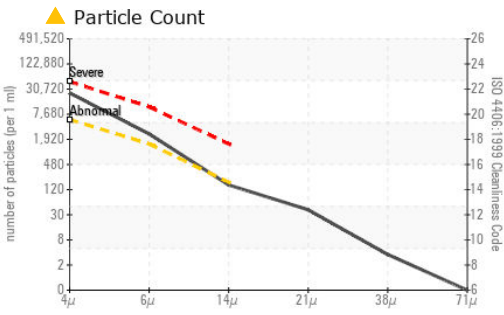

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : HPL0005098 **Received** : 10 May 2024  
**Lab Number** : 06175415 **Tested** : 13 May 2024  
**Unique Number** : 11021468 **Diagnosed** : 14 May 2024 - Don Baldrige  
**Test Package** : MOB 2

**STEVENSON CRANE**  
 410 STEVENSON DR  
 BOLINGBROOK, IL  
 US 60440

Contact: DAVE KOEHNE  
 davidk@stevensoncrane.com

T: (630)972-9199

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

F: