



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area
[05W46607]
 Machine Id
JOHN DEERE 850K 1T0850KXKLF369647
 Component
Hydraulic System
 Fluid
JOHN DEERE HYDRAU (30 GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0214381	JR0192140	JR0169091
Sample Date		Client Info		10 May 2024	20 Nov 2023	12 Apr 2023
Machine Age	hrs	Client Info		5467	4980	4443
Oil Age	hrs	Client Info		1500	4503	477
Filter Age	hrs	Client Info		1500	4503	477
Oil Changed		Client Info		Not Changd	Not Changd	Not Changd
Filter Changed		Client Info		Not Changd	Not Changd	Not Changd
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

PQ		ASTM D8184	>50	17	9	8
Iron	ppm	ASTM D5185m	>23	4	2	1
Chromium	ppm	ASTM D5185m	>9	2	1	<1
Nickel	ppm	ASTM D5185m	>5	0	<1	0
Titanium	ppm	ASTM D5185m		0	<1	0
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m	>9	2	2	<1
Lead	ppm	ASTM D5185m	>28	0	0	0
Copper	ppm	ASTM D5185m	>51	3	<1	0
Tin	ppm	ASTM D5185m	>5	<1	0	0
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION











The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>31	4	3	4
Potassium	ppm	ASTM D5185m	>20	0	1	1
Water		WC Method	>0.075	NEG	NEG	NEG
Particles >4µm		ASTM D7647	>80000	1188	2536	2309
Particles >6µm		ASTM D7647	>20000	147	277	403
Particles >14µm		ASTM D7647	>640	22	23	26
Particles >21µm		ASTM D7647	>160	7	7	7
Particles >38µm		ASTM D7647	>40	0	1	0
Particles >71µm		ASTM D7647	>10	0	0	0
Oil Cleanliness		ISO 4406 (c)	>23/21/16	17/14/12	19/15/12	18/16/12
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.075	NEG	NEG	NEG

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>21	1	0	<1
Boron	ppm	ASTM D5185m		<1	0	<1
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		2	4	4
Manganese	ppm	ASTM D5185m		1	0	<1
Magnesium	ppm	ASTM D5185m		34	38	58
Calcium	ppm	ASTM D5185m	87	210	221	284
Phosphorus	ppm	ASTM D5185m	727	658	684	691
Zinc	ppm	ASTM D5185m	900	834	876	855
Sulfur	ppm	ASTM D5185m	1500	1896	1885	1824
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.55	0.52	0.71
Visc @ 40°C	cSt	ASTM D445	65	56.7	58.2	58.6

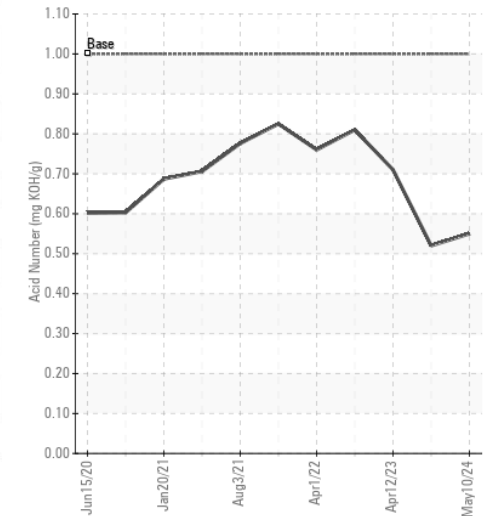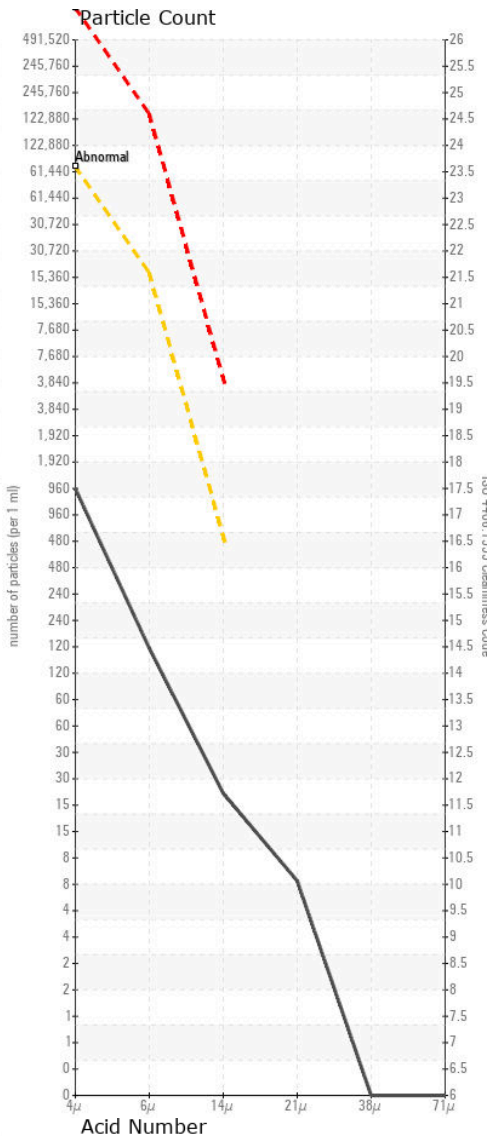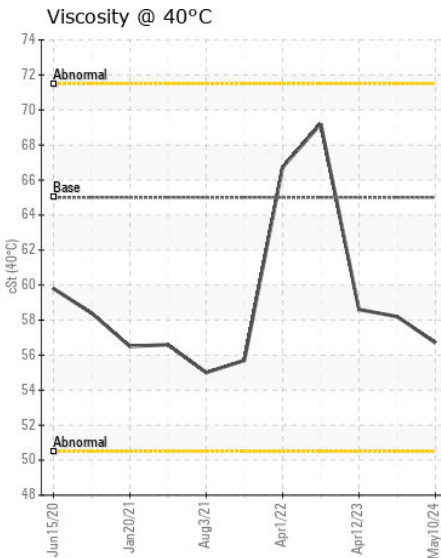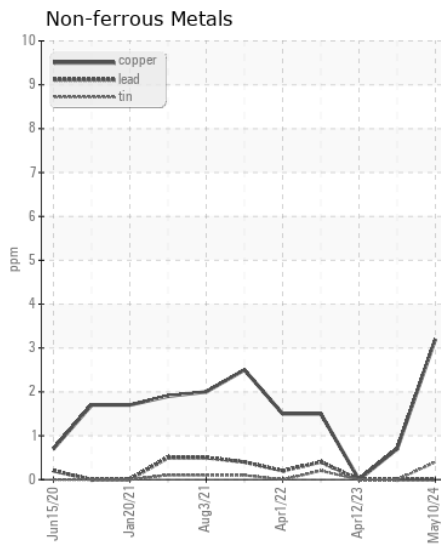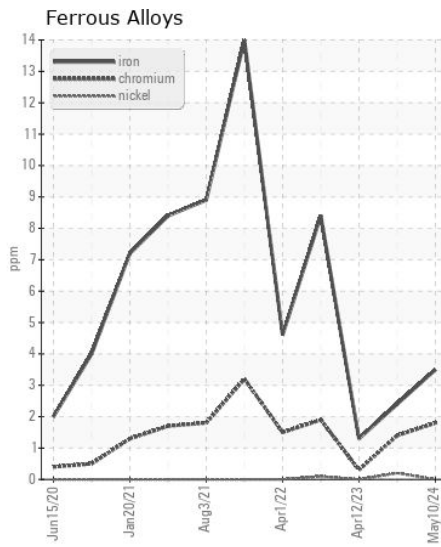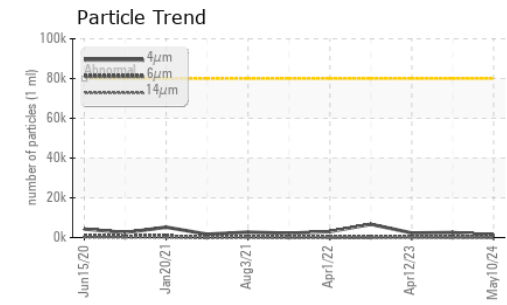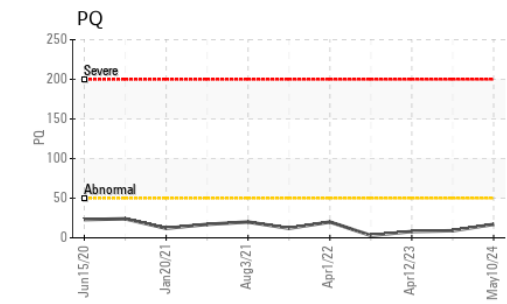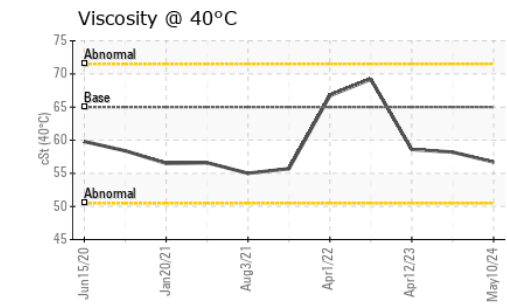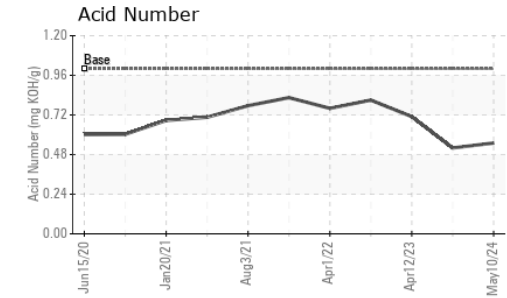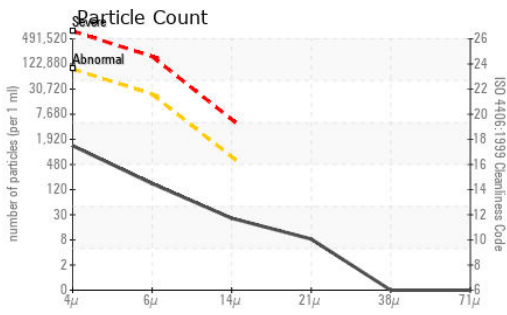

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : JR0214381

Lab Number : 06177034

Unique Number : 11023087

Test Package : CONST (Additional Tests: PQ)

Received : 13 May 2024

Tested : 14 May 2024

Diagnosed : 14 May 2024 - Wes Davis

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

CWS-STRITTMATTER

9102 OWENS DR

MANASSAS PARK, VA

US 20111

Contact: EDDIE GARRETSON

egarretson@strittmattercompanies.com

T: (703)335-2255

F: (703)335-8095