



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
JODY MCMINN
Component
Port Genset
Fluid
CHEVRON DELO 400 LE 15W40 (6 GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		MW0057845	MW0049103	MW0033255
Sample Date		Client Info		06 May 2024	30 Aug 2023	28 Apr 2023
Machine Age	hrs	Client Info		0	0	10644
Oil Age	hrs	Client Info		500	500	492
Filter Age	hrs	Client Info		500	500	492
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>50	29	6	42
Chromium	ppm	ASTM D5185m	>4	<1	<1	<1
Nickel	ppm	ASTM D5185m	>2	<1	0	<1
Titanium	ppm	ASTM D5185m		17	0	15
Silver	ppm	ASTM D5185m	>5	0	0	0
Aluminum	ppm	ASTM D5185m	>12	2	2	2
Lead	ppm	ASTM D5185m	>17	<1	<1	0
Copper	ppm	ASTM D5185m	>70	1	3	1
Tin	ppm	ASTM D5185m	>15	<1	<1	0
Vanadium	ppm	ASTM D5185m		<1	0	<1
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION

There is no indication of any contamination in the oil.


Silicon	ppm	ASTM D5185m	>25	8	11	5
Potassium	ppm	ASTM D5185m	>20	6	2	3
Fuel		WC Method	>4.0	<1.0	<1.0	<1.0
Water		WC Method	>0.1	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844		0.3	0.4	0.5
Nitration	Abs/cm	*ASTM D7624	>20	9.8	10.9	11.2
Sulfation	Abs/.1mm	*ASTM D7415	>30	21.4	21.4	23.0
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG	NEG

FLUID CONDITION


The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		4	5	3
Boron	ppm	ASTM D5185m		226	42	73
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		54	40	38
Manganese	ppm	ASTM D5185m		<1	1	<1
Magnesium	ppm	ASTM D5185m		727	543	818
Calcium	ppm	ASTM D5185m		3149	1725	1673
Phosphorus	ppm	ASTM D5185m	1200	1127	950	741
Zinc	ppm	ASTM D5185m	1300	1358	1155	910
Sulfur	ppm	ASTM D5185m	3200	5276	2876	3814
Oxidation	Abs/.1mm	*ASTM D7414	>25	17.3	18.4	21.2
Base Number (BN)	mg KOH/g	ASTM D2896	9.6	7.1	6.9	6.9
Visc @ 100°C	cSt	ASTM D445	15.7	14.6	12.8	14.8


FT-IR (Direct Trend)

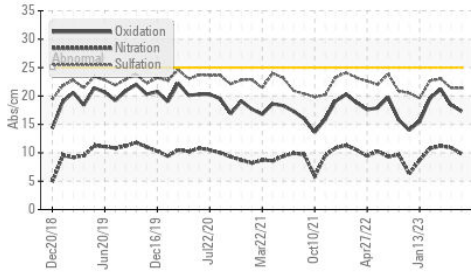


Base Number

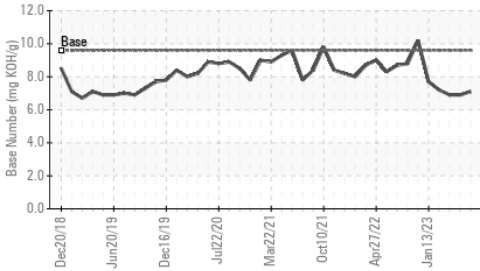


Viscosity @ 100°C

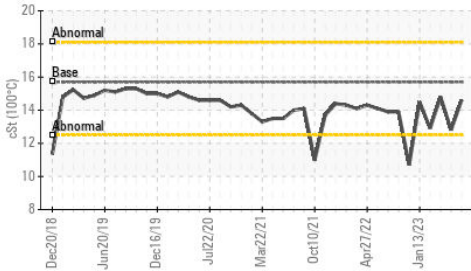


Ferrous Alloys

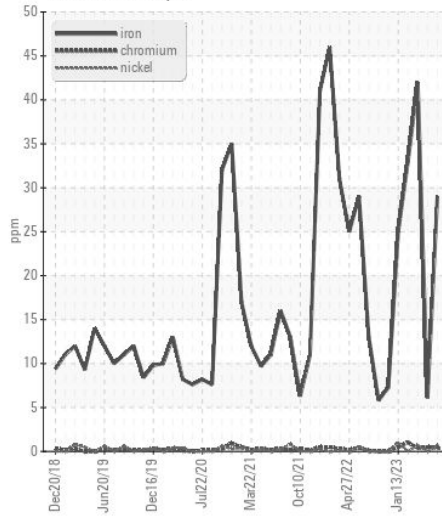


Non-ferrous Metals

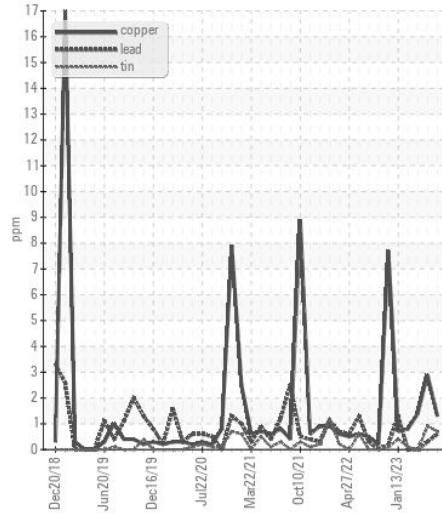

Viscosity @ 100°C

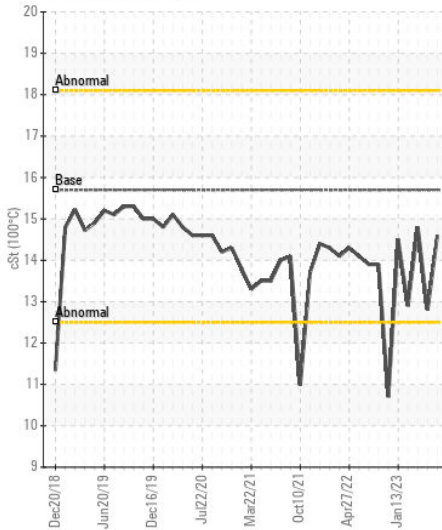

Base Number

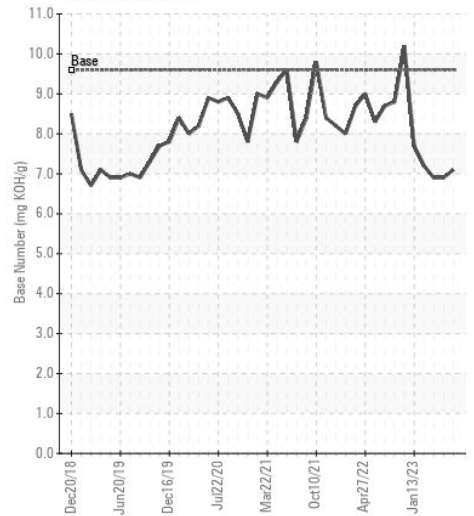

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : MW0057845
Lab Number : 06178220
Unique Number : 11029546
Test Package : MAR 2

Received : 13 May 2024
Tested : 15 May 2024
Diagnosed : 15 May 2024 - Wes Davis

MAGNOLIA MARINE TRANSPORT
 697 HAINING ROAD
 VICKSBURG, MS
 US 39183
 Contact: MMT MAINTENANCE PLANNERS
 mmtmaintenanceplanners@ergon.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: x:
 F: (601)638-8028