



WEAR	ABNORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	NORMAL

Area
[W22114-JOHNSON]

Machine Id
JOHN DEERE 1025R 1LV1025REGG105195

Component
Hydraulic System

Fluid
TDH FLUID SAE 70W80 (--- GAL)

RECOMMENDATION

We recommend you service the filters on this component. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0210857	---	---
Sample Date		Client Info		07 May 2024	---	---
Machine Age	hrs	Client Info		469	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Not Chngd	---	---
Filter Changed		Client Info		Not Chngd	---	---
Sample Status				ABNORMAL	---	---

WEAR

The iron level is abnormal. All other metal levels are typical for a new component breaking in.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	▲ 138	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	3	---	---
Lead	ppm	ASTM D5185m	>10	4	---	---
Copper	ppm	ASTM D5185m	>75	27	---	---
Tin	ppm	ASTM D5185m	>10	1	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION











There is a high amount of particulates present in the oil.

Silicon	ppm	ASTM D5185m	>20	13	---	---
Potassium	ppm	ASTM D5185m	>20	0	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	▲ 93886	---	---
Particles >6µm		ASTM D7647	>1300	▲ 12835	---	---
Particles >14µm		ASTM D7647	>160	▲ 272	---	---
Particles >21µm		ASTM D7647	>40	33	---	---
Particles >38µm		ASTM D7647	>10	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	▲ 24/21/15	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	LIGHT	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185m		3	---	---
Boron	ppm	ASTM D5185m	10	0	---	---
Barium	ppm	ASTM D5185m	10	4	---	---
Molybdenum	ppm	ASTM D5185m	10	0	---	---
Manganese	ppm	ASTM D5185m		2	---	---
Magnesium	ppm	ASTM D5185m	100	95	---	---
Calcium	ppm	ASTM D5185m	3500	3314	---	---
Phosphorus	ppm	ASTM D5185m	1150	1023	---	---
Zinc	ppm	ASTM D5185m	1150	1190	---	---
Sulfur	ppm	ASTM D5185m	5000	3776	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	2.25	1.30	---	---
Visc @ 40°C	cSt	ASTM D445	50	31.7	---	---

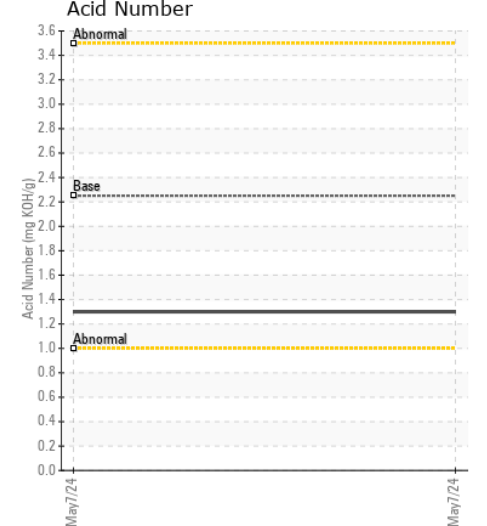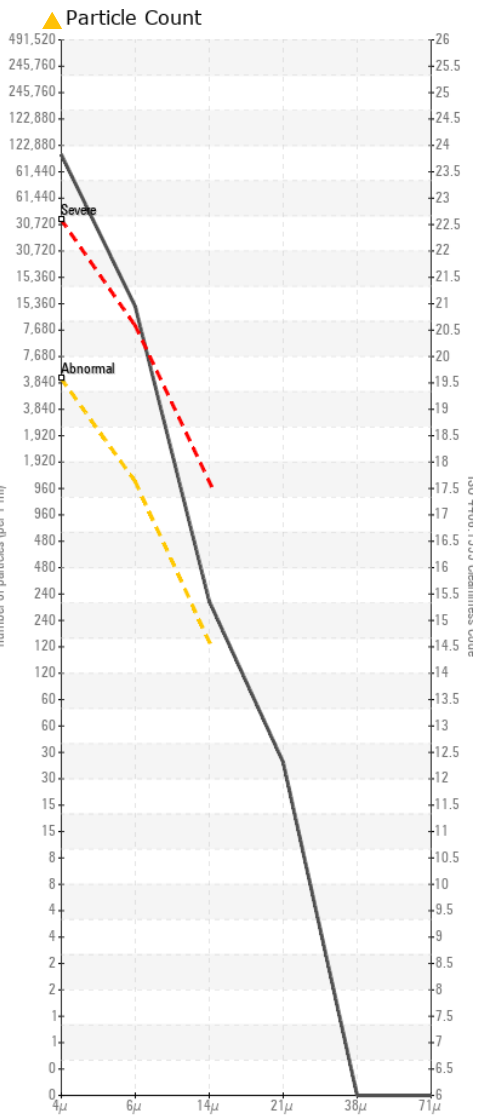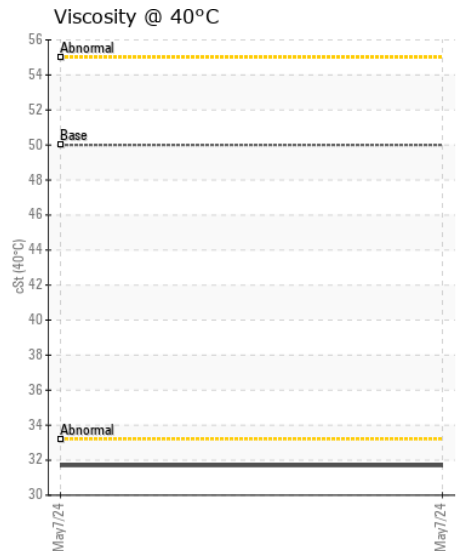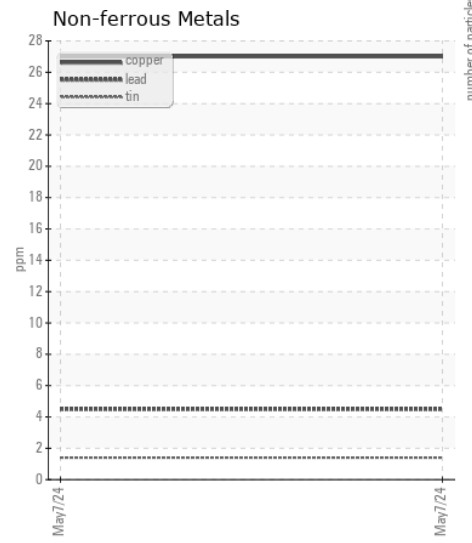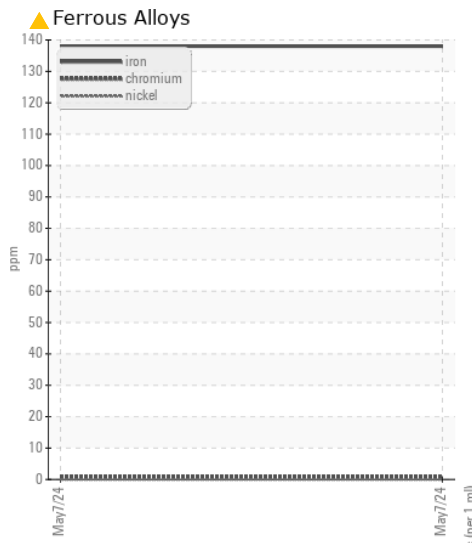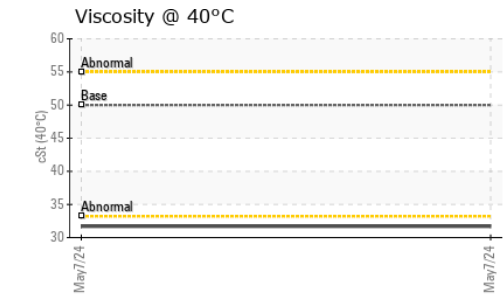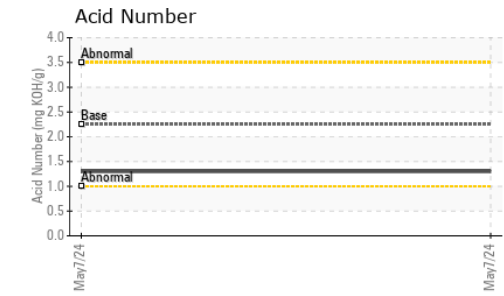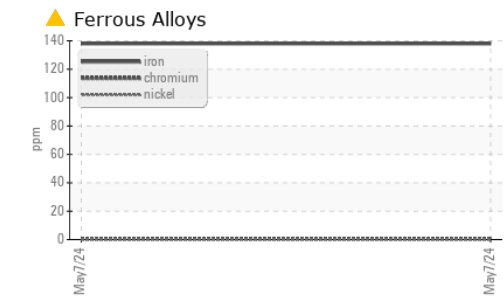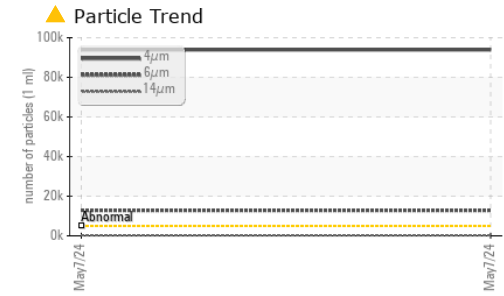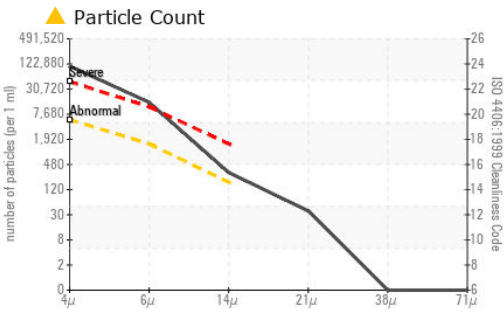

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0210857 **Received** : 14 May 2024
Lab Number : 06178635 **Tested** : 15 May 2024
Unique Number : 11029961 **Diagnosed** : 16 May 2024 - Don Baldrige
Test Package : CONST (Additional Tests: PQ)

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

JRE - BURKEVILLE
 510 WEST COLONIAL DR
 BURKEVILLE, VA
 US 23922

Contact: BRANDON BOLLING
 bbolling@jamesriverequipment.com

T: (434)767-5578
 F: (434)767-3774