



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
C333419 (S/N 21200552)
 Component
Hydraulic System
 Fluid
AW HYDRAULIC OIL ISO 46 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor. The fluid was not specified, however, a fluid match indicates that this fluid is (GENERIC) AW HYDRAULIC OIL ISO 46. Please confirm.
 Please specify the component make and model with your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0215867	---	---
Sample Date		Client Info		24 May 2024	---	---
Machine Age	hrs	Client Info		333	---	---
Oil Age	hrs	Client Info		333	---	---
Filter Age	hrs	Client Info		300	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

PQ		ASTM D8184		12	---	---
Iron	ppm	ASTM D5185m	>20	2	---	---
Chromium	ppm	ASTM D5185m	>10	0	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	0	---	---
Lead	ppm	ASTM D5185m	>10	0	---	---
Copper	ppm	ASTM D5185m	>75	2	---	---
Tin	ppm	ASTM D5185m	>10	0	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION










The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>20	2	---	---
Potassium	ppm	ASTM D5185m	>20	0	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	2386	---	---
Particles >6µm		ASTM D7647	>1300	716	---	---
Particles >14µm		ASTM D7647	>160	67	---	---
Particles >21µm		ASTM D7647	>40	15	---	---
Particles >38µm		ASTM D7647	>10	1	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	18/17/13	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		<1	---	---
Boron	ppm	ASTM D5185m	5	0	---	---
Barium	ppm	ASTM D5185m	5	0	---	---
Molybdenum	ppm	ASTM D5185m	5	0	---	---
Manganese	ppm	ASTM D5185m		0	---	---
Magnesium	ppm	ASTM D5185m	25	29	---	---
Calcium	ppm	ASTM D5185m	200	30	---	---
Phosphorus	ppm	ASTM D5185m	300	274	---	---
Zinc	ppm	ASTM D5185m	370	337	---	---
Sulfur	ppm	ASTM D5185m	2500	1528	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	0.57	0.38	---	---
Visc @ 40°C	cSt	ASTM D445	46	43.0	---	---

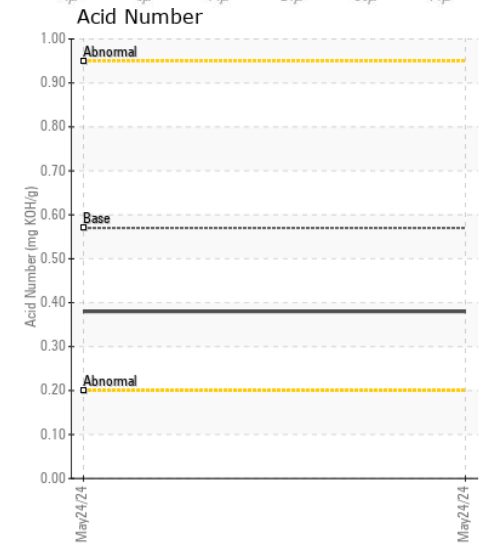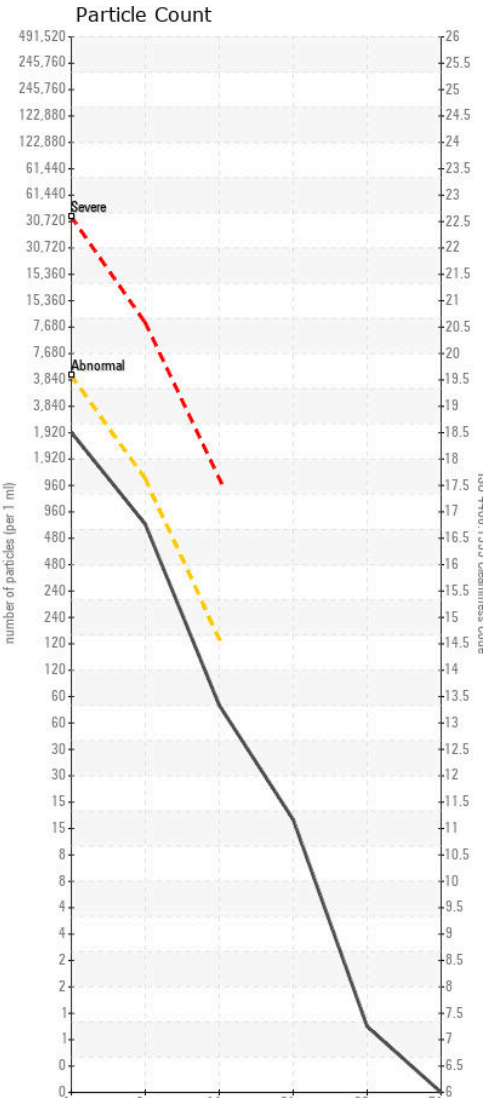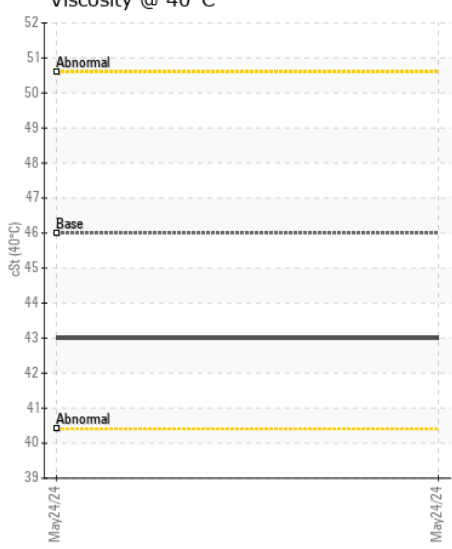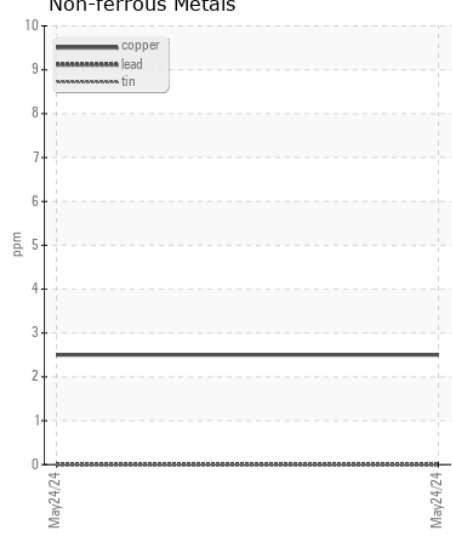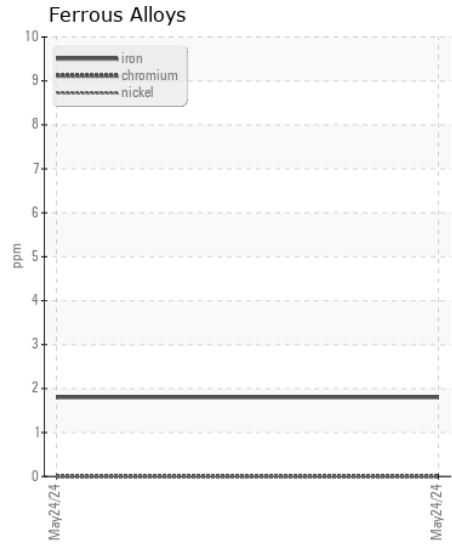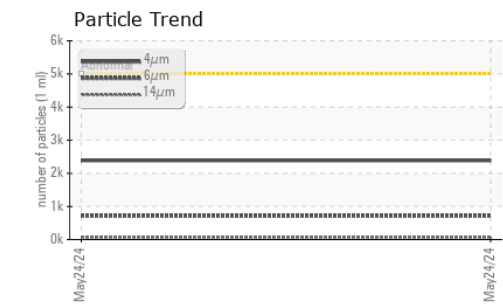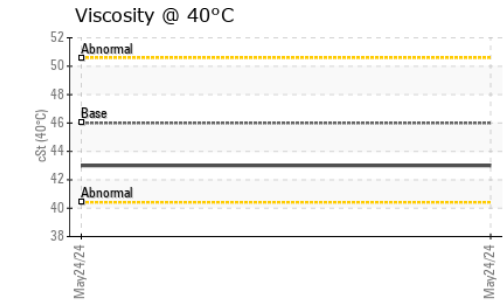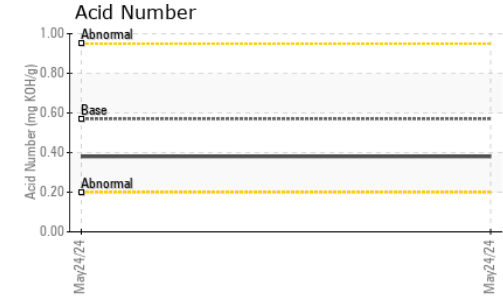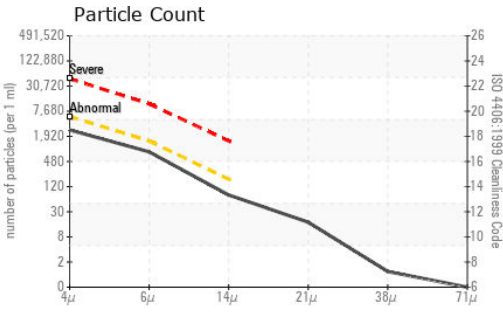

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0215867 **Received** : 29 May 2024
Lab Number : 06193871 **Tested** : 30 May 2024
Unique Number : 11055994 **Diagnosed** : 30 May 2024 - Wes Davis
Test Package : CONST (Additional Tests: PQ)

JRE - CHARLOTTE
 9550 STATESVILLE ROAD
 CHARLOTTE, NC
 US 28269
 Contact: CHARLOTTE SHOP
 myoung@jamesriverequipment.com
 T: (704)597-0211
 F: (704)596-6198

Certificate L2367
 To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)