



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 844L 1DW844LXHNL713327

Component
Hydraulic System

Fluid
JOHN DEERE HYDRAU (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WE0007442	---	---
Sample Date		Client Info		22 May 2024	---	---
Machine Age	hrs	Client Info		14844	---	---
Oil Age	hrs	Client Info		4844	---	---
Filter Age	hrs	Client Info		4844	---	---
Oil Changed		Client Info		Not Chngd	---	---
Filter Changed		Client Info		Not Chngd	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
PQ		ASTM D8184		10	---	---
Iron	ppm	ASTM D5185m	>20	4	---	---
Chromium	ppm	ASTM D5185m	>10	4	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	<1	---	---
Lead	ppm	ASTM D5185m	>10	<1	---	---
Copper	ppm	ASTM D5185m	>75	1	---	---
Tin	ppm	ASTM D5185m	>10	<1	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION












The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>20	2	---	---
Potassium	ppm	ASTM D5185m	>20	1	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	957	---	---
Particles >6µm		ASTM D7647	>1300	102	---	---
Particles >14µm		ASTM D7647	>160	9	---	---
Particles >21µm		ASTM D7647	>40	1	---	---
Particles >38µm		ASTM D7647	>10	0	---	---
Particles >71µm		ASTM D7647	>3	0	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	17/14/10	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		2	---	---
Boron	ppm	ASTM D5185m		0	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		<1	---	---
Manganese	ppm	ASTM D5185m		0	---	---
Magnesium	ppm	ASTM D5185m		4	---	---
Calcium	ppm	ASTM D5185m	87	314	---	---
Phosphorus	ppm	ASTM D5185m	727	735	---	---
Zinc	ppm	ASTM D5185m	900	913	---	---
Sulfur	ppm	ASTM D5185m	1500	2001	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.65	---	---
Visc @ 40°C	cSt	ASTM D445	65	55.5	---	---

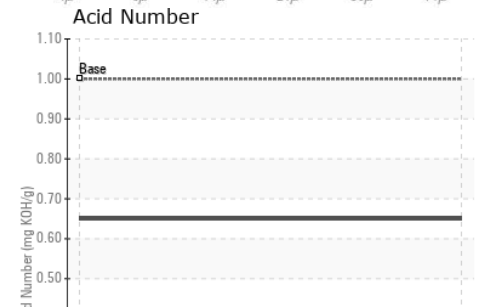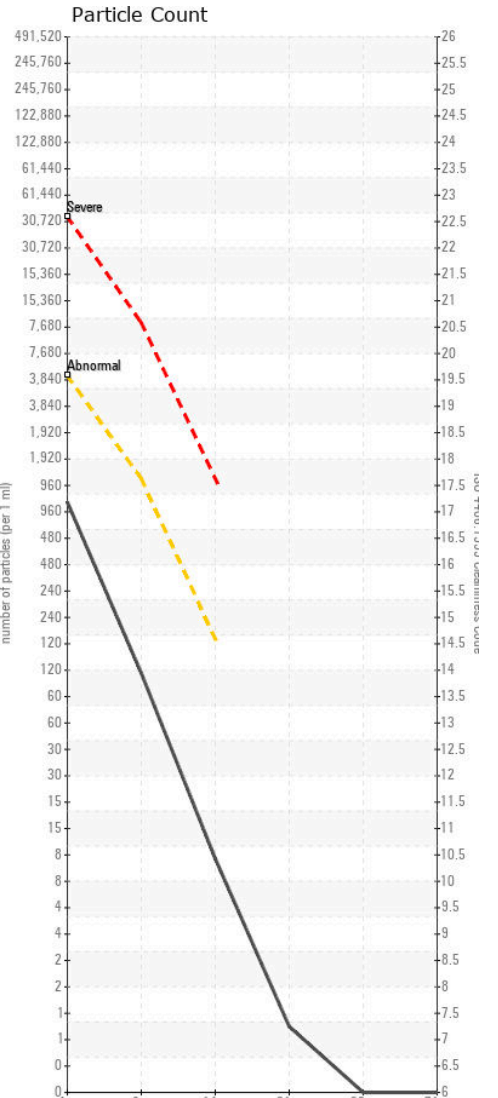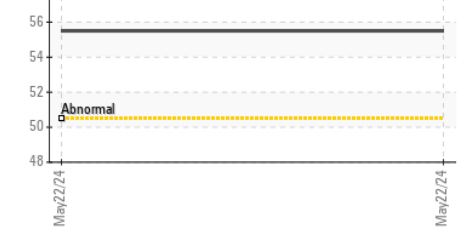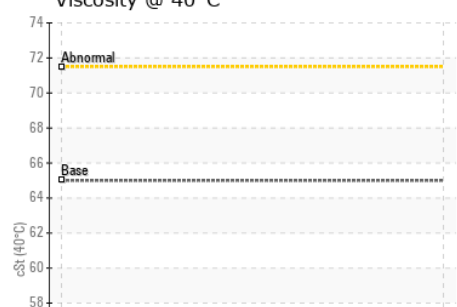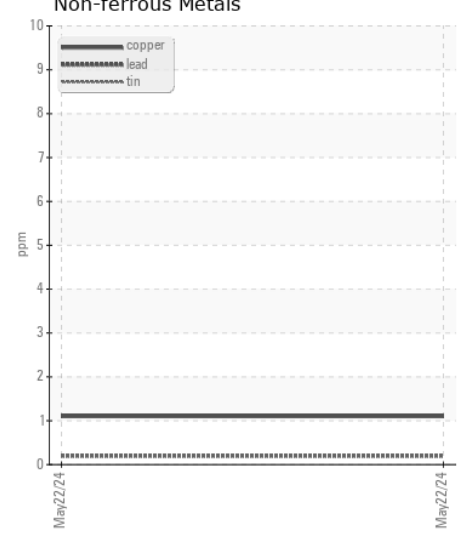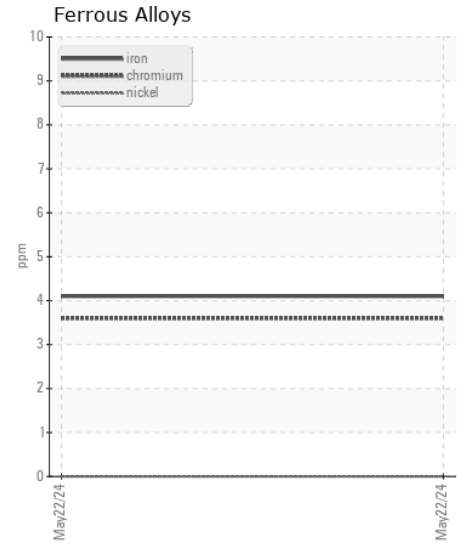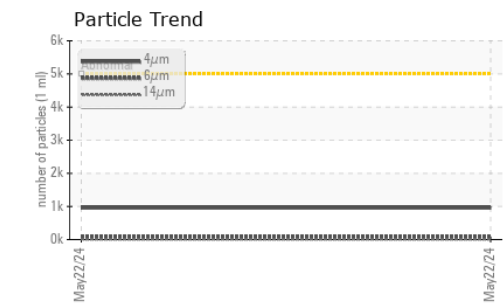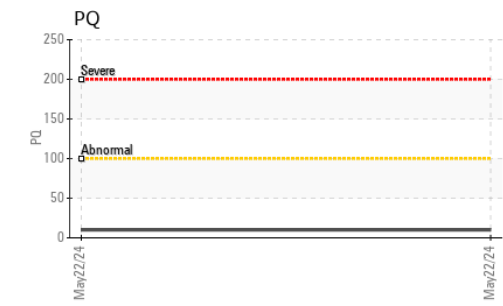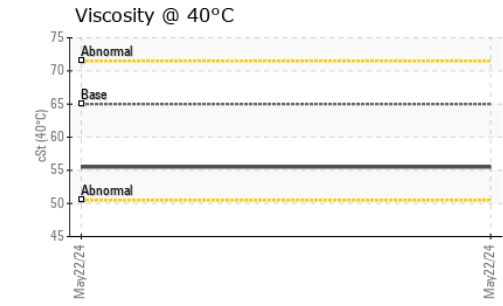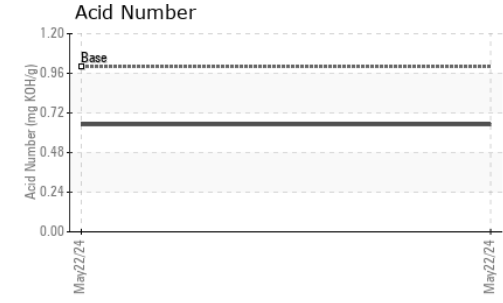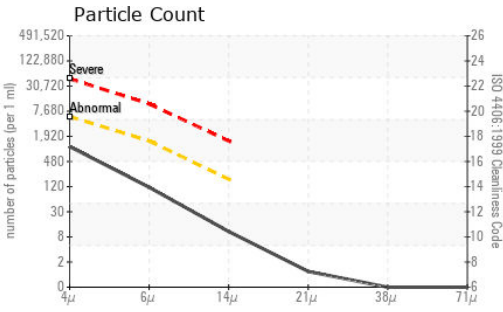

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WE0007442 **Received** : 30 May 2024
Lab Number : 06195325 **Tested** : 31 May 2024
Unique Number : 11057448 **Diagnosed** : 31 May 2024 - Wes Davis
Test Package : CONST (Additional Tests: PQ)

WARRIOR TRACTOR AND EQUIPMENT - MONROEVILLE
 66 INDUSTRIAL PARK DR
 MONROEVILLE, AL
 US 36460
 Contact: SCOTT WILLIAMSON
 swilliamson@warriortractor.com
 T: (251)575-7111
 F:

Certificate L2367
 To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)