



WEAR CHECK

OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	SEVERE
FLUID CONDITION	ABNORMAL

Machine Id
7701
 Component
Diesel Engine
 Fluid
DIESEL ENGINE OIL SAE 15W40 (--- GAL)

RECOMMENDATION

We advise that you check the fuel injection system. The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition. Please specify the component make and model with your next sample. Please specify the brand, type, and viscosity of the oil on your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0887560	WC0860380	WC0827018
Sample Date		Client Info		22 May 2024	31 Oct 2023	13 Jun 2023
Machine Age	mls	Client Info		452481	443070	441695
Oil Age	mls	Client Info		0	6000	0
Filter Age	mls	Client Info		0	6000	0
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				SEVERE	SEVERE	ABNORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	14	8	13
Chromium	ppm	ASTM D5185m	>20	<1	<1	<1
Nickel	ppm	ASTM D5185m	>4	0	<1	0
Titanium	ppm	ASTM D5185m		0	<1	<1
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m	>20	2	2	<1
Lead	ppm	ASTM D5185m	>40	<1	<1	0
Copper	ppm	ASTM D5185m	>330	1	<1	<1
Tin	ppm	ASTM D5185m	>15	<1	0	0
Vanadium	ppm	ASTM D5185m		0	<1	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION









There is a high amount of fuel present in the oil. Tests confirm the presence of fuel in the oil.

Silicon	ppm	ASTM D5185m	>25	9	8	8
Potassium	ppm	ASTM D5185m	>20	<1	1	2
Fuel	%	ASTM D3524	>5	▲ 9.1	▲ 10.8	▲ 7.7
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	1	1	0.9
Nitration	Abs/cm	*ASTM D7624	>20	11.0	10.9	11.8
Sulfation	Abs/.1mm	*ASTM D7415	>30	23.2	22.3	24.8
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.

Sodium	ppm	ASTM D5185m	>158	13	6	6
Boron	ppm	ASTM D5185m	250	53	14	16
Barium	ppm	ASTM D5185m	10	0	0	0
Molybdenum	ppm	ASTM D5185m	100	72	73	69
Manganese	ppm	ASTM D5185m		<1	<1	0
Magnesium	ppm	ASTM D5185m	450	249	295	245
Calcium	ppm	ASTM D5185m	3000	1619	1766	1849
Phosphorus	ppm	ASTM D5185m	1150	934	973	958
Zinc	ppm	ASTM D5185m	1350	1088	1197	1183
Sulfur	ppm	ASTM D5185m	4250	3381	3195	3768
Oxidation	Abs/.1mm	*ASTM D7414	>25	19.7	18.8	22.4
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	6.1	7.2	5.9
Visc @ 100°C	cSt	ASTM D445	14.4	▲ 11.4	▲ 12.2	▲ 11.5

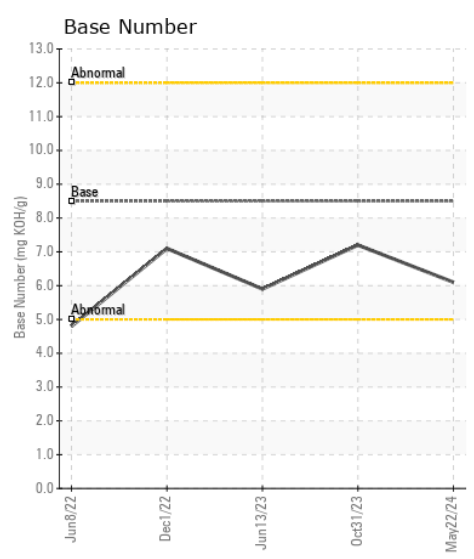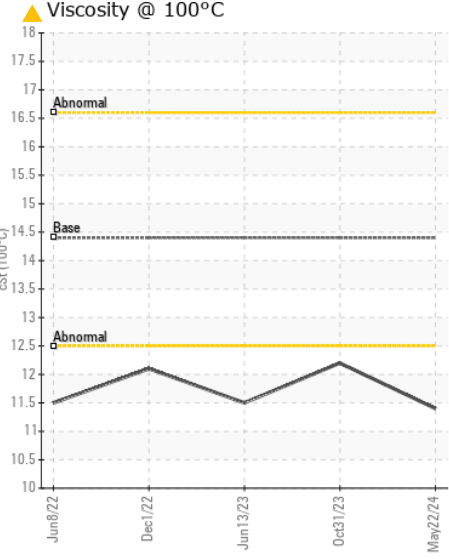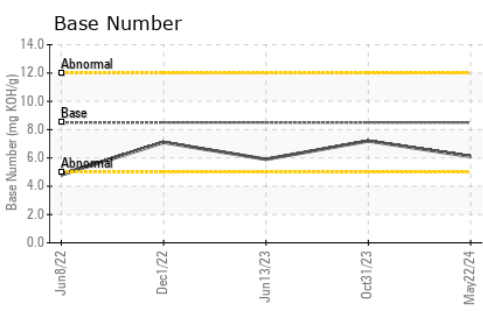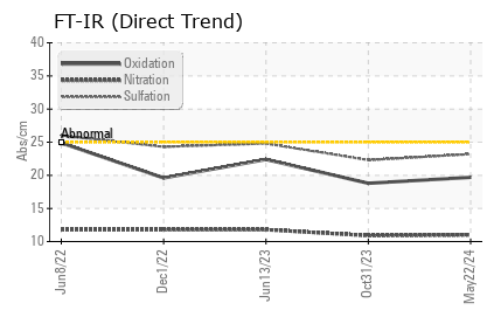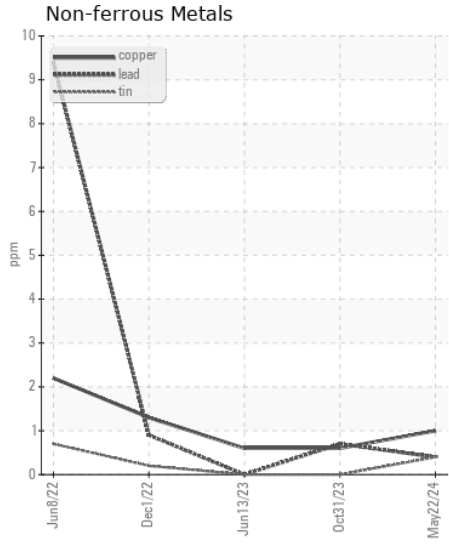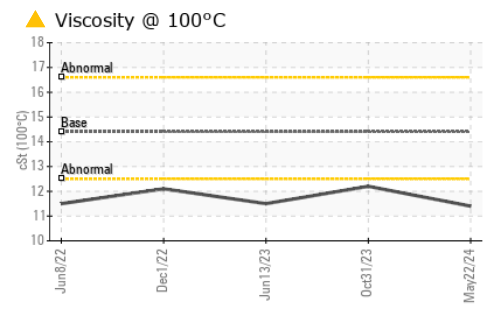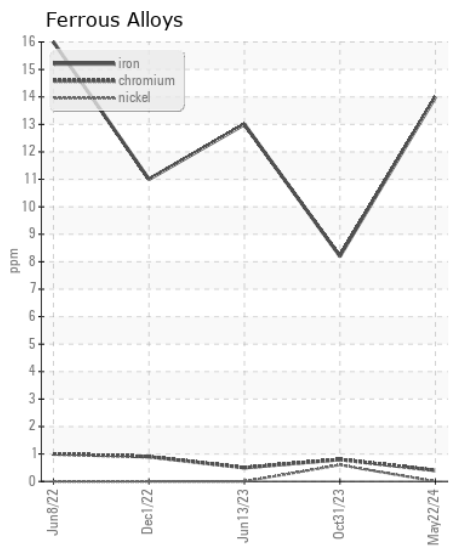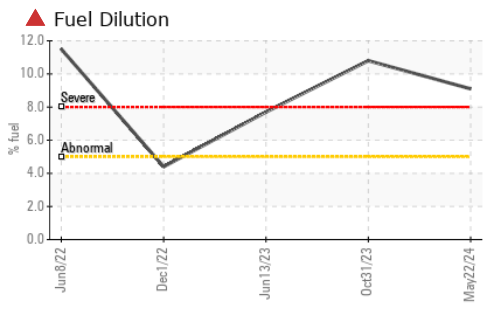

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0887560 **Received** : 31 May 2024
Lab Number : 06196197 **Tested** : 05 Jun 2024
Unique Number : 11058320 **Diagnosed** : 05 Jun 2024 - Wes Davis
Test Package : FLEET (Additional Tests: PercentFuel)

TOWN OF CHAPEL HILL
 6900 MILLHOUSE RD
 CHAPEL HILL, NC
 US 27516
 Contact: Lisa DePasqua
 ldepasqua@townofchapelhill.org
 T: (919)696-4941
 F:

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)