

Machine Id JOHN DEERE 325G 1T0325GKEMJ407224 Component Diesel Engine Fluid DIESEL ENGINE OIL SAE 30 (--- GAL)

| DIESEL ENGINE OIL SAE SU (GAL) | | | | | | | |
|--|-------------------------|----------|----------------------------|-----------|-------------|----------|----------|
| RECOMMENDATION | Test | UOM | Method | Limit/Abn | Current | History1 | History2 |
| Resample at the next service interval to monitor. The fluid was not specified, however, a fluid match indicates that this fluid is (GENERIC) DIESEL ENGINE OIL SAE 30. Please confirm. | Sample Number | | Client Info | | JR0212854 | | |
| | Sample Date | | Client Info | | 29 May 2024 | | |
| | Machine Age | hrs | Client Info | | 497 | | |
| | Oil Age | hrs | Client Info | | 0 | | |
| | Filter Age | hrs | Client Info | | 0 | | |
| | Oil Changed | 1110 | Client Info | | Changed | | |
| | Filter Changed | | Client Info | | Changed | | |
| | Sample Status | | | | NORMAL | | |
| | | | | | | | |
| WEAR Metal levels are typical for a new component breaking in. | Iron | ppm | ASTM D5185m | >51 | 9 | | |
| | Chromium | ppm | ASTM D5185m | >11 | <1 | | |
| | Nickel | ppm | ASTM D5185m | >5 | <1 | | |
| | Titanium | ppm | ASTM D5185m | | <1 | | |
| | Silver | ppm | ASTM D5185m | >3 | <1 | | |
| | Aluminum | ppm | ASTM D5185m | >31 | 3 | | |
| | Lead | ppm | ASTM D5185m | >26 | <1 | | |
| | Copper | ppm | ASTM D5185m | >26 | 7 | | |
| | Tin | ppm | ASTM D5185m | >4 | <1 | | |
| | Vanadium | ppm | ASTM D5185m | | <1 | | |
| | White Metal | scalar | *Visual | NONE | NONE | | |
| | Yellow Metal | scalar | *Visual | NONE | NONE | | |
| | | | | | | | |
| CONTAMINATION | Silicon | ppm | ASTM D5185m | >22 | 19 | | |
| There is no indication of any contamination in the oil. | Potassium | ppm | ASTM D5185m | >20 | 3 | | |
| | Fuel | % | ASTM D3524 | | <1.0 | | |
| | Water | | WC Method | >0.21 | NEG | | |
| | Glycol | | WC Method | | NEG | | |
| | Soot % | % | *ASTM D7844 | >3 | 0.2 | | |
| | Nitration | Abs/cm | | >20 | 7.9 | | |
| | Sulfation | Abs/.1mm | *ASTM D7415 | >30 | 20.9 | | |
| | Silt | scalar | *Visual | NONE | NONE | | |
| | Debris | scalar | *Visual | NONE | NONE | | |
| | Sand/Dirt | scalar | *Visual | NONE | NONE | | |
| | Appearance | scalar | *Visual | NORML | NORML | | |
| | Odor | scalar | *Visual | NORML | NORML | | |
| | Emulsified Water | scalar | *Visual | >0.21 | NEG | | |
| | Sodium | nnm | ASTM D5185m | . 75 | 2 | | |
| FLUID CONDITION | Sodium | ppm | | | | | |
| The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service. | Boron | ppm | ASTM D5185m ASTM D5185m | | 307 | | |
| | Barium | ppm | | | <1 116 | | |
| | Molybdenum Manganese | ppm | ASTM D5185m ASTM D5185m | 100 | 116 | | |
| | - | ppm | | 150 | <1 426 | | |
| | Magnesium | ppm | ASTM D5185m | | | | |
| | Calcium Phosphorus | ppm | ASTM D5185m ASTM D5185m | | 1566 | | |
| | | ppm | | | 935 | | |
| | Zinc | ppm | ASTM D5185m | 1350 | 1084 | | |

Sulfur

Oxidation

Visc @ 100°C cSt

ppm ASTM D5185m 4250

Abs/.1mm *ASTM D7414 >25

ASTM D445 10.9


Base Number (BN) mg KOH/g ASTM D2896 8.5


3450

17.4

6.9

12.0

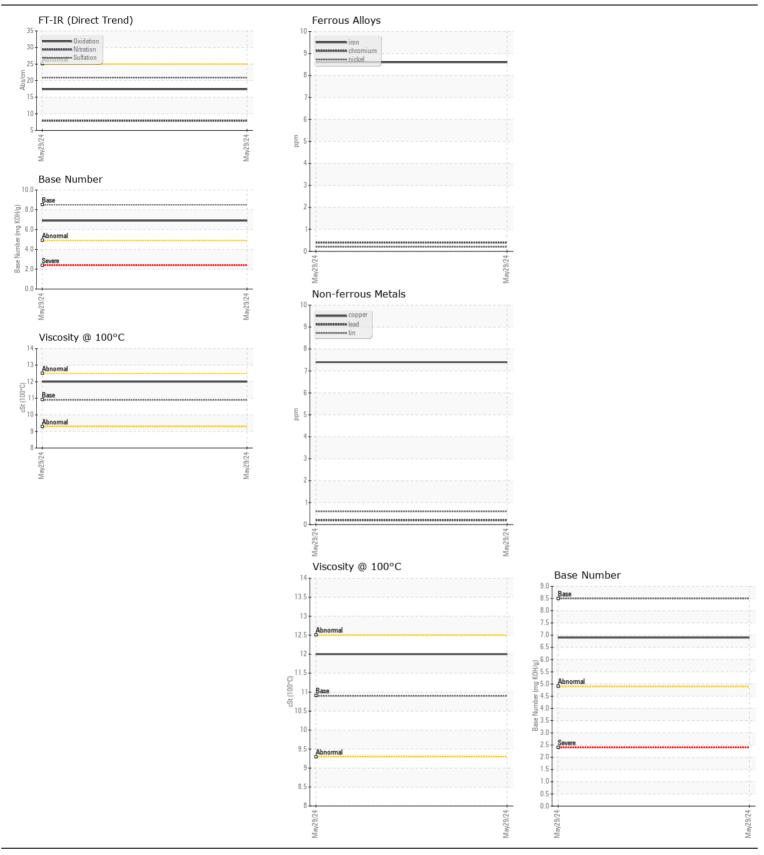



F:

Submitted By: Steven Bass Page 2 of 2