WEAR CONTAMINATION FLUID CONDITION

NORMAL

ABNORMAL

NORMAL


Area

[P&P EXCAVATING CORP] JCB 510-56 JCBKGPL01402245

Hydraulic System

{not provided} (--- GAL)

{iiot provided} (GAL)							
RECOMMENDATION	Test	UOM	Method	Limit/Abn	Current	History1	History2
We recommend you service the filters on this component. We recommend an early resample to monitor this condition. Please specify the brand, type, and viscosity of the oil on your next sample.	Sample Number	2 3	Client Info		JR0184418		
	Sample Date		Client Info		10 Jun 2024		
	Machine Age	hrs	Client Info		8600		
	Oil Age	hrs	Client Info		0		
	Filter Age	hrs	Client Info		0		
	Oil Changed	1110	Client Info		Not Changd		
	Filter Changed		Client Info		Not Change		
	Sample Status		0		ABNORMAL		
WEAR All component wear rates are normal.	PQ		ASTM D8184		18		
	Iron	ppm	ASTM D5185m	>20	8		
	Chromium	ppm	ASTM D5185m	>10	2		
	Nickel	ppm	ASTM D5185m	>10	0		
	Titanium	ppm	ASTM D5185m		<1		
	Silver	ppm	ASTM D5185m		0		
	Aluminum	ppm	ASTM D5185m	>10	2		
	Lead	ppm	ASTM D5185m	>10	2		
	Copper	ppm	ASTM D5185m	>75	2		
	Tin	ppm	ASTM D5185m	>10	0		
	Vanadium	ppm	ASTM D5185m		0		
	White Metal	scalar	*Visual	NONE	NONE		
	Yellow Metal	scalar	*Visual	NONE	NONE		
CONTABINATION	0.1.		AOTA DE LOS		•		
CONTAMINATION	Silicon	ppm	ASTM D5185m		8		
There is a moderate amount of silt (particulates < 14 microns in size) present in the oil.	Potassium	ppm	ASTM D5185m		2		
	Water		WC Method		NEG		
	Particles >4µm		ASTM D7647		<u>^</u> 20915		
	Particles >6µm		ASTM D7647		995		
	Particles >14µm		ASTM D7647		7		
	Particles >21µm		ASTM D7647		0		
	Particles >38µm		ASTM D7647		0		
	Particles >71µm		ASTM D7647		0		
	Oil Cleanliness	!	ISO 4406 (c)		<u>A 22/17/10</u>		
	Silt Debris	scalar	*Visual	NONE	NONE		
	Sand/Dirt	scalar	*Visual	NONE	NONE		
		scalar	*Visual	NONE	NONE NORML		
	Appearance	scalar	*Visual *Visual	NORML	_		
	Odor Emulsified Water	scalar	*Visual	NORML	NORML NEG		
		Scalai	VISUAI	>0.1	NEG		
FLUID CONDITION	Sodium	ppm	ASTM D5185m		0		
	Boron	ppm	ASTM D5185m		31		
The AN level is acceptable for this fluid. The oil is still serviceable	Barium	ppm	ASTM D5185m		<1		
provided that the contaminant(s) can be reduced to acceptable levels.	Molybdenum	ppm	ASTM D5185m		<1		
	Manganese	ppm	ASTM D5185m		0		
	Magnesium	ppm	ASTM D5185m		13		
	Calcium	ppm	ASTM D5185m		1364		
	Phosphorus	ppm	ASTM D5185m		614		
	Zinc	ppm	ASTM D5185m		739		
	Sulfur	ppm	ASTM D5185m		2414		
	Acid Number (AN)	mg KOH/g	ASTM D8045		0.50		
	Visc @ 40°C	cSt	ASTM D445		41.5		

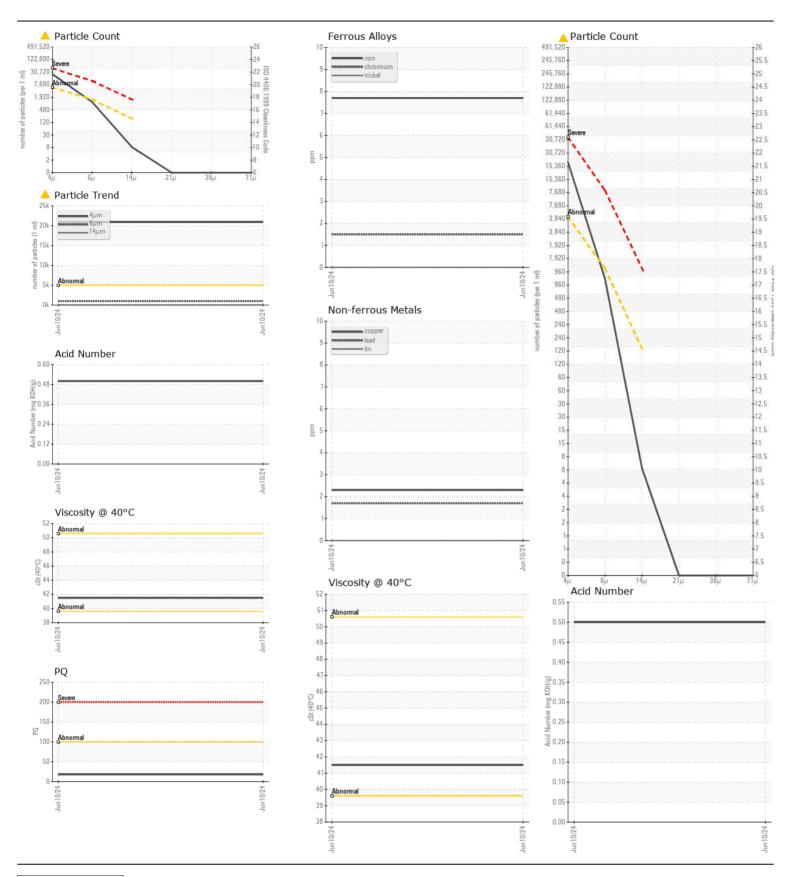



Certificate L2367

Laboratory Sample No. Lab Number

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 : JR0184418 : 06210686

Unique Number : 11083550

Received : 14 Jun 2024 **Tested** Diagnosed

: 18 Jun 2024 : 18 Jun 2024 - Wes Davis

JRE - STEPHENSON 245 YARDMASTER COURT STEPHENSON, VA US 22656-1761

Contact: PHIL DAUGHERTY pdaugherty@jamesriverequipment.com

To discuss this sample report, contact Customer Service at 1-800-237-1369. * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Test Package : CONST (Additional Tests: PQ)

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012) F: (540)869-0549

T: