



VOLVO

OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Machine Id
VOLVO A40G 352198
Component
Diesel Engine
Fluid
MOBIL 15W40 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		VCP447481	VCP435446	VCP435151
Sample Date		Client Info		07 Jun 2024	29 Apr 2024	02 Apr 2024
Machine Age	hrs	Client Info		5957	5700	5479
Oil Age	hrs	Client Info		257	221	265
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	4	2	4
Chromium	ppm	ASTM D5185m	>20	0	0	<1
Nickel	ppm	ASTM D5185m	>2	<1	0	1
Titanium	ppm	ASTM D5185m		0	0	<1
Silver	ppm	ASTM D5185m	>2	0	0	<1
Aluminum	ppm	ASTM D5185m	>25	1	2	3
Lead	ppm	ASTM D5185m	>40	0	0	<1
Copper	ppm	ASTM D5185m	>330	<1	1	<1
Tin	ppm	ASTM D5185m	>15	0	<1	<1
Vanadium	ppm	ASTM D5185m		0	0	<1
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION












There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>25	5	5	6
Potassium	ppm	ASTM D5185m	>20	<1	<1	2
Fuel		WC Method	>6.0	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.1	0.1	0.1
Nitration	Abs/cm	*ASTM D7624	>20	6.2	6.2	7.3
Sulfation	Abs/.1mm	*ASTM D7415	>30	21.8	20.9	20.0
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>118	2	2	2
Boron	ppm	ASTM D5185m		56	77	91
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		43	54	74
Manganese	ppm	ASTM D5185m		0	<1	0
Magnesium	ppm	ASTM D5185m		578	549	551
Calcium	ppm	ASTM D5185m		1887	1733	1498
Phosphorus	ppm	ASTM D5185m		898	802	789
Zinc	ppm	ASTM D5185m		1032	928	893
Sulfur	ppm	ASTM D5185m		3388	3131	3220
Oxidation	Abs/.1mm	*ASTM D7414	>25	19.5	18.4	17.6
Base Number (BN)	mg KOH/g	ASTM D2896		10.0	9.4	8.8
Visc @ 100°C	cSt	ASTM D445		12.5	12.7	12.7

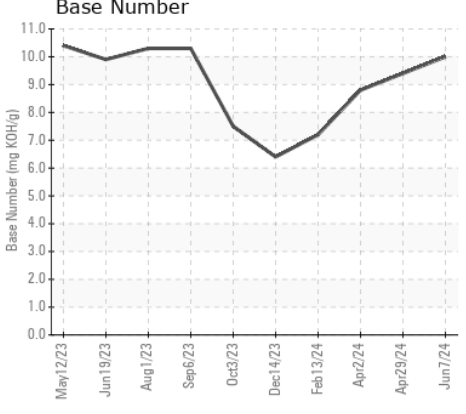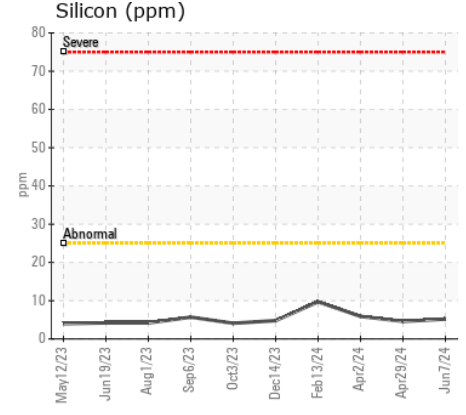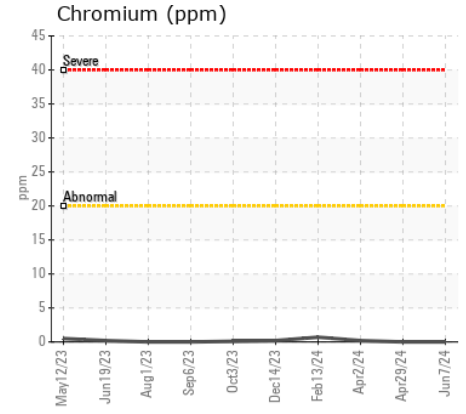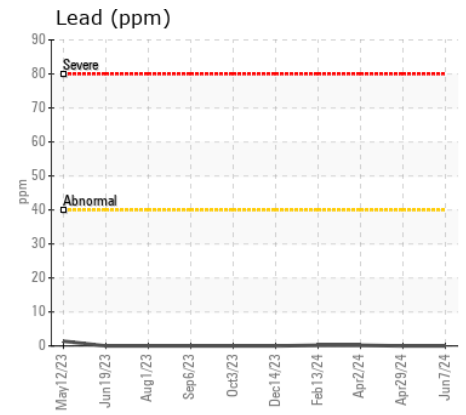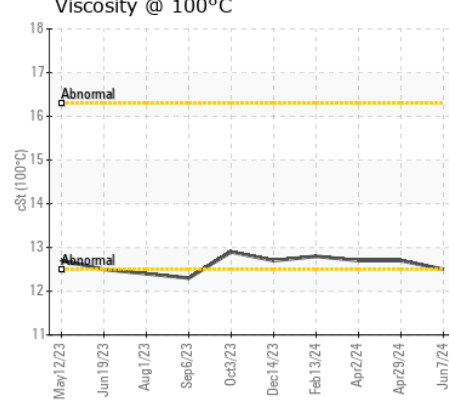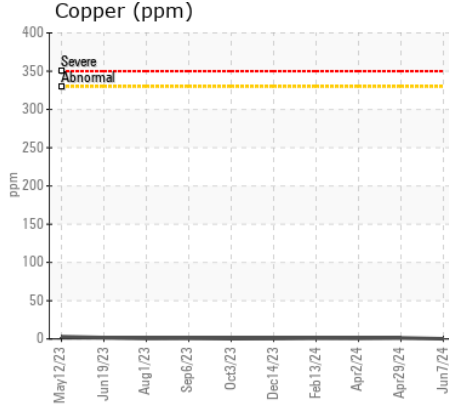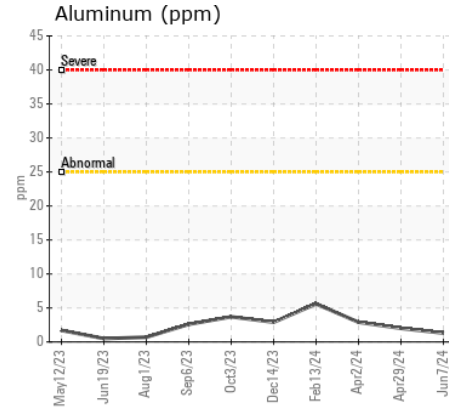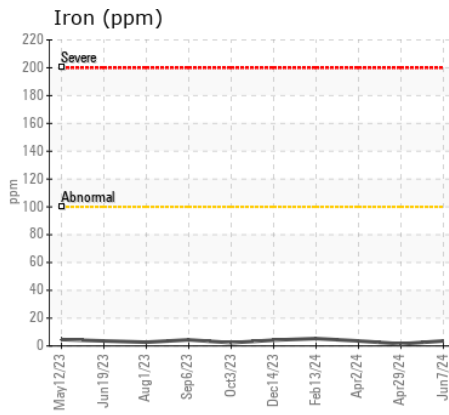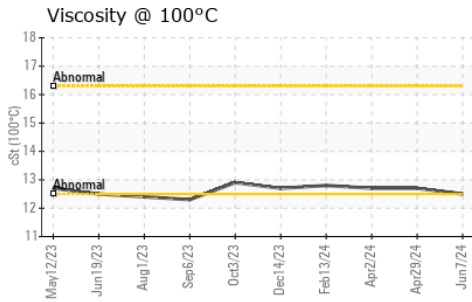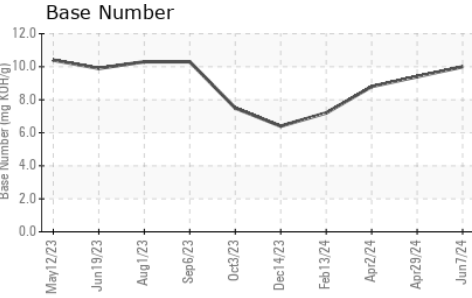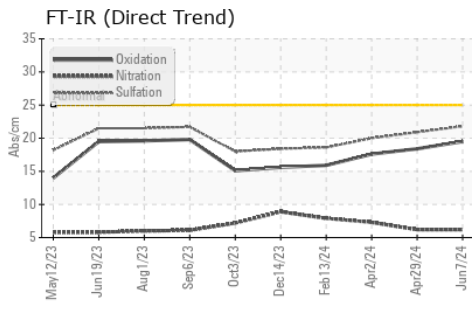

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : VCP447481 **Received** : 17 Jun 2024
Lab Number : 06211228 **Tested** : 19 Jun 2024
Unique Number : 11084092 **Diagnosed** : 19 Jun 2024 - Wes Davis
Test Package : MOB 1 (Additional Tests: TBN)

SCHILDBERG CONSTRUCTION COMPANY
 PO BOX 358
 GREENFIELD, IA
 US 50849
 Contact: SCOTT ARMSTRONG
 sarmstrong@schildberg.com
 T: (641)743-8237
 F: (641)743-2486

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)