



WEAR	ABNORMAL
CONTAMINATION	SEVERE
FLUID CONDITION	ABNORMAL

Machine Id
WC TRANS
 Component
Diesel Engine
 Fluid
DIESEL ENGINE OIL SAE 15W40 (--- QTS)

RECOMMENDATION

We advise that you check for the source of the coolant leak. Check for low coolant level. We recommend that you drain the oil and perform a filter service on this component if not already done. We recommend an early resample to monitor this condition.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		IL0020788	---	---
Sample Date		Client Info		13 Jun 2024	---	---
Machine Age	mls	Client Info		654268	---	---
Oil Age	mls	Client Info		0	---	---
Filter Age	mls	Client Info		0	---	---
Oil Changed		Client Info		N/A	---	---
Filter Changed		Client Info		N/A	---	---
Sample Status				SEVERE	---	---

WEAR

The lead level is abnormal. All other component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	43	---	---
Chromium	ppm	ASTM D5185m	>20	<1	---	---
Nickel	ppm	ASTM D5185m	>4	2	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m	>3	0	---	---
Aluminum	ppm	ASTM D5185m	>20	6	---	---
Lead	ppm	ASTM D5185m	>40	▲ 48	---	---
Copper	ppm	ASTM D5185m	>330	8	---	---
Tin	ppm	ASTM D5185m	>15	8	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION














Sodium and/or potassium levels are high. There is a high concentration of glycol present in the oil.

Silicon	ppm	ASTM D5185m	>25	9	---	---
Potassium	ppm	ASTM D5185m	>20	▲ 1691	---	---
Fuel		WC Method	>5	<1.0	---	---
Water		WC Method	>0.2	NEG	---	---
Glycol	%	*ASTM D2982		▲ 0.20	---	---
Soot %	%	*ASTM D7844	>3	0.6	---	---
Nitration	Abs/cm	*ASTM D7624	>20	18.7	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	24.5	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---	---

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The oil is no longer serviceable due to the presence of contaminants.

Sodium	ppm	ASTM D5185m	>158	▲ 1675	---	---
Boron	ppm	ASTM D5185m	250	26	---	---
Barium	ppm	ASTM D5185m	10	1	---	---
Molybdenum	ppm	ASTM D5185m	100	309	---	---
Manganese	ppm	ASTM D5185m		2	---	---
Magnesium	ppm	ASTM D5185m	450	426	---	---
Calcium	ppm	ASTM D5185m	3000	1073	---	---
Phosphorus	ppm	ASTM D5185m	1150	785	---	---
Zinc	ppm	ASTM D5185m	1350	717	---	---
Sulfur	ppm	ASTM D5185m	4250	3363	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	16.8	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	18.2	---	---
Visc @ 100°C	cSt	ASTM D445	14.4	15.2	---	---

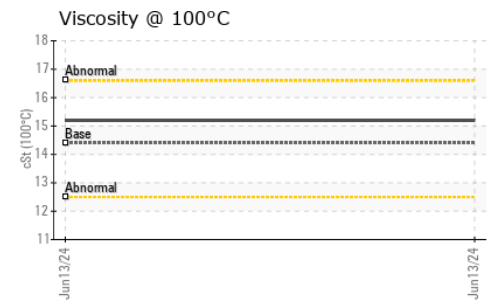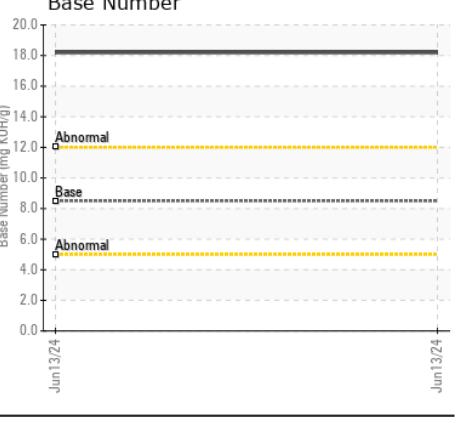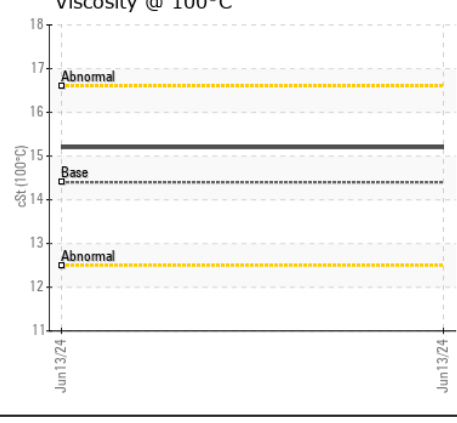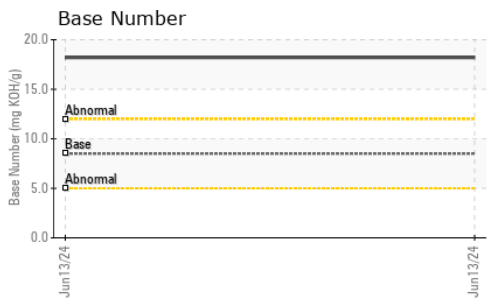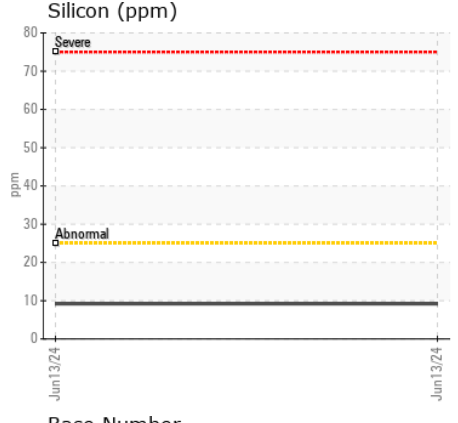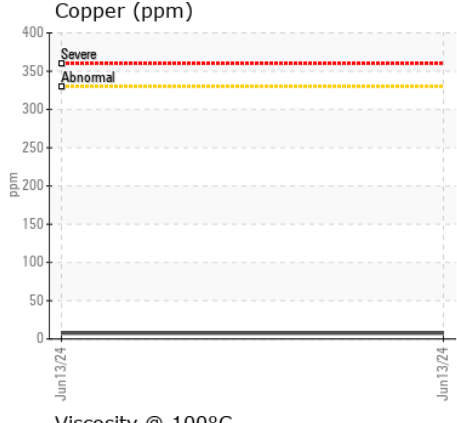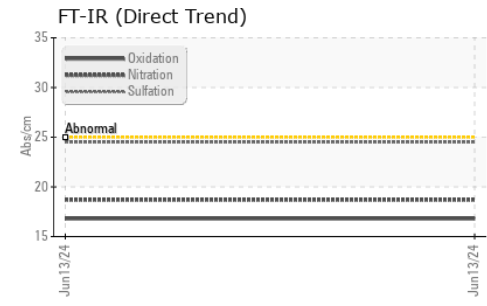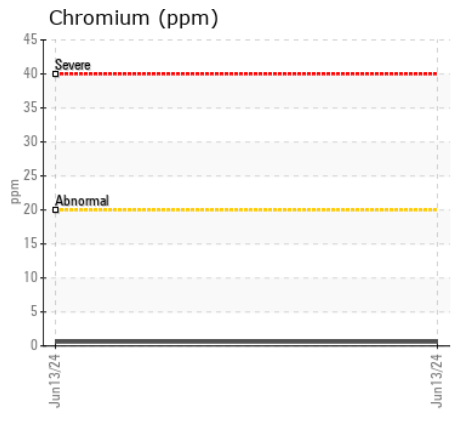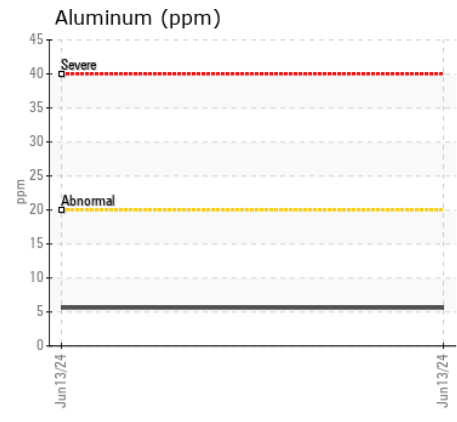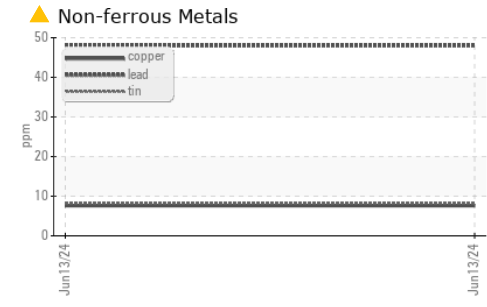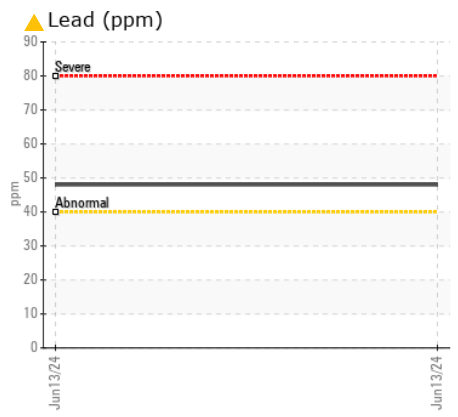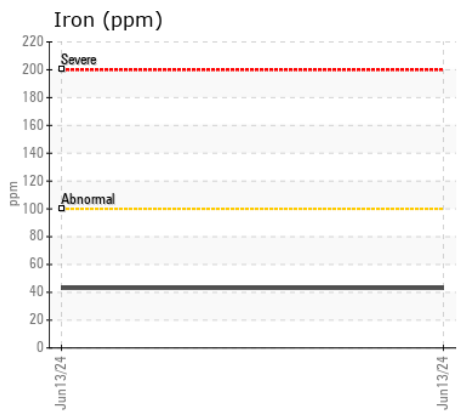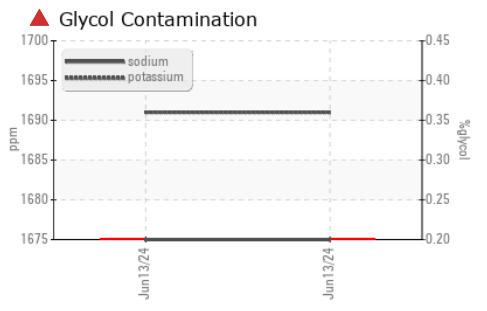

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : IL0020788 **Received** : 17 Jun 2024
Lab Number : 06211339 **Tested** : 20 Jun 2024
Unique Number : 11084203 **Diagnosed** : 20 Jun 2024 - Jonathan Hester
Test Package : MOB1+ (Additional Tests: Glycol)

BLUEGRASS IDEALEASE
 101 TRIPORT CIRCLE
 GEORGETOWN, KY
 US 40324-9619
 Contact: Leann Mitchell
 lmitchell@bluegrasstrucks.com
 T: (502)570-5252
 F: (502)863-3166

Certificate L2367
 To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)