



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
FREIGHTLINER 46111
Component
Diesel Engine
Fluid
MOBIL 15W40 (--- QTS)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0946030	WC0795676	WC0794529
Sample Date		Client Info		10 Jun 2024	08 Nov 2023	05 May 2023
Machine Age	mls	Client Info		0	428142	410748
Oil Age	mls	Client Info		0	21196	25000
Filter Age	mls	Client Info		0	21196	25000
Oil Changed		Client Info		N/A	Changed	Changed
Filter Changed		Client Info		N/A	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>80	48	22	12
Chromium	ppm	ASTM D5185m	>5	2	1	<1
Nickel	ppm	ASTM D5185m	>2	<1	0	0
Titanium	ppm	ASTM D5185m		<1	0	0
Silver	ppm	ASTM D5185m	>3	<1	0	0
Aluminum	ppm	ASTM D5185m	>30	5	2	<1
Lead	ppm	ASTM D5185m	>30	6	6	2
Copper	ppm	ASTM D5185m	>150	2	<1	<1
Tin	ppm	ASTM D5185m	>5	<1	<1	<1
Vanadium	ppm	ASTM D5185m		<1	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION

There is no indication of any contamination in the oil.


Silicon	ppm	ASTM D5185m	>20	7	5	4
Potassium	ppm	ASTM D5185m	>20	2	<1	1
Fuel		WC Method	>5	<1.0	<1.0	<1.0
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.5	0.5	0.3
Nitration	Abs/cm	*ASTM D7624	>20	10.4	11.0	9.9
Sulfation	Abs/.1mm	*ASTM D7415	>30	23.3	23.0	19.8
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG

FLUID CONDITION


The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>118	<1	2	0
Boron	ppm	ASTM D5185m		98	6	4
Barium	ppm	ASTM D5185m		<1	0	2
Molybdenum	ppm	ASTM D5185m		87	62	65
Manganese	ppm	ASTM D5185m		<1	<1	<1
Magnesium	ppm	ASTM D5185m		685	932	932
Calcium	ppm	ASTM D5185m		1278	1130	1117
Phosphorus	ppm	ASTM D5185m		1057	1064	1053
Zinc	ppm	ASTM D5185m		1260	1303	1247
Sulfur	ppm	ASTM D5185m		3181	3187	3390
Oxidation	Abs/.1mm	*ASTM D7414	>25	19.4	19.1	15.7
Base Number (BN)	mg KOH/g	ASTM D2896		7.0	6.0	9.9
Visc @ 100°C	cSt	ASTM D445		13.5	13.6	13.0


FT-IR (Direct Trend)

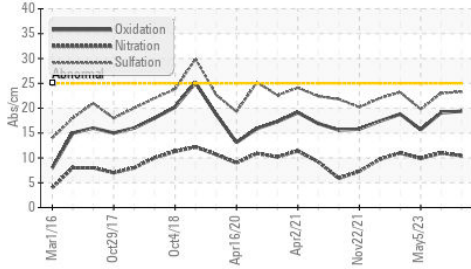


Ferrous Alloys

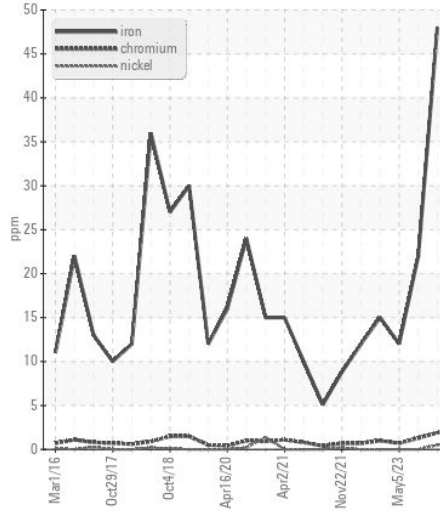


Base Number

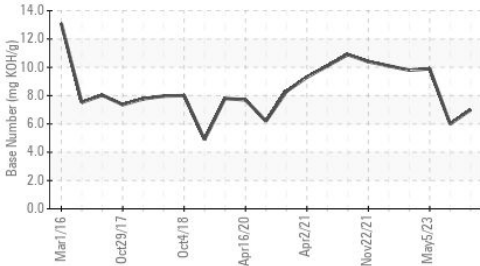


Non-ferrous Metals

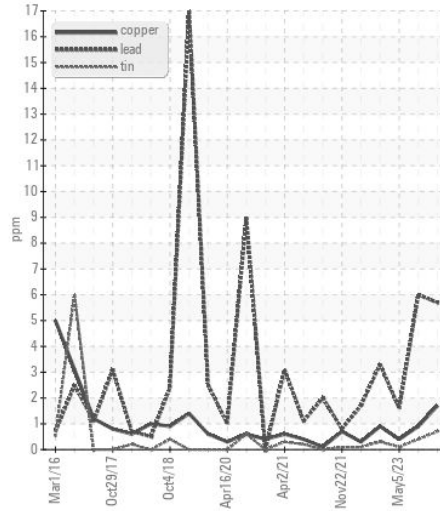


Viscosity @ 100°C

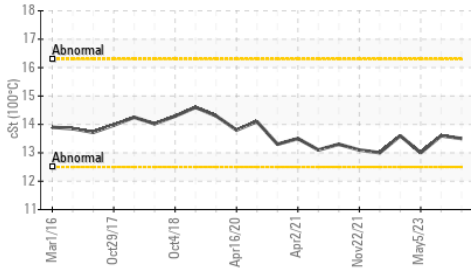

Viscosity @ 100°C

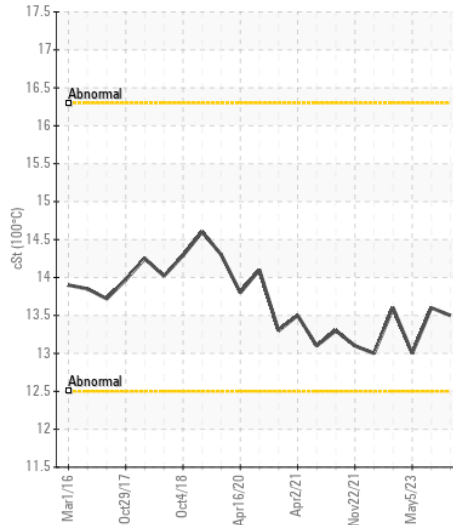

Base Number

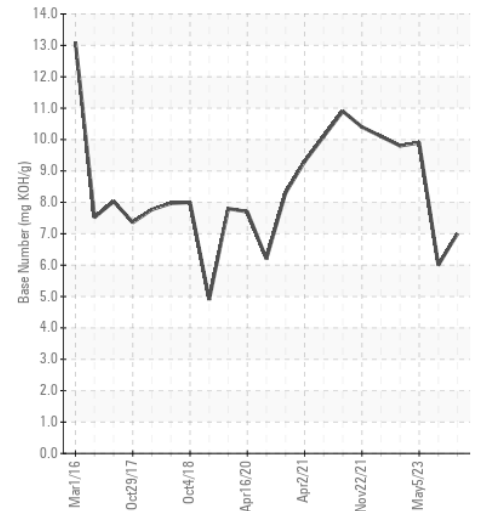

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0946030
Lab Number : 06213040
Unique Number : 11085904
Test Package : FLEET

Received : 17 Jun 2024
Tested : 19 Jun 2024
Diagnosed : 19 Jun 2024 - Wes Davis

SALEM NATIONALEASE CORPORATION
 198 PARK PLAZA DRIVE
 WINSTON SALEM, NC
 US 27105

Contact: Audrey Hopkins
 Audrey.Hopkins@salemcorp.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (336)767-9642

F: x: