



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	ABNORMAL

Machine Id
RBI 3107
 Component
Diesel Engine
 Fluid
DIESEL ENGINE OIL SAE 15W40 (--- QTS)

RECOMMENDATION

We advise that you check for the source of the coolant leak. Check for low coolant level. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0913603	WC0882837	---
Sample Date		Client Info		14 Jun 2024	24 Jan 2024	---
Machine Age	hrs	Client Info		8513	8286	---
Oil Age	hrs	Client Info		1000	750	---
Filter Age	hrs	Client Info		1000	750	---
Oil Changed		Client Info		Changed	Changed	---
Filter Changed		Client Info		Changed	Changed	---
Sample Status				ABNORMAL	NORMAL	---

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	40	37	---
Chromium	ppm	ASTM D5185m	>20	0	<1	---
Nickel	ppm	ASTM D5185m	>4	<1	<1	---
Titanium	ppm	ASTM D5185m		<1	<1	---
Silver	ppm	ASTM D5185m	>3	0	0	---
Aluminum	ppm	ASTM D5185m	>20	4	10	---
Lead	ppm	ASTM D5185m	>40	0	0	---
Copper	ppm	ASTM D5185m	>330	2	2	---
Tin	ppm	ASTM D5185m	>15	<1	<1	---
Vanadium	ppm	ASTM D5185m		0	0	---
White Metal	scalar	*Visual	NONE	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	---

CONTAMINATION

Sodium and/or potassium levels are high.


Silicon	ppm	ASTM D5185m	>25	9	7	---
Potassium	ppm	ASTM D5185m	>20	▲ 47	6	---
Fuel		WC Method	>5	<1.0	<1.0	---
Water		WC Method	>0.2	NEG	NEG	---
Glycol	%	*ASTM D2982		NEG	NEG	---
Soot %	%	*ASTM D7844	>3	0.5	0.6	---
Nitration	Abs/cm	*ASTM D7624	>20	7.1	9.5	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	20.6	22.5	---
Silt	scalar	*Visual	NONE	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	---

FLUID CONDITION


The BN result indicates that there is suitable alkalinity remaining in the oil.

Sodium	ppm	ASTM D5185m	>158	▲ 195	38	---
Boron	ppm	ASTM D5185m	250	279	240	---
Barium	ppm	ASTM D5185m	10	0	0	---
Molybdenum	ppm	ASTM D5185m	100	104	259	---
Manganese	ppm	ASTM D5185m		<1	<1	---
Magnesium	ppm	ASTM D5185m	450	449	846	---
Calcium	ppm	ASTM D5185m	3000	1363	1431	---
Phosphorus	ppm	ASTM D5185m	1150	1042	947	---
Zinc	ppm	ASTM D5185m	1350	1218	1097	---
Sulfur	ppm	ASTM D5185m	4250	3776	3059	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	13.5	17.0	---
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	7.6	8.5	---
Visc @ 100°C	cSt	ASTM D445	14.4	13.1	14.0	---


FT-IR (Direct Trend)

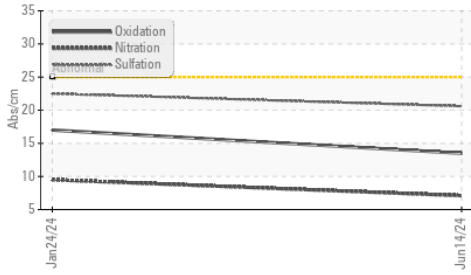


Base Number

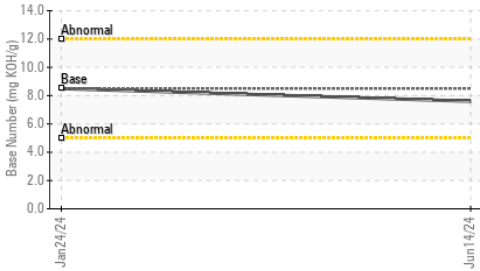


Viscosity @ 100°C

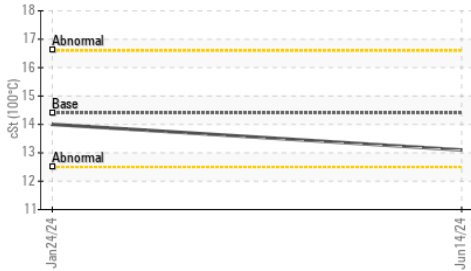


Glycol Contamination

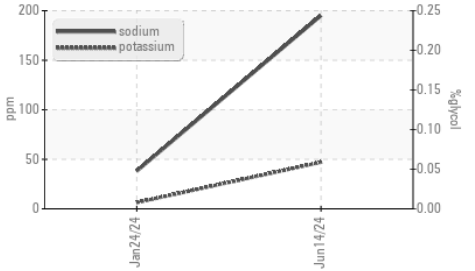


Ferrous Alloys

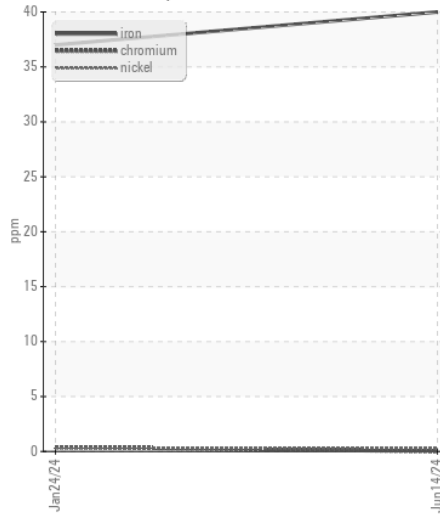


Non-ferrous Metals

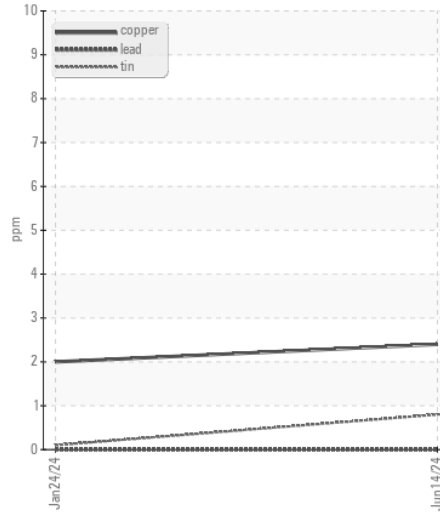

Viscosity @ 100°C

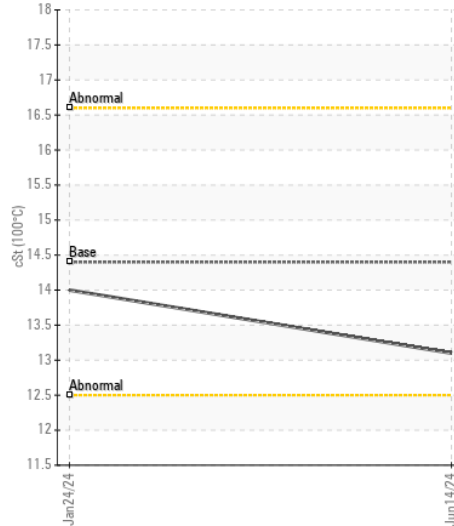

Base Number

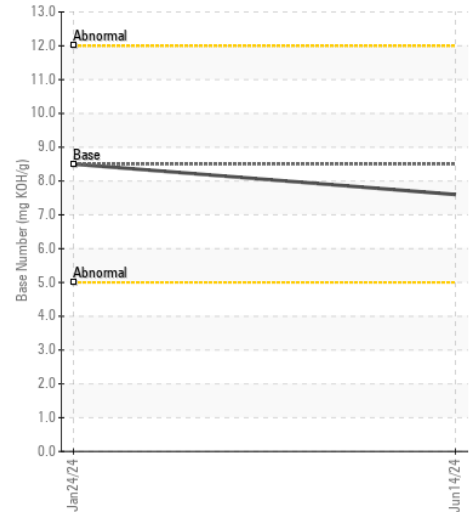

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0913603 **Received** : 19 Jun 2024
Lab Number : 06214501 **Tested** : 24 Jun 2024
Unique Number : 11087365 **Diagnosed** : 24 Jun 2024 - Jonathan Hester
Test Package : CONST (Additional Tests: Glycol, TBN)

SULLIVAN EASTERN INC
 2860 C SLATER RD
 MORRISVILLE, NC
 US 27560

Contact: SCOTT SULLIVAN
 ssullivan@sullivaneastern.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (919)484-8993

F: (919)484-2136