



WEAR	<b>NORMAL</b>
CONTAMINATION	<b>NORMAL</b>
FLUID CONDITION	<b>NORMAL</b>

Machine Id  
**SANY SY365CLC SY0365MCA00258**  
 Component  
**Swing Drive**  
 Fluid  
**GEAR OIL SAE 80W90 (--- GAL)**

### RECOMMENDATION

Resample at the next service interval to monitor. The fluid was not specified, however, a fluid match indicates that this fluid is (GENERIC) GEAR OIL SAE 80W90. Please confirm.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		<b>JR0220228</b>	---	---
Sample Date		Client Info		<b>17 Jun 2024</b>	---	---
Machine Age	hrs	Client Info		<b>4235</b>	---	---
Oil Age	hrs	Client Info		<b>0</b>	---	---
Filter Age	hrs	Client Info		<b>0</b>	---	---
Oil Changed		Client Info		<b>Changed</b>	---	---
Filter Changed		Client Info		<b>N/A</b>	---	---
Sample Status				<b>NORMAL</b>	---	---

### WEAR

All component wear rates are normal.

Test	UOM	Method	Limit/Abn	Current	History1	History2
PQ		ASTM D8184		<b>16</b>	---	---
Iron	ppm	ASTM D5185m	>400	<b>4</b>	---	---
Chromium	ppm	ASTM D5185m	>10	<b>0</b>	---	---
Nickel	ppm	ASTM D5185m	>10	<b>0</b>	---	---
Titanium	ppm	ASTM D5185m		<b>&lt;1</b>	---	---
Silver	ppm	ASTM D5185m		<b>0</b>	---	---
Aluminum	ppm	ASTM D5185m	>25	<b>0</b>	---	---
Lead	ppm	ASTM D5185m	>50	<b>0</b>	---	---
Copper	ppm	ASTM D5185m	>200	<b>&lt;1</b>	---	---
Tin	ppm	ASTM D5185m	>10	<b>0</b>	---	---
Vanadium	ppm	ASTM D5185m		<b>&lt;1</b>	---	---
White Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	---	---

### CONTAMINATION






There is no indication of any contamination in the oil.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Silicon	ppm	ASTM D5185m	>50	<b>2</b>	---	---
Potassium	ppm	ASTM D5185m	>20	<b>1</b>	---	---
Water		WC Method	>0.2	<b>NEG</b>	---	---
Silt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Debris	scalar	*Visual	NONE	<b>NONE</b>	---	---
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	---	---
Appearance	scalar	*Visual	NORML	<b>NORML</b>	---	---
Odor	scalar	*Visual	NORML	<b>NORML</b>	---	---
Emulsified Water	scalar	*Visual	>0.2	<b>NEG</b>	---	---

### FLUID CONDITION

The condition of the oil is acceptable for the time in service.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sodium	ppm	ASTM D5185m	>170	<b>3</b>	---	---
Boron	ppm	ASTM D5185m	400	<b>28</b>	---	---
Barium	ppm	ASTM D5185m	200	<b>0</b>	---	---
Molybdenum	ppm	ASTM D5185m	12	<b>0</b>	---	---
Manganese	ppm	ASTM D5185m		<b>&lt;1</b>	---	---
Magnesium	ppm	ASTM D5185m	12	<b>1</b>	---	---
Calcium	ppm	ASTM D5185m	150	<b>67</b>	---	---
Phosphorus	ppm	ASTM D5185m	1650	<b>802</b>	---	---
Zinc	ppm	ASTM D5185m	125	<b>17</b>	---	---
Sulfur	ppm	ASTM D5185m	22500	<b>22834</b>	---	---
Visc @ 40°C	cSt	ASTM D445	143	<b>159</b>	---	---

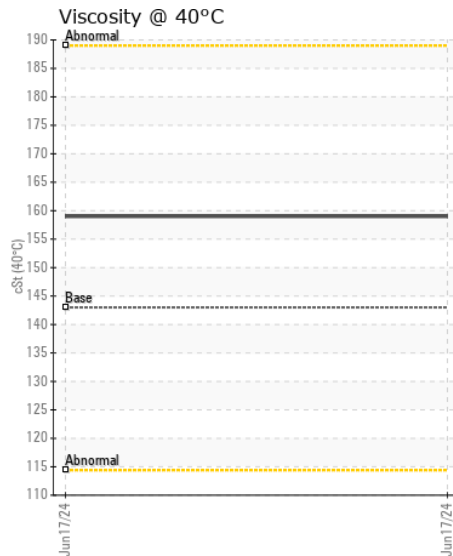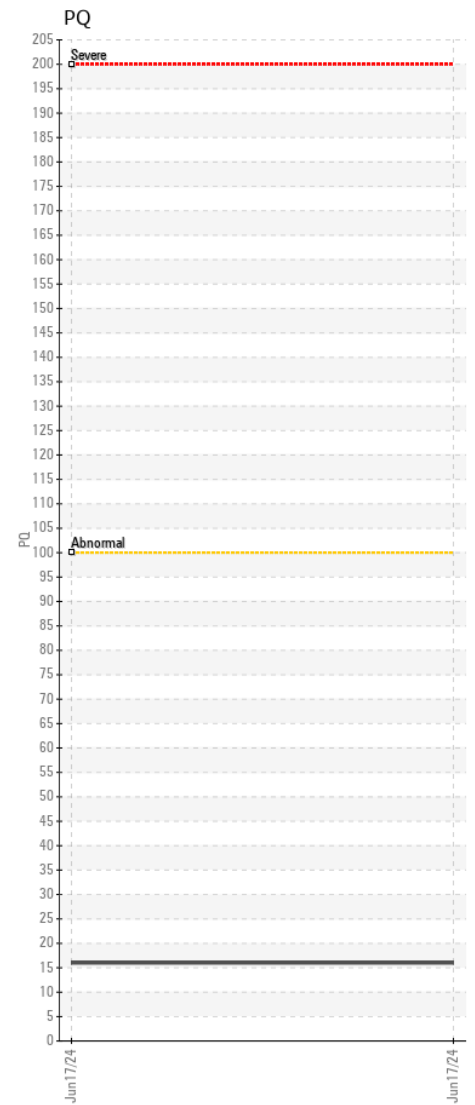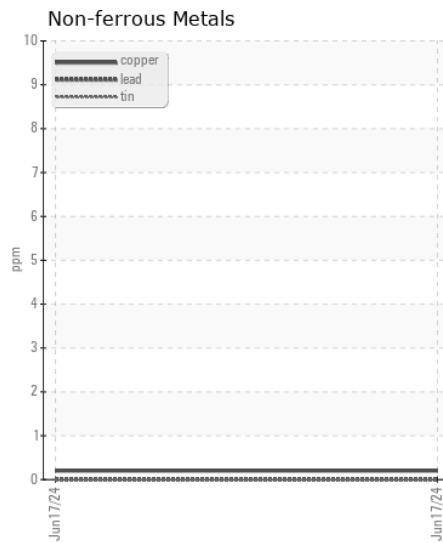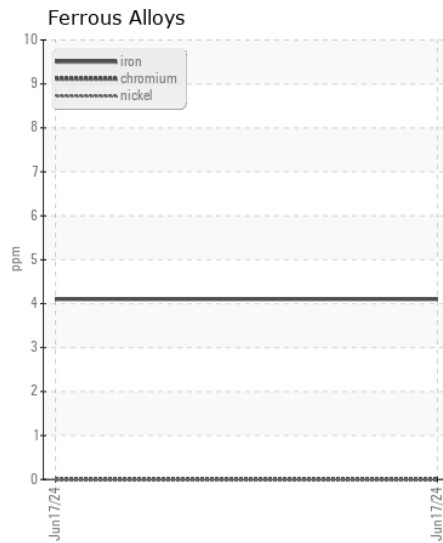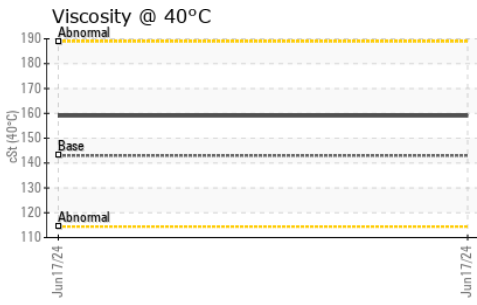

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513

**Sample No.** : JR0220228

**Lab Number** : 06215002

**Unique Number** : 11087866

**Test Package** : CONST ( Additional Tests: PQ )

**Received** : 19 Jun 2024

**Tested** : 20 Jun 2024

**Diagnosed** : 20 Jun 2024 - Wes Davis

**JRE - CHARLOTTE**

9550 STATESVILLE ROAD

CHARLOTTE, NC

US 28269

Contact: Chuck Sorrow

J.Sorrow@jamesriverequipment.com

T:

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

F: (704)596-6198