



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Machine Id
JOHN DEERE 700K 524 (S/N 1T0700KXTKF361562)
 Component
Diesel Engine
 Fluid
DIESEL ENGINE OIL SAE 40 (--- QTS)

RECOMMENDATION

Resample at the next service interval to monitor. The fluid was not specified, however, a fluid match indicates that this fluid is (GENERIC) DIESEL ENGINE OIL SAE 40. Please confirm.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0218287	---	---
Sample Date		Client Info		04 Jun 2024	---	---
Machine Age	hrs	Client Info		6918	---	---
Oil Age	hrs	Client Info		500	---	---
Filter Age	hrs	Client Info		500	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				NORMAL	---	---

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>51	42	---	---
Chromium	ppm	ASTM D5185m	>11	1	---	---
Nickel	ppm	ASTM D5185m	>5	3	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m	>3	0	---	---
Aluminum	ppm	ASTM D5185m	>31	3	---	---
Lead	ppm	ASTM D5185m	>26	<1	---	---
Copper	ppm	ASTM D5185m	>26	2	---	---
Tin	ppm	ASTM D5185m	>4	<1	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION








There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>22	9	---	---
Potassium	ppm	ASTM D5185m	>20	8	---	---
Fuel		WC Method	>2.1	<1.0	---	---
Water		WC Method	>0.21	NEG	---	---
Glycol		WC Method		NEG	---	---
Soot %	%	*ASTM D7844	>3	0.4	---	---
Nitration	Abs/cm	*ASTM D7624	>20	9.3	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	23.0	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.21	NEG	---	---

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>216	2	---	---
Boron	ppm	ASTM D5185m	250	62	---	---
Barium	ppm	ASTM D5185m	10	0	---	---
Molybdenum	ppm	ASTM D5185m	100	27	---	---
Manganese	ppm	ASTM D5185m		<1	---	---
Magnesium	ppm	ASTM D5185m	450	137	---	---
Calcium	ppm	ASTM D5185m	3000	2176	---	---
Phosphorus	ppm	ASTM D5185m	1150	1017	---	---
Zinc	ppm	ASTM D5185m	1350	1222	---	---
Sulfur	ppm	ASTM D5185m	4250	3411	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	18.0	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	5.7	---	---
Visc @ 100°C	cSt	ASTM D445	14.4	13.5	---	---

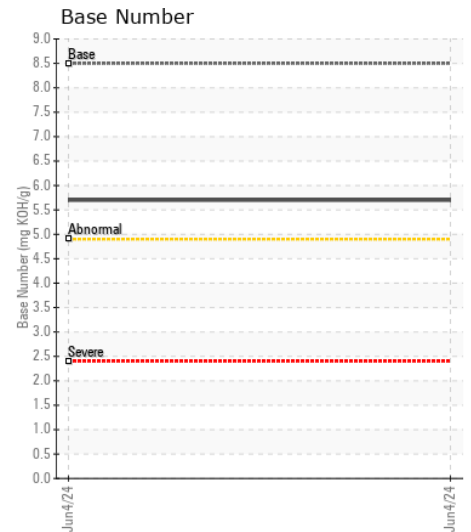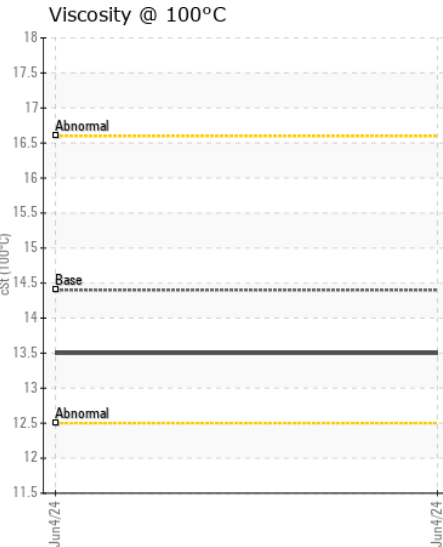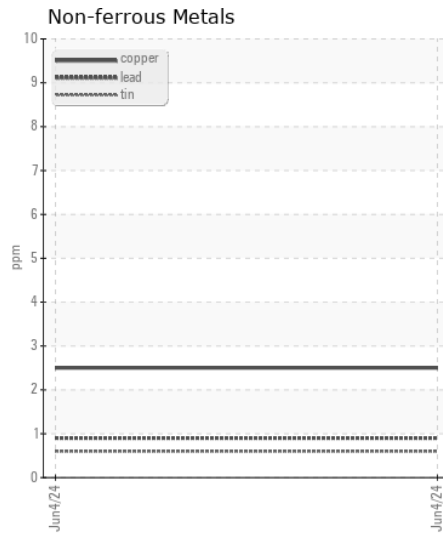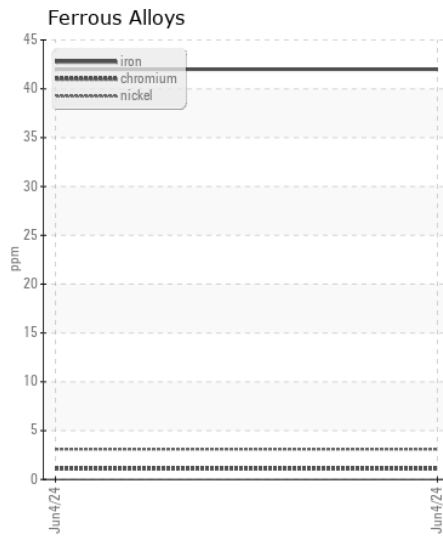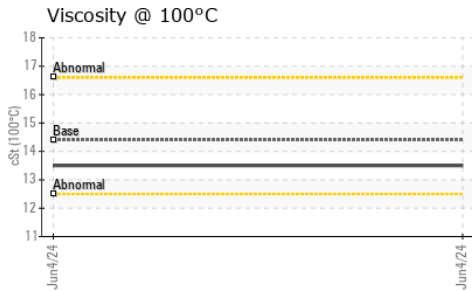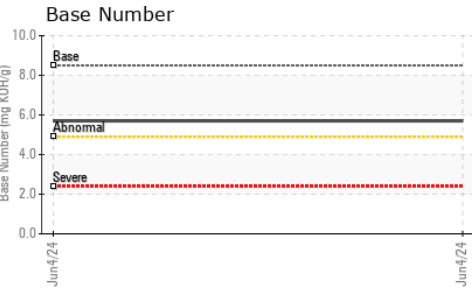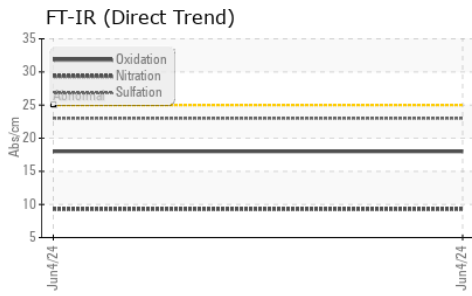

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0218287
Lab Number : 06215469
Unique Number : 11088333
Test Package : CONST (Additional Tests: TBN)

Received : 20 Jun 2024
Tested : 21 Jun 2024
Diagnosed : 21 Jun 2024 - Wes Davis

TOTAL DEVELOPMENT SOLUTIONS LLC
 7805 PROGRESS CT
 GAINESVILLE, VA
 US 20155
 Contact: JOE SEALE

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (571)220-7763

F: (703)753-4586