



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area
[ro#152261]
 Machine Id
JOHN DEERE 333G 1T0333GMPJF330716
 Component
Hydraulic System
 Fluid
JOHN DEERE HYDRAU (9 GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LEC0051781	LEC0032497	LEC0035399
Sample Date		Client Info		18 Jun 2024	11 Apr 2023	15 Dec 2022
Machine Age	hrs	Client Info		1372	1110	1109
Oil Age	hrs	Client Info		262	1	1109
Filter Age	hrs	Client Info		262	1	1109
Oil Changed		Client Info		Not Chngd	Changed	Changed
Filter Changed		Client Info		Not Chngd	Changed	Changed
Sample Status				NORMAL	NORMAL	ABNORMAL

WEAR

All component wear rates are normal.

PQ		ASTM D8184	>50	18	14	20
Iron	ppm	ASTM D5185m	>71	15	8	22
Chromium	ppm	ASTM D5185m	>11	3	1	2
Nickel	ppm	ASTM D5185m	>6	<1	0	0
Titanium	ppm	ASTM D5185m		0	0	0
Silver	ppm	ASTM D5185m		0	0	<1
Aluminum	ppm	ASTM D5185m	>11	1	0	1
Lead	ppm	ASTM D5185m	>13	2	0	1
Copper	ppm	ASTM D5185m	>21	17	6	17
Tin	ppm	ASTM D5185m	>5	<1	0	<1
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	LIGHT
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION











The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>24	8	6	15
Potassium	ppm	ASTM D5185m	>20	4	0	0
Water		WC Method	>0.075	NEG	NEG	NEG
Particles >4µm		ASTM D7647	>80000	1690	4971	105296
Particles >6µm		ASTM D7647	>5000	56	237	10050
Particles >14µm		ASTM D7647	>640	4	13	101
Particles >21µm		ASTM D7647	>160	1	2	16
Particles >38µm		ASTM D7647	>40	0	0	1
Particles >71µm		ASTM D7647	>10	0	0	0
Oil Cleanliness		ISO 4406 (c)	>23/19/16	18/13/9	19/15/11	24/21/14
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.075	NEG	NEG	NEG

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>21	3	<1	2
Boron	ppm	ASTM D5185m		12	4	12
Barium	ppm	ASTM D5185m		0	0	0
Molybdenum	ppm	ASTM D5185m		8	4	9
Manganese	ppm	ASTM D5185m		<1	<1	<1
Magnesium	ppm	ASTM D5185m		38	21	32
Calcium	ppm	ASTM D5185m	87	215	184	288
Phosphorus	ppm	ASTM D5185m	727	620	618	555
Zinc	ppm	ASTM D5185m	900	781	830	638
Sulfur	ppm	ASTM D5185m	1500	2056	1720	2080
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.58	0.69	0.61
Visc @ 40°C	cSt	ASTM D445	65	55.3	57.1	50.7

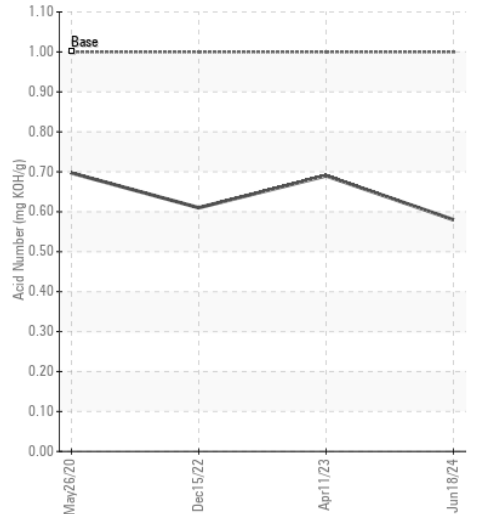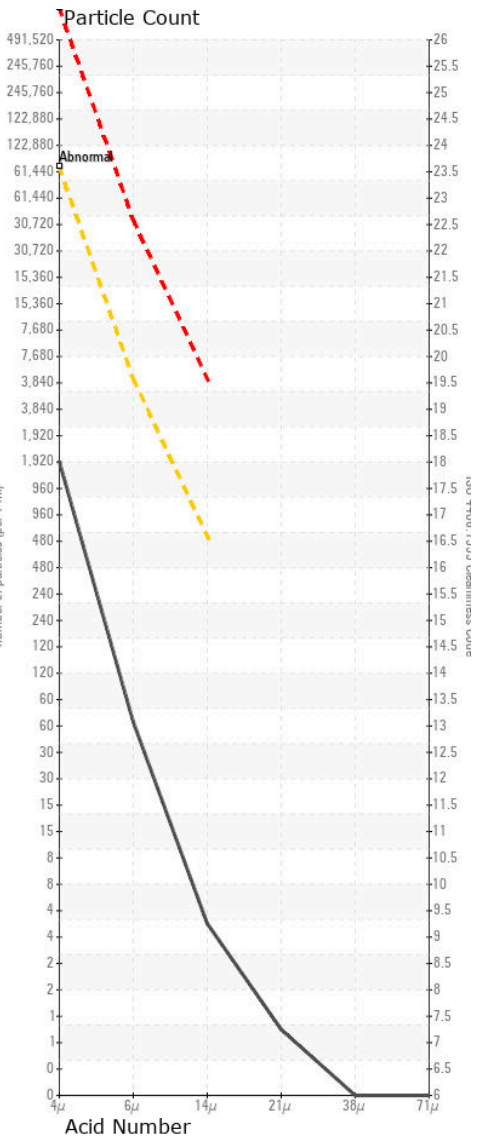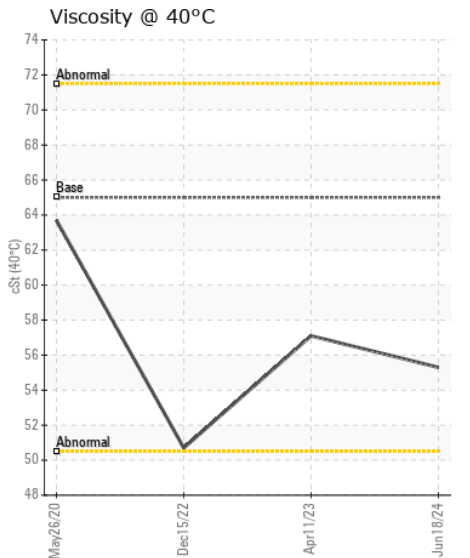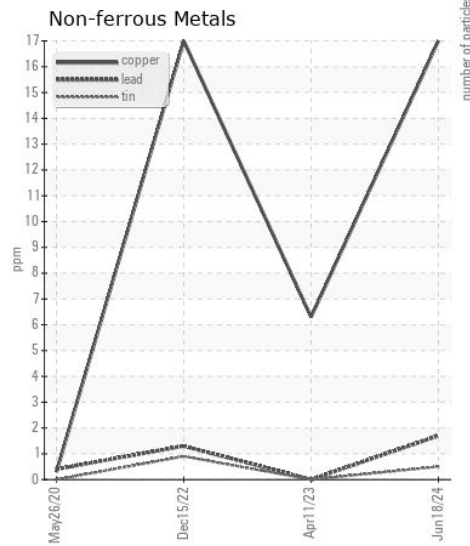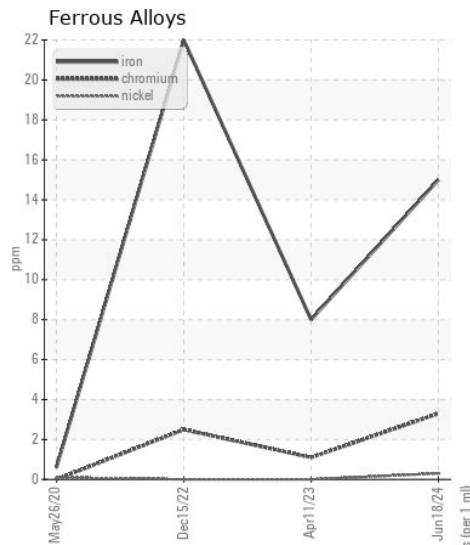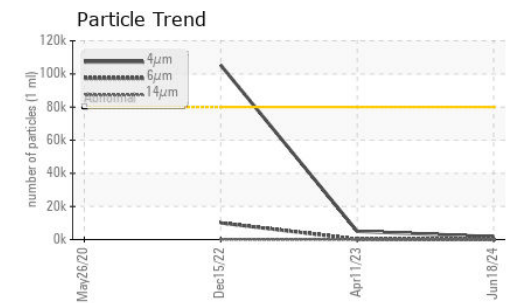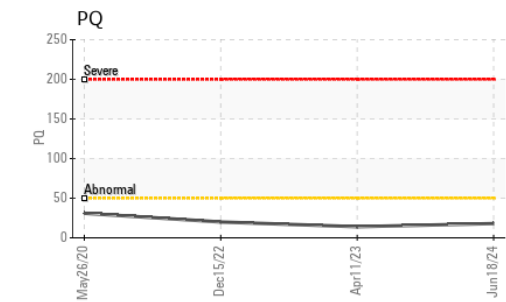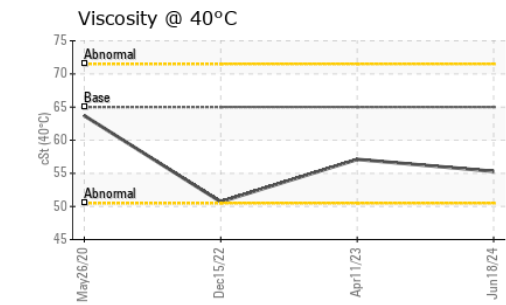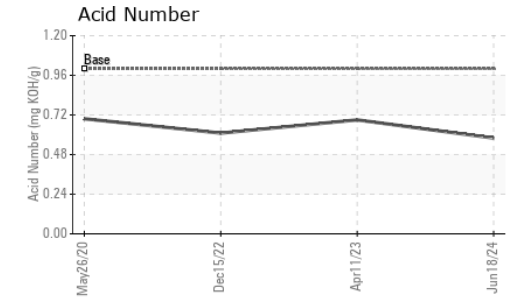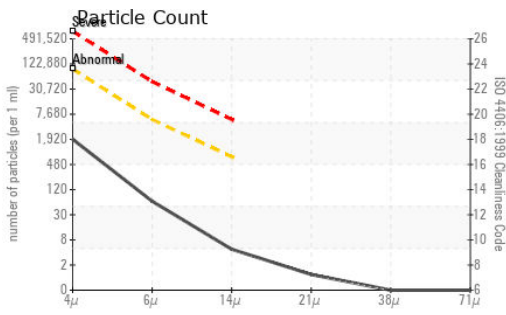

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : LEC0051781 **Received** : 20 Jun 2024
Lab Number : 06215730 **Tested** : 21 Jun 2024
Unique Number : 11088594 **Diagnosed** : 21 Jun 2024 - Wes Davis
Test Package : CONST (Additional Tests: PQ)

LESLIE EQUIPMENT COMPANY
 105 TENNIS CENTER DR.
 MARIETTA, OH
 US 45750-9765
 Contact: LEANNE KENDALL
 KendalLeanne@lec1.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T: (740)373-5570