



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area

[W/O 10979]

Machine Id

VOLVO EC480 310440

Component

Diesel Engine

Fluid

VOLVO ULTRA DIESEL ENGINE OIL 15W40 VDS-3 (14 GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		ML0002106	ML0000146	VCP286047
Sample Date		Client Info		17 Jun 2024	02 Feb 2024	27 Aug 2020
Machine Age	hrs	Client Info		6147	5715	4753
Oil Age	hrs	Client Info		432	250	500
Filter Age	hrs	Client Info		432	250	0
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				NORMAL	NORMAL	NORMAL

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	14	1	12
Chromium	ppm	ASTM D5185m	>10	<1	<1	<1
Nickel	ppm	ASTM D5185m	>10	0	0	<1
Titanium	ppm	ASTM D5185m		<1	<1	15
Silver	ppm	ASTM D5185m	>2	0	0	0
Aluminum	ppm	ASTM D5185m	>10	3	3	2
Lead	ppm	ASTM D5185m	>20	<1	0	2
Copper	ppm	ASTM D5185m	>15	<1	0	2
Tin	ppm	ASTM D5185m	>10	0	<1	1
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION








There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>20	10	6	6
Potassium	ppm	ASTM D5185m	>20	2	0	4
Fuel	%	ASTM D3524	>6.0	<1.0	<1.0	<1.0
Water		WC Method	>0.1	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	0.1	0.1	0.2
Nitration	Abs/cm	*ASTM D7624	>20	7.7	6.1	10.5
Sulfation	Abs/.1mm	*ASTM D7415	>30	22.4	21.9	22.3
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG	NEG

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185m		0	<1	3
Boron	ppm	ASTM D5185m	2.5	208	312	24
Barium	ppm	ASTM D5185m	0.0	0	0	0
Molybdenum	ppm	ASTM D5185m	0.7	105	109	27
Manganese	ppm	ASTM D5185m	0.0	0	<1	<1
Magnesium	ppm	ASTM D5185m	256	598	631	742
Calcium	ppm	ASTM D5185m	2057	1475	1346	1554
Phosphorus	ppm	ASTM D5185m	935	781	720	664
Zinc	ppm	ASTM D5185m	1223	953	837	731
Sulfur	ppm	ASTM D5185m	4079	3489	2399	3465
Oxidation	Abs/.1mm	*ASTM D7414	>25	17.3	15.8	17.4
Base Number (BN)	mg KOH/g	ASTM D2896	10	8.0	8.2	---
Visc @ 100°C	cSt	ASTM D445	15.0	12.4	12.9	13.4

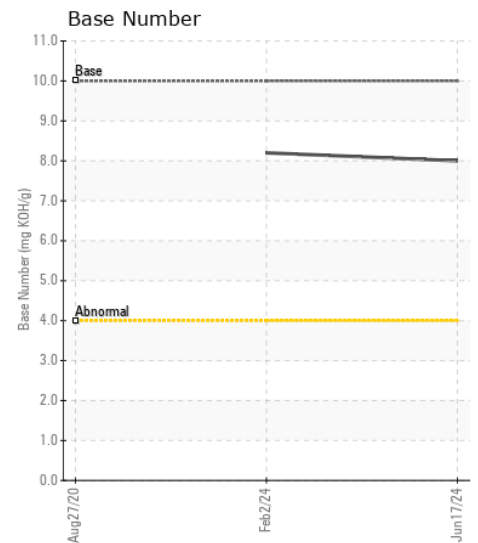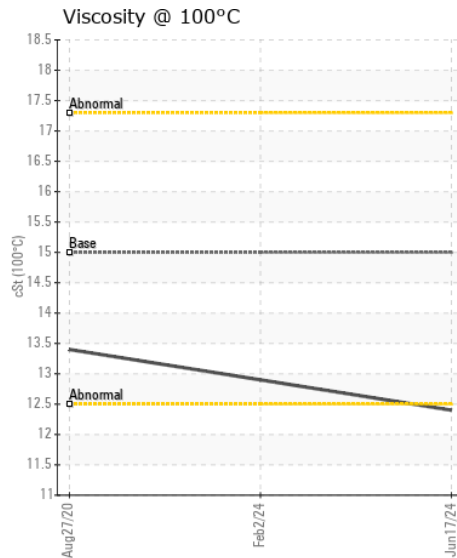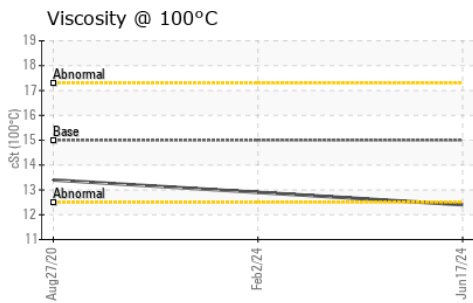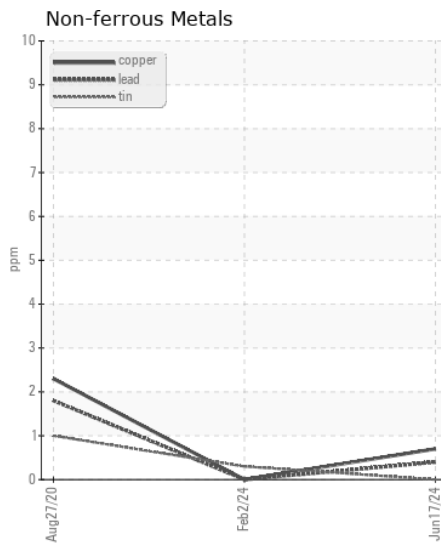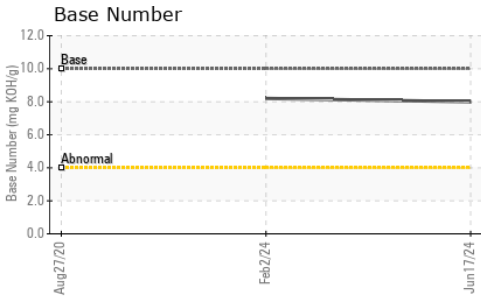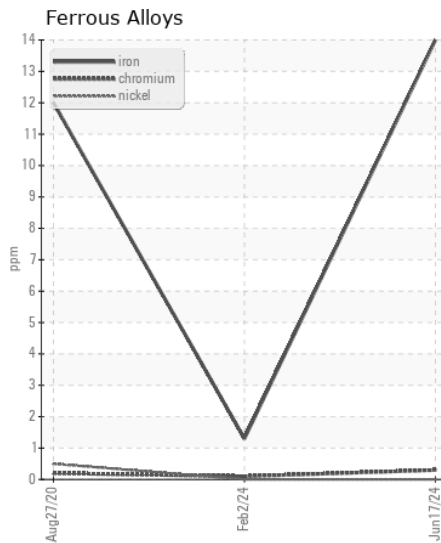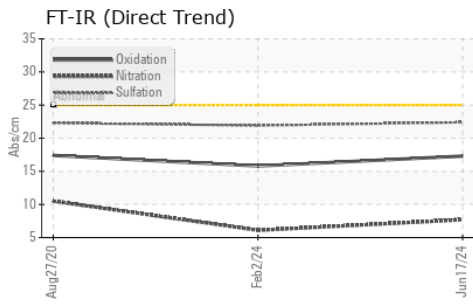

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : ML0002106 **Received** : 20 Jun 2024
Lab Number : 06216436 **Tested** : 28 Jun 2024
Unique Number : 11089300 **Diagnosed** : 28 Jun 2024 - Sean Felton
Test Package : CONST (Additional Tests: FuelDilution, PercentFuel, TBN)

MCCLEUNG-LOGAN EQUIPMENT CO - MANASSAS
 8450 QUARRY ROAD
 MANASSAS, VA
 US 20110
 Contact: MIKE MAYHUGH
 MMAYHUGH@MCCLEUNG-LOGAN.COM
 T: (703)393-7344
 F: (703)393-7844

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)