



Machine Id
JOHN DEERE 904P 904 P-TIER 4WD LOADER (S/N LX07673)

Component
Diesel Engine

Fluid
{not provided} (--- GAL)

RECOMMENDATION

Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0219787	---	---
Sample Date		Client Info		20 Jun 2024	---	---
Machine Age	hrs	Client Info		580	---	---
Oil Age	hrs	Client Info		580	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				ABNORMAL	---	---

WEAR

The copper level is abnormal. In the absence of other significant wear metals, suspect copper due to sources other than wear (i.e. cooling core). All other metal levels are typical for a new component breaking in.

Iron	ppm	ASTM D5185m	>51	65	---	---
Chromium	ppm	ASTM D5185m	>11	1	---	---
Nickel	ppm	ASTM D5185m	>5	1	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m	>3	<1	---	---
Aluminum	ppm	ASTM D5185m	>31	8	---	---
Lead	ppm	ASTM D5185m	>26	22	---	---
Copper	ppm	ASTM D5185m	>26	▲ 614	---	---
Tin	ppm	ASTM D5185m	>4	14	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION










Fuel content negligible. There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>22	19	---	---
Potassium	ppm	ASTM D5185m	>20	8	---	---
Fuel	%	ASTM D3524	>2.1	0.7	---	---
Water		WC Method	>0.21	NEG	---	---
Glycol	%	*ASTM D2982		NEG	---	---
Soot %	%	*ASTM D7844	>3	0.7	---	---
Nitration	Abs/cm	*ASTM D7624	>20	9.6	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	24.4	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.21	NEG	---	---

FLUID CONDITION

The oil viscosity is lower than normal. The BN result indicates that there is suitable alkalinity remaining in the oil. Confirm oil type.

Sodium	ppm	ASTM D5185m	>31	11	---	---
Boron	ppm	ASTM D5185m		92	---	---
Barium	ppm	ASTM D5185m		4	---	---
Molybdenum	ppm	ASTM D5185m		266	---	---
Manganese	ppm	ASTM D5185m		15	---	---
Magnesium	ppm	ASTM D5185m		777	---	---
Calcium	ppm	ASTM D5185m		1358	---	---
Phosphorus	ppm	ASTM D5185m		806	---	---
Zinc	ppm	ASTM D5185m		1036	---	---
Sulfur	ppm	ASTM D5185m		2562	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	18.0	---	---
Base Number (BN)	mg KOH/g	ASTM D2896		8.0	---	---
Visc @ 100°C	cSt	ASTM D445		● 9.7	---	---

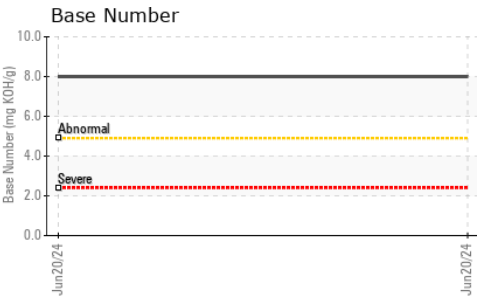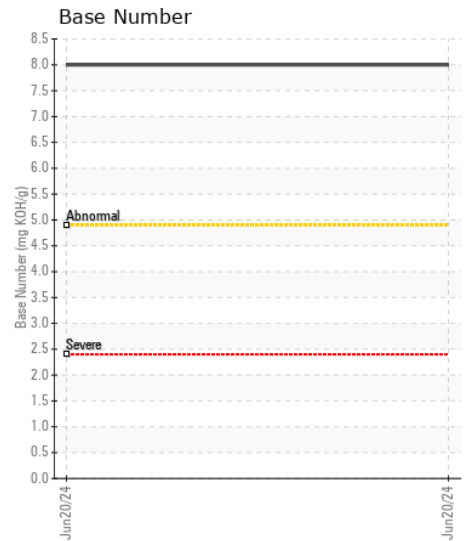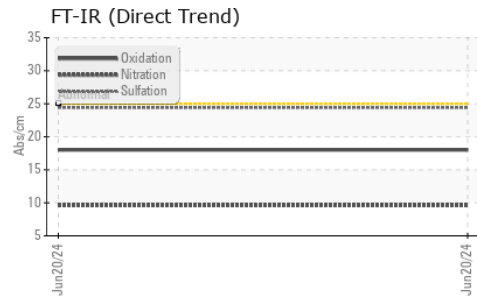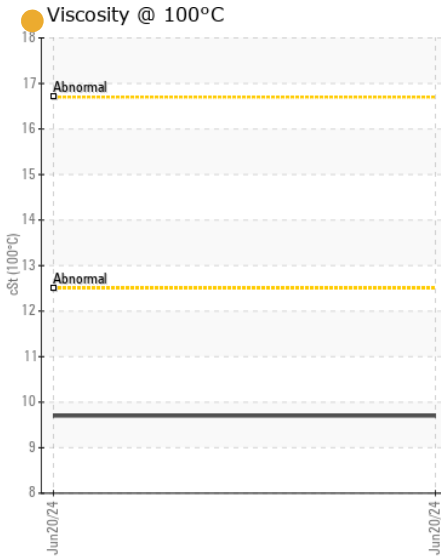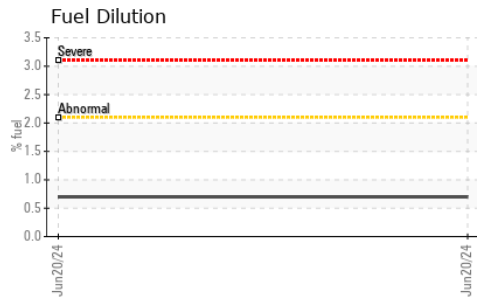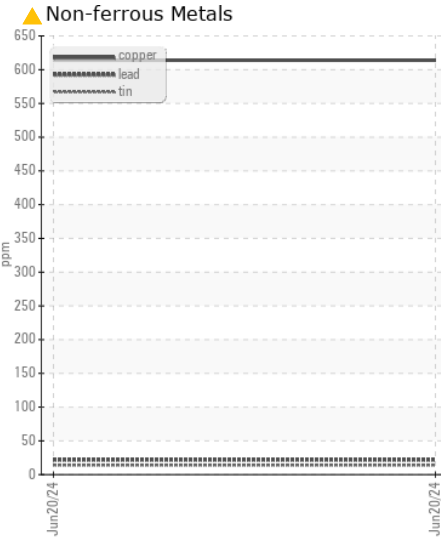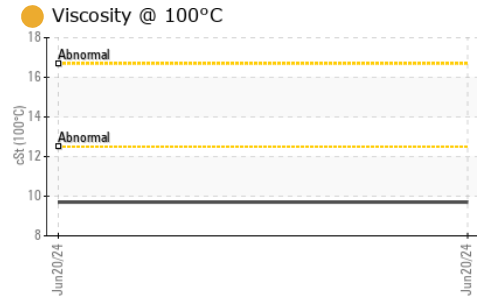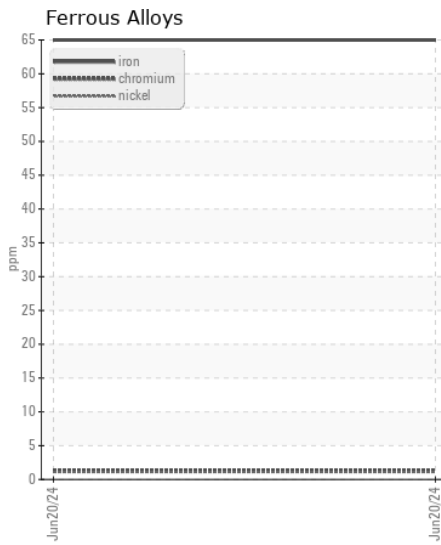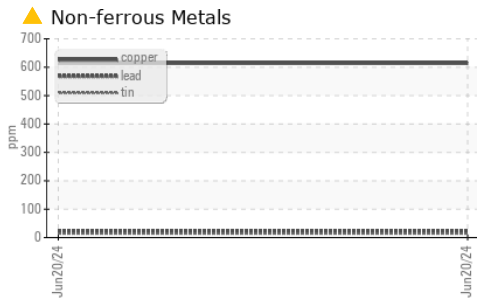

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : JR0219787

Lab Number : 06219492

Unique Number : 11097689

Test Package : CONST (Additional Tests: FuelDilution, Glycol, PercentFuel, TBN)

Received : 25 Jun 2024

Tested : 28 Jun 2024

Diagnosed : 28 Jun 2024 - Jonathan Hester

JRE - CHARLOTTE

9550 STATESVILLE ROAD

CHARLOTTE, NC

US 28269

Contact: CHARLOTTE SHOP

myoung@jamesriverequipment.com

T: (704)597-0211

F: (704)596-6198

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)