

#### Machine Id VOLVO EC210C 110262 Component Left Travel Fluid {not provided} (--- GAL)

#### RECOMMENDATION

We advise that you check all areas where dirt can enter the system. The oil change at the time of sampling has been noted. We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

### WEAR

The iron and chrome levels are severe. Gear wear is indicated.

## CONTAMINATION


Elemental levels of silicon (Si) and aluminum (Al) indicate aluminasilicate (coarse dirt) ingress. There is a light concentration of water present in the oil.

Test	UOM	Method	Limit/Abn	Cı	urrent	History1	History2
Sample Number		Client Info		AS	C0003303		
Sample Date		Client Info		25	Jun 2024		
Machine Age	hrs	Client Info		90	00		
Oil Age	hrs	Client Info		90	00		
Filter Age	hrs	Client Info		0			
Oil Changed		Client Info		Cł	nanged		
Filter Changed		Client Info		N/	Α		
Sample Status				SE	VERE		
Iron	ppm	ASTM D5185m	>1200		6543		
Chromium	ppm	ASTM D5185m	>20		55		
Nickel	ppm	ASTM D5185m	>5		4		
Titanium	ppm	ASTM D5185m	20		34		
Silver		ASTM D5185m			0		
Aluminum	ppm	ASTM D5185m	>100		586		
	ppm	ASTM D5185m			500 1		
Lead	ppm		>50		-		
Copper	ppm	ASTM D5185m	>50		10		
Tin	ppm	ASTM D5185m	>5		<1		
Vanadium	ppm	ASTM D5185m			<1		
White Metal	scalar	*Visual	NONE		NONE		
Yellow Metal	scalar	*Visual	NONE		NONE		
Silicon	ppm	ASTM D5185m	>100		1766		
Potassium	ppm	ASTM D5185m	>20	-	151		
Water	%	ASTM D6304	>0.25		0.362		
ppm Water	ppm	ASTM D6304	>2500		3620		
Silt	scalar	*Visual	NONE		NONE		
Debris	scalar	*Visual	NONE		NONE		
Sand/Dirt	scalar	*Visual	NONE		NONE		
Appearance	scalar	*Visual	NORML		NORML		
Odor	scalar	*Visual	NORML		NORML		
Emulsified Water	scalar	*Visual	>0.25		0.2%		
	Scala	• 150ai	20.25		0.2 /8		
Sodium	ppm	ASTM D5185m			20		
Boron	ppm	ASTM D5185m			203		
Barium	ppm	ASTM D5185m			4		
Molybdenum	ppm	ASTM D5185m			9		
Manganese	ppm	ASTM D5185m			39		
Magnesium	ppm	ASTM D5185m			54		
Calcium	ppm	ASTM D5185m			66		
Phosphorus	ppm	ASTM D5185m			2124		
Zinc	ppm	ASTM D5185m			90		
Sulfur	ppm	ASTM D5185m			59152		
Visc @ 40°C	cSt	ASTM D445		L	68.2		

# FLUID CONDITION

The oil is no longer serviceable due to the presence of contaminants.

Submitted By: Kendall Rhodes

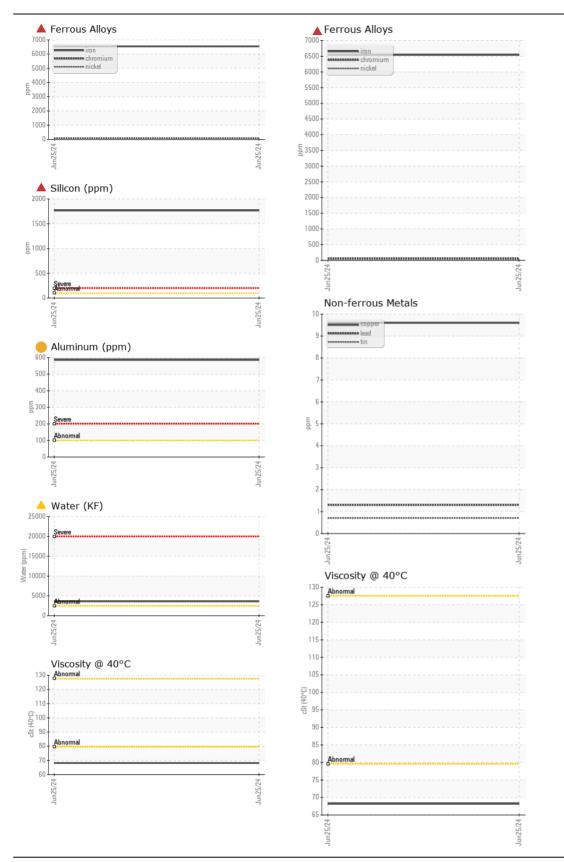

160 - ASCENDUM MACHINERY INC - MILLS RIVER Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513 Sample No. Received 215 FANNING FIELDS RD : ASC0003303 : 26 Jun 2024 Lab Number : 06221682 MILLS RIVER, NC Tested : 27 Jun 2024 : 28 Jun 2024 - Don Baldridge US 28759 Unique Number : 11099879 Diagnosed Test Package : CONST (Additional Tests: KF) Contact: BRANDON DRAKE Certificate L2367 To discuss this sample report, contact Customer Service at 1-800-237-1369. brandon.drake@ascendummachinery.com \* - Denotes test methods that are outside of the ISO 17025 scope of accreditation. T: 8(286)687-0620 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012) F: (828)687-0622