



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	SEVERE
FLUID CONDITION	ABNORMAL



Machine Id
CATERPILLAR 950M
Component
Diesel Engine
Fluid
GIBRALTAR 15W/40 SUPER S-3 LX (--- GAL)

RECOMMENDATION

We advise that you check for the source of the coolant leak. Check for low coolant level. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		WC0875502	---	---
Sample Date		Client Info		25 May 2024	---	---
Machine Age	hrs	Client Info		21429	---	---
Oil Age	hrs	Client Info		900	---	---
Filter Age	hrs	Client Info		900	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				SEVERE	---	---

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>100	33	---	---
Chromium	ppm	ASTM D5185m	>20	1	---	---
Nickel	ppm	ASTM D5185m	>2	0	---	---
Titanium	ppm	ASTM D5185m	>2	<1	---	---
Silver	ppm	ASTM D5185m	>2	0	---	---
Aluminum	ppm	ASTM D5185m	>25	11	---	---
Lead	ppm	ASTM D5185m	>40	<1	---	---
Copper	ppm	ASTM D5185m	>330	129	---	---
Tin	ppm	ASTM D5185m	>15	0	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION













Sodium and/or potassium levels are high. Test for glycol is positive.

Silicon	ppm	ASTM D5185m	>25	24	---	---
Potassium	ppm	ASTM D5185m	>20	▲ 1643	---	---
Fuel		WC Method	>5	<1.0	---	---
Water		WC Method	>0.2	NEG	---	---
Glycol	%	*ASTM D2982		▲ 0.20	---	---
Soot %	%	*ASTM D7844	>3	0.3	---	---
Nitration	Abs/cm	*ASTM D7624	>20	9.9	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	20.3	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.2	NEG	---	---

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The oil is no longer serviceable due to the presence of contaminants.

Sodium	ppm	ASTM D5185m		▲ 354	---	---
Boron	ppm	ASTM D5185m		<1	---	---
Barium	ppm	ASTM D5185m		<1	---	---
Molybdenum	ppm	ASTM D5185m	66	242	---	---
Manganese	ppm	ASTM D5185m		1	---	---
Magnesium	ppm	ASTM D5185m	1000	824	---	---
Calcium	ppm	ASTM D5185m	1050	1214	---	---
Phosphorus	ppm	ASTM D5185m	1150	918	---	---
Zinc	ppm	ASTM D5185m	1270	1282	---	---
Sulfur	ppm	ASTM D5185m		3663	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	14.9	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	10.1	6.7	---	---
Visc @ 100°C	cSt	ASTM D445	15.5	13.7	---	---

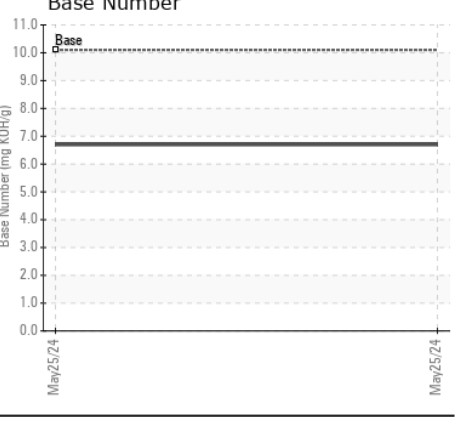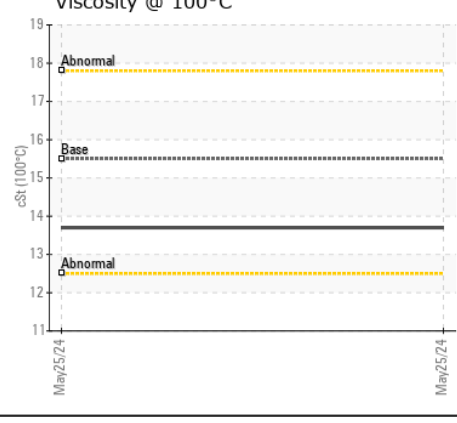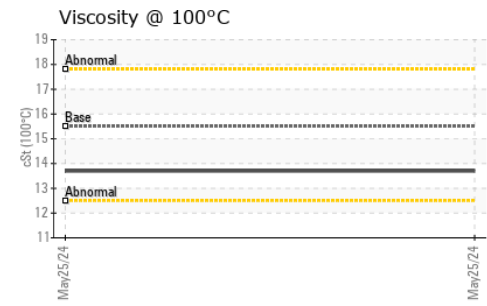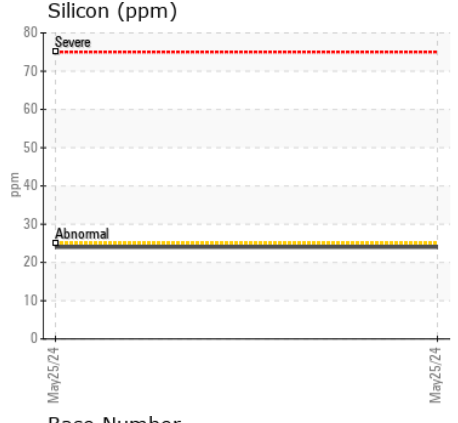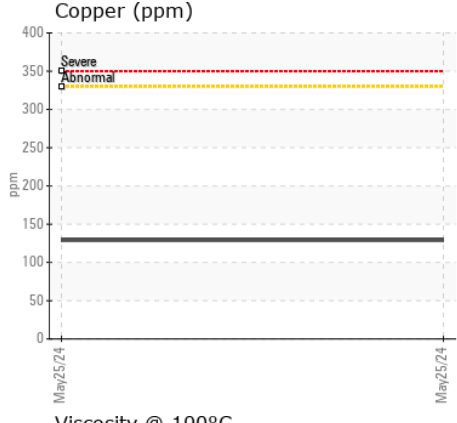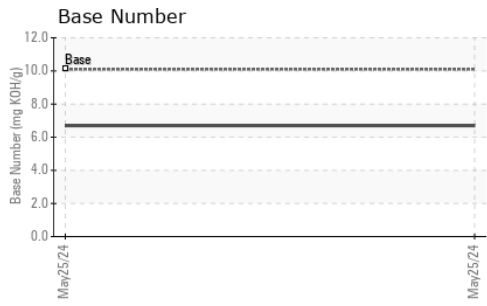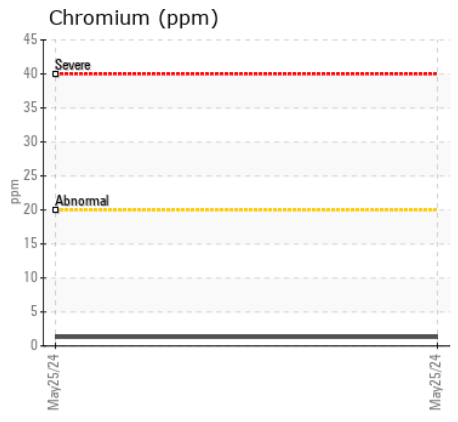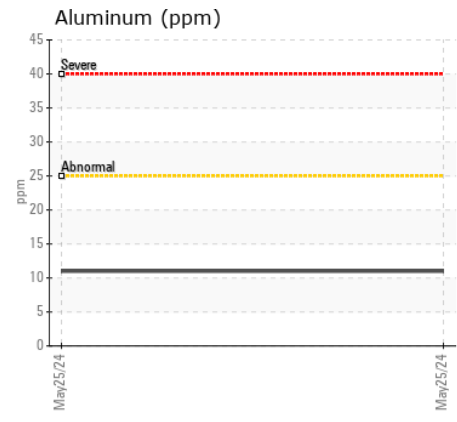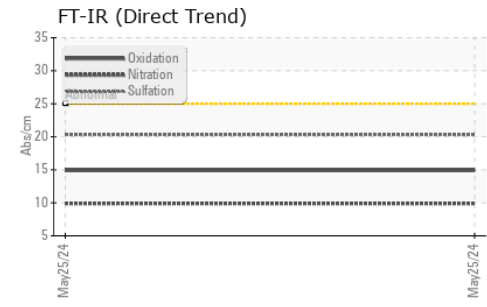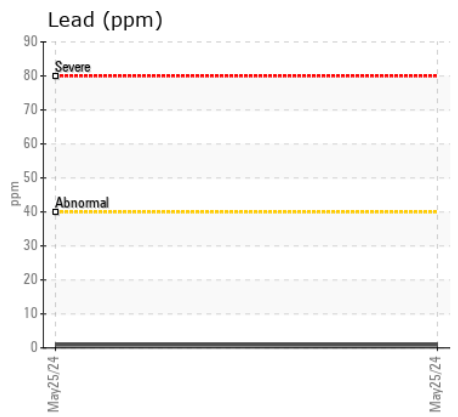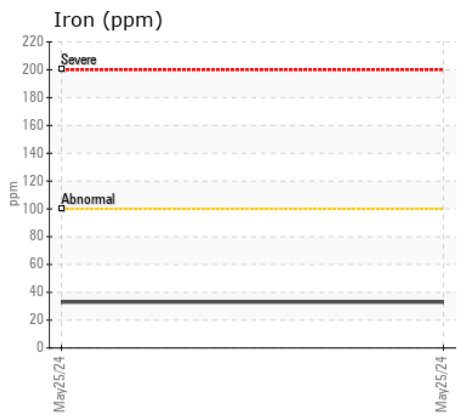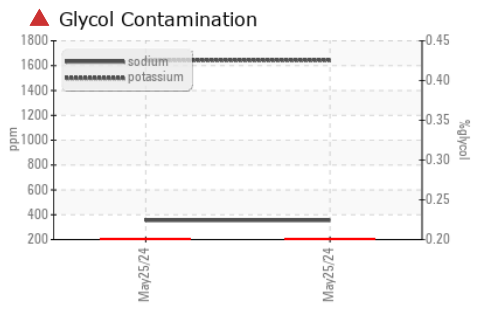

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : WC0875502 **Received** : 28 Jun 2024
Lab Number : 06223195 **Tested** : 01 Jul 2024
Unique Number : 11101392 **Diagnosed** : 01 Jul 2024 - Jonathan Hester
Test Package : MOB 1 (Additional Tests: Glycol, TBN)

OAKRIDGE WASTE
 307 WHITE ST
 DANBURY, CT
 US 06810

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

Contact: CHRIS CONTI
 chris.conti@oakridgewaste.com
 T:
 F: