



RECOMMENDATION

JOHN DEERE 210G 1FF210GXVNF530404

Right Final Drive

JOHN DEERE GL-5 80W90 (--- GAL)

We advise that you check all areas where dirt can enter the system. We recommend an early resample to monitor this condition.

١	Λ	E	A	R	P

Gear wear is indicated. All other metal levels are typical for a new component breaking in.

CONTAMINATION


Elemental levels of silicon (Si) and aluminum (Al) indicate aluminasilicate (coarse dirt) ingress.

FLUID CONDITION

The condition of the oil is acceptable for the time in service.

jAL)						
Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0220343		
Sample Date		Client Info		26 Jun 2024		
Machine Age	hrs	Client Info		1425		
Oil Age	hrs	Client Info		0		
Filter Age	hrs	Client Info		0		
Oil Changed		Client Info		Not Changd		
Filter Changed		Client Info		N/A		
Sample Status				SEVERE		
PQ		ASTM D8184	>1250	961		
Iron	ppm	ASTM D5185m	>750	<u> </u>		
Chromium	ppm	ASTM D5185m	>9	▲ 28		
Nickel	ppm	ASTM D5185m	>10	4		
Titanium	ppm	ASTM D5185m	210	8		
Silver	ppm	ASTM D5185m		۲ <1		
Aluminum	ppm	ASTM D5185m	>40	40		
Lead	ppm	ASTM D5185m	>15	0		
Copper	ppm	ASTM D5185m	>40	5		
Tin	ppm	ASTM D5185m	>10	0		
Vanadium	ppm	ASTM D5185m	210	۲ ۲		
White Metal	scalar	*Visual	NONE	NONE		
Yellow Metal	scalar	*Visual	NONE	NONE		
Silicon	ppm	ASTM D5185m	>75	4 97		
Potassium	ppm	ASTM D5185m	>20	14		
Water		WC Method	>0.075	NEG		
Silt	scalar	*Visual	NONE	NONE		
Debris	scalar	*Visual	NONE	NONE		
Sand/Dirt	scalar	*Visual	NONE	NONE		
Appearance	scalar	*Visual	NORML	NORML		
Odor	scalar	*Visual	NORML	NORML		
Emulsified Water	scalar	*Visual	>0.075	NEG		
Sodium	ppm	ASTM D5185m	>51	6		
Boron	ppm	ASTM D5185m		62		
Barium	ppm	ASTM D5185m		4		
Molybdenum	ppm	ASTM D5185m		1		
Manganese	ppm	ASTM D5185m		29		
Magnesium	ppm	ASTM D5185m		6		
Calcium	ppm	ASTM D5185m		49		
Phosphorus	ppm	ASTM D5185m		486		
Zinc	ppm	ASTM D5185m		34		
Sulfur	ppm	ASTM D5185m		22360		
Visc @ 40°C	cSt	ASTM D445		198		

Contact/Location: Mike Young - CHARLOTTE SHOP - JAMCHA

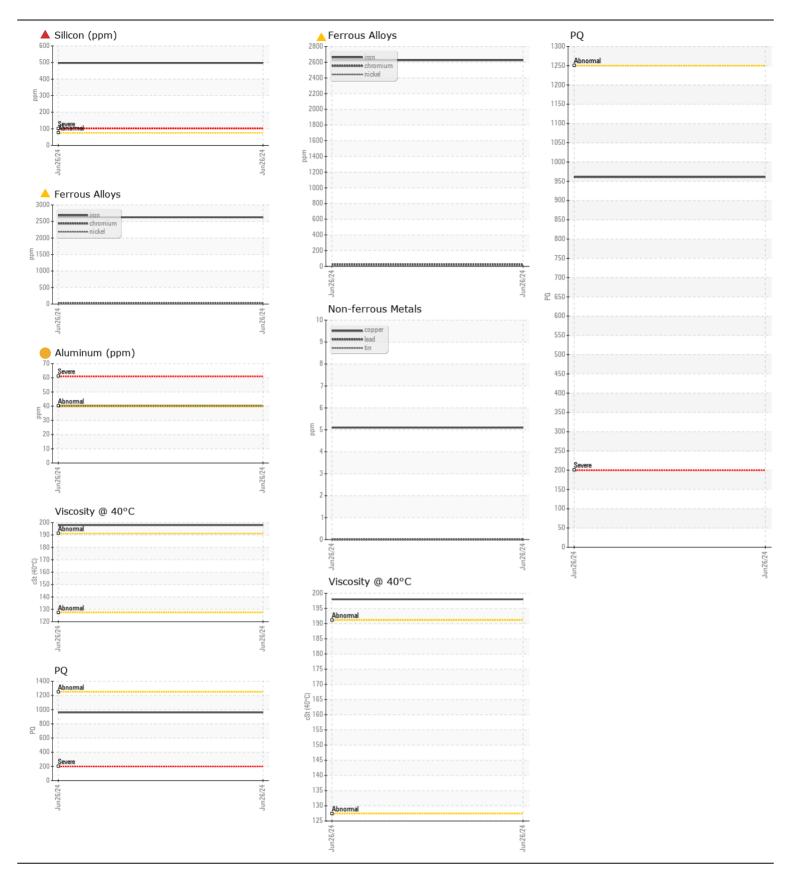

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513 **JRE - CHARLOTTE** Sample No. : JR0220343 Received 9550 STATESVILLE ROAD : 28 Jun 2024 **ī**8 : 06223686 Lab Number Tested : 01 Jul 2024 CHARLOTTE, NC : 01 Jul 2024 - Don Baldridge Unique Number : 11101883 Diagnosed US 28269 Test Package : CONST (Additional Tests: PQ) Contact: CHARLOTTE SHOP Certificate L2367 To discuss this sample report, contact Customer Service at 1-800-237-1369. myoung@jamesriverequipment.com * - Denotes test methods that are outside of the ISO 17025 scope of accreditation. T: (704)597-0211 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012) F: (704)596-6198

Contact/Location: Mike Young - CHARLOTTE SHOP - JAMCHA