



VOLVO

OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area
[HERC RENTALS]
 Machine Id
VOLVO ECR145 315949
 Component
Diesel Engine
 Fluid
DIESEL ENGINE OIL SAE 15W40 (--- GAL)

RECOMMENDATION

Oil and filter change at the time of sampling has been noted. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		VCP443802	---	---
Sample Date		Client Info		24 Jun 2024	---	---
Machine Age	hrs	Client Info		863	---	---
Oil Age	hrs	Client Info		0	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Changed	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				NORMAL	---	---

WEAR

Metal levels are typical for a new component breaking in.

Iron	ppm	ASTM D5185m	>100	10	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	<1	---	---
Titanium	ppm	ASTM D5185m		<1	---	---
Silver	ppm	ASTM D5185m	>2	0	---	---
Aluminum	ppm	ASTM D5185m	>10	5	---	---
Lead	ppm	ASTM D5185m	>20	0	---	---
Copper	ppm	ASTM D5185m	>15	<1	---	---
Tin	ppm	ASTM D5185m	>10	<1	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION














Fuel content negligible. There is no indication of any contamination in the oil.

Silicon	ppm	ASTM D5185m	>20	5	---	---
Potassium	ppm	ASTM D5185m	>20	0	---	---
Fuel	%	ASTM D3524	>6.0	0.4	---	---
Water		WC Method	>0.1	NEG	---	---
Glycol		WC Method		NEG	---	---
Soot %	%	*ASTM D7844	>3	0.1	---	---
Nitration	Abs/cm	*ASTM D7624	>20	5.8	---	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	19.5	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is acceptable for the time in service.

Sodium	ppm	ASTM D5185m	>158	2	---	---
Boron	ppm	ASTM D5185m	250	293	---	---
Barium	ppm	ASTM D5185m	10	0	---	---
Molybdenum	ppm	ASTM D5185m	100	74	---	---
Manganese	ppm	ASTM D5185m		<1	---	---
Magnesium	ppm	ASTM D5185m	450	415	---	---
Calcium	ppm	ASTM D5185m	3000	1451	---	---
Phosphorus	ppm	ASTM D5185m	1150	982	---	---
Zinc	ppm	ASTM D5185m	1350	1203	---	---
Sulfur	ppm	ASTM D5185m	4250	3780	---	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	13.1	---	---
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	7.2	---	---
Visc @ 100°C	cSt	ASTM D445	14.4	12.2	---	---

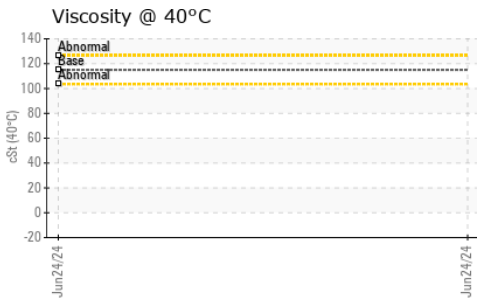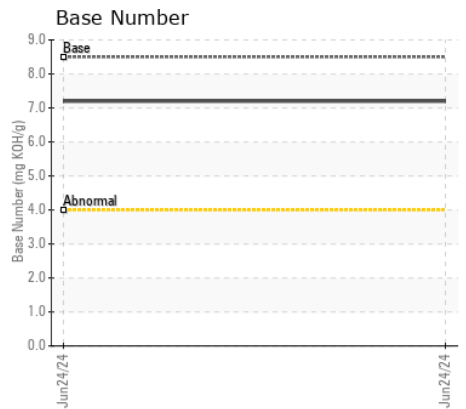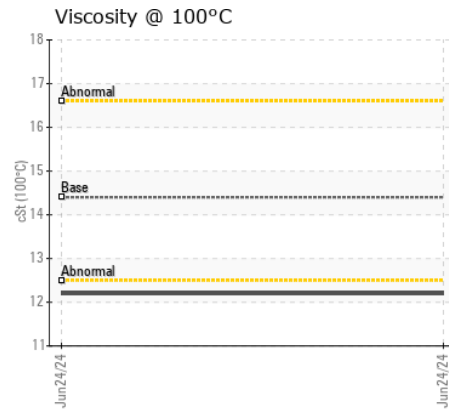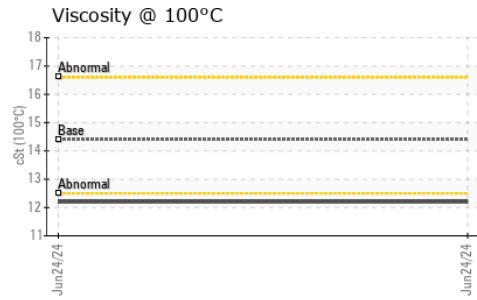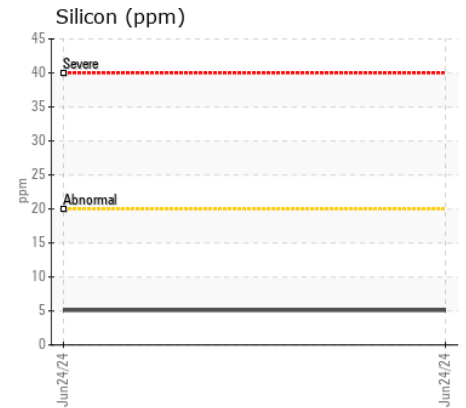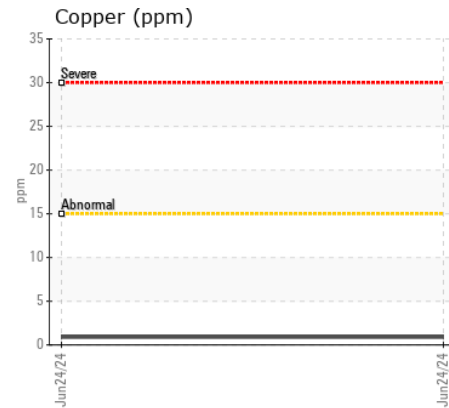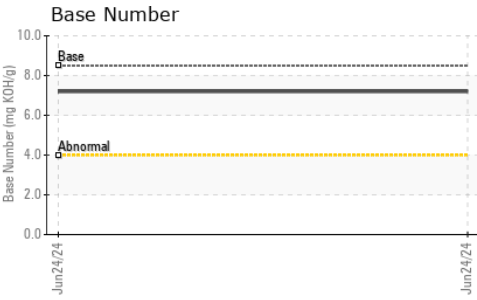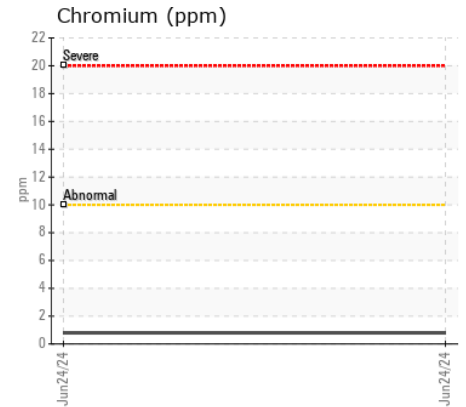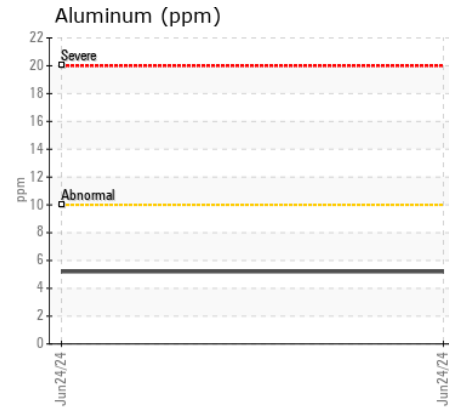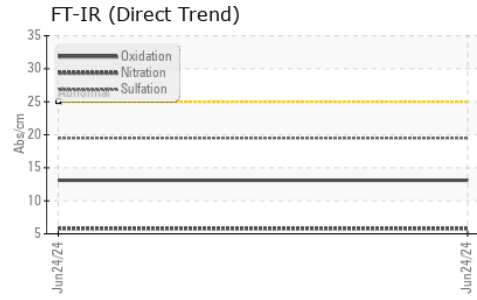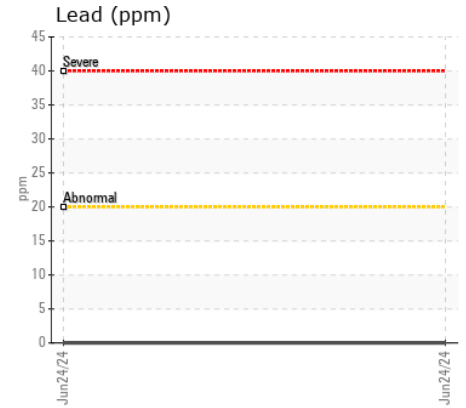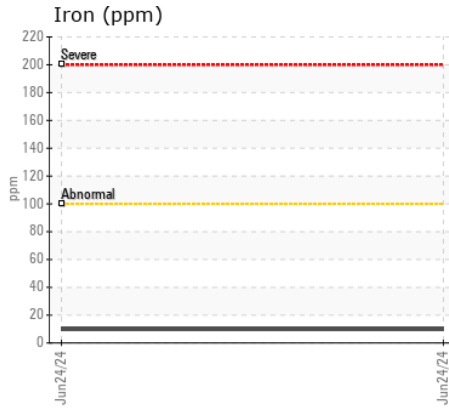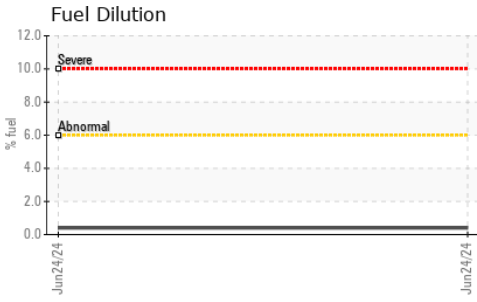

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : VCP443802
Lab Number : 06224271
Unique Number : 11102468
Test Package : MOB 1 (Additional Tests: FuelDilution, KV40, PercentFuel, TBN)

Received : 01 Jul 2024
Tested : 03 Jul 2024
Diagnosed : 03 Jul 2024 - Jonathan Hester

ALTA EQUIPMENT/FLAGLER CONSTRUCTION EQUIPMENT LLC
 8418 PALM RIVER ROAD
 TAMPA, FL
 US 33619
 Contact: KENNY HANEY
 khaney@flaglerce.com
 T: (813)630-0077
 F: (813)630-2233

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)