



WEAR	<b>NORMAL</b>
CONTAMINATION	<b>NORMAL</b>
FLUID CONDITION	<b>NORMAL</b>



Machine Id  
**2016**  
Component  
**Diesel Engine**  
Fluid  
**JOHN DEERE ENGINE OIL PLUS 50 II 15W40 (--- GAL)**

### RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		<b>JR0221916</b>	JR0195381	JR0184576
Sample Date		Client Info		<b>17 Jun 2024</b>	20 Feb 2024	10 Nov 2023
Machine Age	hrs	Client Info		<b>4750</b>	4163	3663
Oil Age	hrs	Client Info		<b>500</b>	4000	500
Filter Age	hrs	Client Info		<b>500</b>	4000	500
Oil Changed		Client Info		<b>Changed</b>	Changed	Changed
Filter Changed		Client Info		<b>Changed</b>	Changed	Changed
Sample Status				<b>NORMAL</b>	NORMAL	NORMAL

### WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>51	<b>14</b>	12	8
Chromium	ppm	ASTM D5185m	>11	<b>&lt;1</b>	<1	<1
Nickel	ppm	ASTM D5185m	>5	<b>5</b>	7	4
Titanium	ppm	ASTM D5185m		<b>&lt;1</b>	<1	0
Silver	ppm	ASTM D5185m	>3	<b>&lt;1</b>	0	0
Aluminum	ppm	ASTM D5185m	>31	<b>3</b>	2	5
Lead	ppm	ASTM D5185m	>26	<b>&lt;1</b>	<1	0
Copper	ppm	ASTM D5185m	>26	<b>5</b>	1	<1
Tin	ppm	ASTM D5185m	>4	<b>&lt;1</b>	<1	0
Vanadium	ppm	ASTM D5185m		<b>&lt;1</b>	<1	<1
White Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE

### CONTAMINATION

There is no indication of any contamination in the oil.


Silicon	ppm	ASTM D5185m	>22	<b>5</b>	5	6
Potassium	ppm	ASTM D5185m	>20	<b>3</b>	2	2
Fuel		WC Method	>2.1	<b>&lt;1.0</b>	<1.0	<1.0
Water		WC Method	>0.21	<b>NEG</b>	NEG	NEG
Glycol		WC Method		<b>NEG</b>	NEG	NEG
Soot %	%	*ASTM D7844	>3	<b>0.2</b>	0.2	0.2
Nitration	Abs/cm	*ASTM D7624	>20	<b>6.8</b>	6.7	7.8
Sulfation	Abs/.1mm	*ASTM D7415	>30	<b>17.4</b>	17.3	21.1
Silt	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Debris	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	<b>NONE</b>	NONE	NONE
Appearance	scalar	*Visual	NORML	<b>NORML</b>	NORML	NORML
Odor	scalar	*Visual	NORML	<b>NORML</b>	NORML	NORML
Emulsified Water	scalar	*Visual	>0.21	<b>NEG</b>	NEG	NEG

### FLUID CONDITION


The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m	>31	<b>0</b>	<1	2
Boron	ppm	ASTM D5185m		<b>7</b>	34	239
Barium	ppm	ASTM D5185m		<b>&lt;1</b>	0	0
Molybdenum	ppm	ASTM D5185m		<b>11</b>	43	239
Manganese	ppm	ASTM D5185m		<b>&lt;1</b>	<1	<1
Magnesium	ppm	ASTM D5185m		<b>71</b>	155	760
Calcium	ppm	ASTM D5185m		<b>2362</b>	2220	1392
Phosphorus	ppm	ASTM D5185m		<b>890</b>	923	915
Zinc	ppm	ASTM D5185m		<b>1087</b>	1094	1107
Sulfur	ppm	ASTM D5185m		<b>3363</b>	4092	3203
Oxidation	Abs/.1mm	*ASTM D7414	>25	<b>10.0</b>	10.5	15.2
Base Number (BN)	mg KOH/g	ASTM D2896	13.6	<b>6.9</b>	7.0	9.0
Visc @ 100°C	cSt	ASTM D445	15.4	<b>13.1</b>	13.1	13.6


**FT-IR (Direct Trend)**

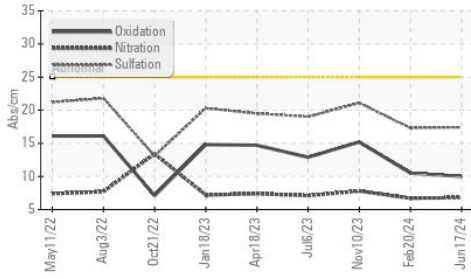


**Ferrous Alloys**

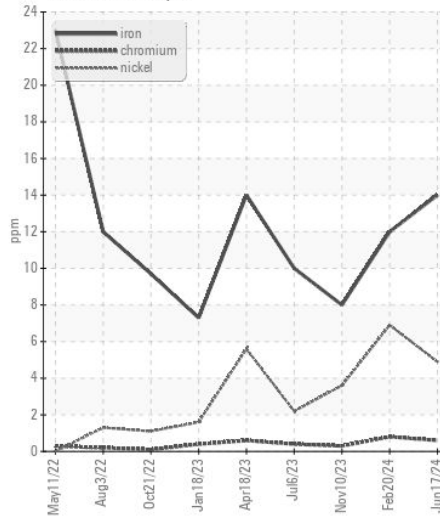


**Base Number**

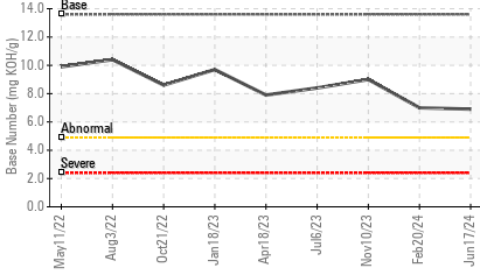


**Non-ferrous Metals**

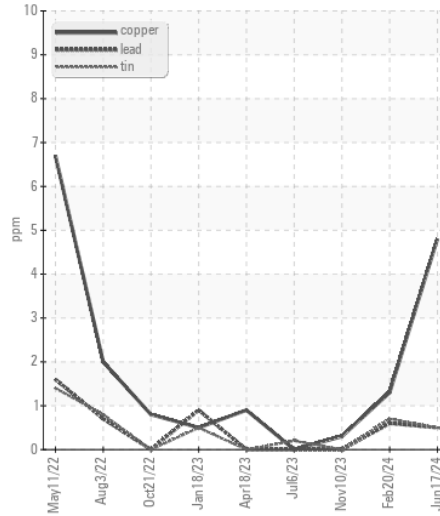


**Viscosity @ 100°C**

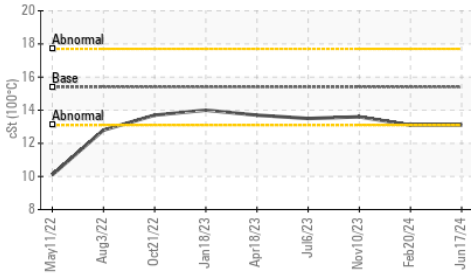

**Viscosity @ 100°C**

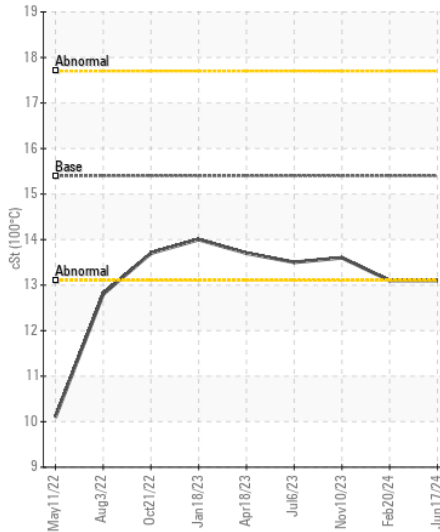

**Base Number**

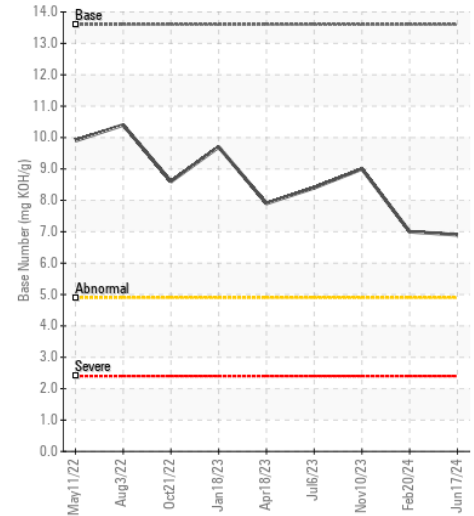

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : JR0221916 **Received** : 02 Jul 2024  
**Lab Number** : 06225948 **Tested** : 03 Jul 2024  
**Unique Number** : 11109441 **Diagnosed** : 03 Jul 2024 - Angela Borella  
**Test Package** : CONST ( Additional Tests: TBN )

**PATRIOT DEVELOPMENT CORP**  
 22721 LADBROOK DRIVE STE 120  
 STERLING, VA  
 US 20166  
 Contact: ROBERT MOSS  
 robert.moss@patriotdev.net

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:  
F: