

Machine Id VOLVO EC300EL 314193 Component Rear Right Final Drive Fluid GEAR OIL SAE 75W80 (--- GAL)

RECOMMENDATION

We advise that you check all areas where dirt can enter the system. The oil change at the time of sampling has been noted. We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

WEAR

Gear wear is indicated.

CONTAMINATION

Elemental levels of silicon (Si) and aluminum (AI) indicate aluminasilicate (coarse dirt) ingress.


FLUID CONDITION

The oil is no longer serviceable due to the presence of contaminants.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		ML0002723		
Sample Date		Client Info		25 Jun 2024		
Machine Age	hrs	Client Info		4326		
Oil Age	hrs	Client Info		4326		
Filter Age	hrs	Client Info		0		
Oil Changed		Client Info		Changed		
Filter Changed		Client Info		N/A		
Sample Status				SEVERE		
Iron			. 500	A 10500		
lron Chromium	ppm	ASTM D5185m	>500 >10	▲ 12538		
	ppm	ASTM D5185m		▲ 117 10		
Nickel	ppm	ASTM D5185m	>10	10 37		
Titanium Silver	ppm	ASTM D5185m ASTM D5185m		37 <1		
Aluminum	ppm	ASTM D5185m	>25	<1		
Lead	ppm	ASTM D5185m	>20	- 352 1		
Copper	ppm	ASTM D5185m	>20	29		
Tin	ppm	ASTM D5185m	>50	29 3		
Vanadium	ppm	ASTM D5185m	>10	2		
White Metal	ppm scalar	*Visual	NONE	2 NONE		
Yellow Metal	scalar	*Visual	NONE	NONE		
	Scala	visuai				
Silicon	ppm	ASTM D5185m	>75	2908		
Potassium	ppm	ASTM D5185m	>20	84		
Water		WC Method	>0.2	NEG		
Silt	scalar	*Visual	NONE	NONE		
Debris	scalar	*Visual	NONE	NONE		
Sand/Dirt	scalar	*Visual	NONE	NONE		
Appearance	scalar	*Visual	NORML	NORML		
Odor	scalar	*Visual	NORML	NORML		
Emulsified Water	scalar	*Visual	>0.2	NEG		
Sodium	nnm	ASTM D5185m		20		
Boron	ppm	ASTM D5185m	400	83		
Barium	ppm ppm	ASTM D5185m	200	3		
Molybdenum	ppm	ASTM D5185m	12	18		
Manganese	ppm	ASTM D5185m	12	89		
Magnesium	ppm	ASTM D5185m	12	46		
Calcium	ppm	ASTM D5185m	150	221		
Phosphorus	ppm	ASTM D5185m	1650	699		
Zinc	ppm	ASTM D5185m	125	26		
Sulfur	ppm	ASTM D5185m	22500	78806		
Visc @ 40°C	cSt	ASTM D3103III	48	263		
	501	, 10 1 10 DTTJ	10			

Submitted By: Service - Alex Anderson

WEAR SEVERE CONTAMINATION SEVERE FLUID CONDITION NORMAL

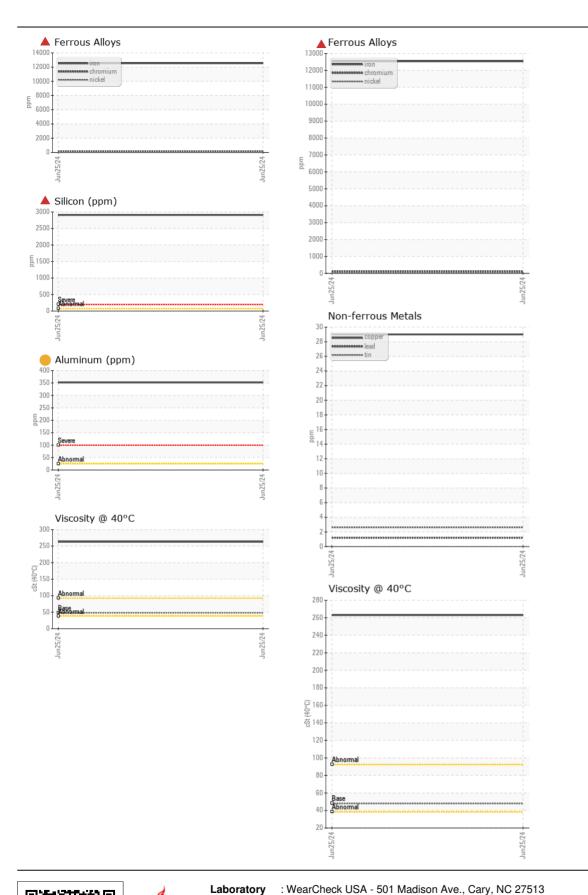

MCCLUNG-LOGAN EQUIPMENT CO - RICHMOND 1345 MOUNTAIN ROAD GLEN ALLEN, VA : 05 Jul 2024 - Jonathan Hester US 23060 Contact: Alex Anderson aanderson@mcclung-logan.com T: Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012) F: (804)266-1611

Certificate L2367

Sample No.

Lab Number : 06226849

Unique Number : 11110342

Test Package : CONST

: ML0002723

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Received

Diagnosed

Tested

: 02 Jul 2024

: 05 Jul 2024

Submitted By: Service - Alex Anderson Page 2 of 2