



# OIL ANALYSIS REPORT

WEAR	<b>SEVERE</b>
CONTAMINATION	<b>SEVERE</b>
FLUID CONDITION	<b>NORMAL</b>

## Store 3 - Norton

Machine Id  
**JOHN DEERE 160G EX22 (S/N HF056770)**

Component  
**Right Final Drive**  
Fluid  
**GEAR OIL SAE 90 (--- GAL)**

### RECOMMENDATION

We advise that you check all areas where dirt can enter the system. We recommend that you drain the oil from the component if this has not already been done. We advise that you inspect for the source(s) of wear. We recommend an early resample to monitor this condition.

### WEAR

Gear wear is indicated.










### CONTAMINATION

Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress.

### FLUID CONDITION

The oil is no longer serviceable due to the presence of contaminants.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		LEC0049341	---	---
Sample Date		Client Info		24 Jun 2024	---	---
Machine Age	hrs	Client Info		3927	---	---
Oil Age	hrs	Client Info		500	---	---
Filter Age	hrs	Client Info		0	---	---
Oil Changed		Client Info		Not Changd	---	---
Filter Changed		Client Info		Changed	---	---
Sample Status				SEVERE	---	---
PQ		ASTM D8184	>1250	60	---	---
Iron	ppm	ASTM D5185m	>750	▲ 1433	---	---
Chromium	ppm	ASTM D5185m	>9	▲ 9	---	---
Nickel	ppm	ASTM D5185m	>10	2	---	---
Titanium	ppm	ASTM D5185m		3	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>40	● 39	---	---
Lead	ppm	ASTM D5185m	>15	0	---	---
Copper	ppm	ASTM D5185m	>40	1	---	---
Tin	ppm	ASTM D5185m	>10	0	---	---
Vanadium	ppm	ASTM D5185m		<1	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---
Silicon	ppm	ASTM D5185m	>75	▲ 192	---	---
Potassium	ppm	ASTM D5185m	>20	11	---	---
Water		WC Method	>0.075	NEG	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.075	NEG	---	---
Sodium	ppm	ASTM D5185m	>51	3	---	---
Boron	ppm	ASTM D5185m	400	136	---	---
Barium	ppm	ASTM D5185m	200	0	---	---
Molybdenum	ppm	ASTM D5185m	12	0	---	---
Manganese	ppm	ASTM D5185m		11	---	---
Magnesium	ppm	ASTM D5185m	12	8	---	---
Calcium	ppm	ASTM D5185m	150	60	---	---
Phosphorus	ppm	ASTM D5185m	1650	1089	---	---
Zinc	ppm	ASTM D5185m	125	4	---	---
Sulfur	ppm	ASTM D5185m	22500	23260	---	---
Visc @ 40°C	cSt	ASTM D445	183	136	---	---

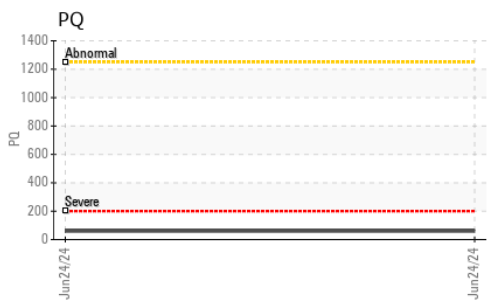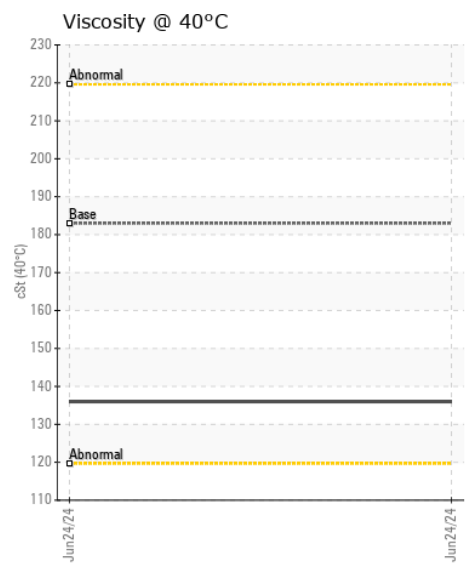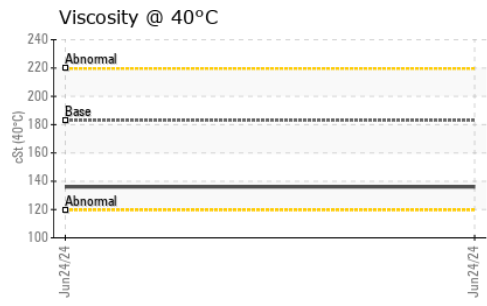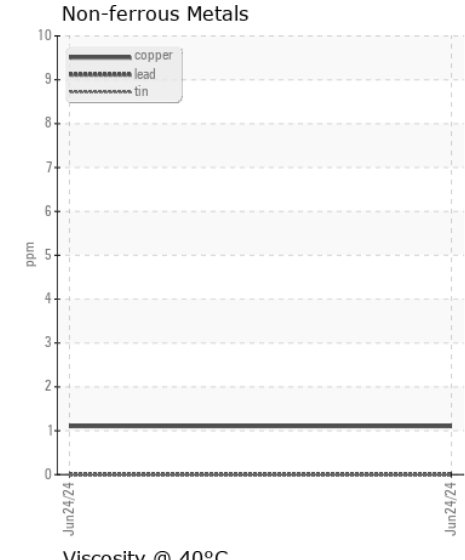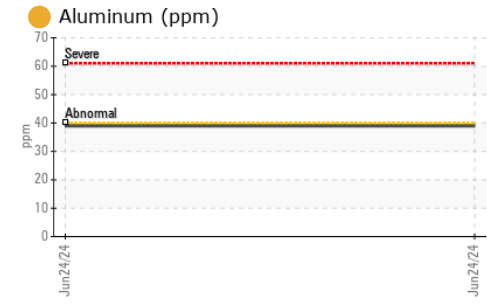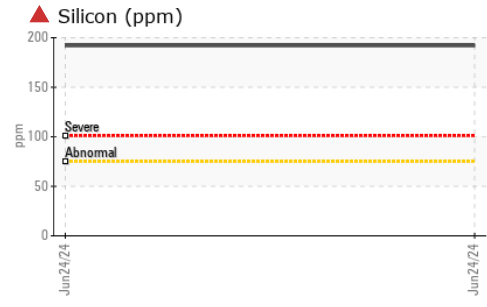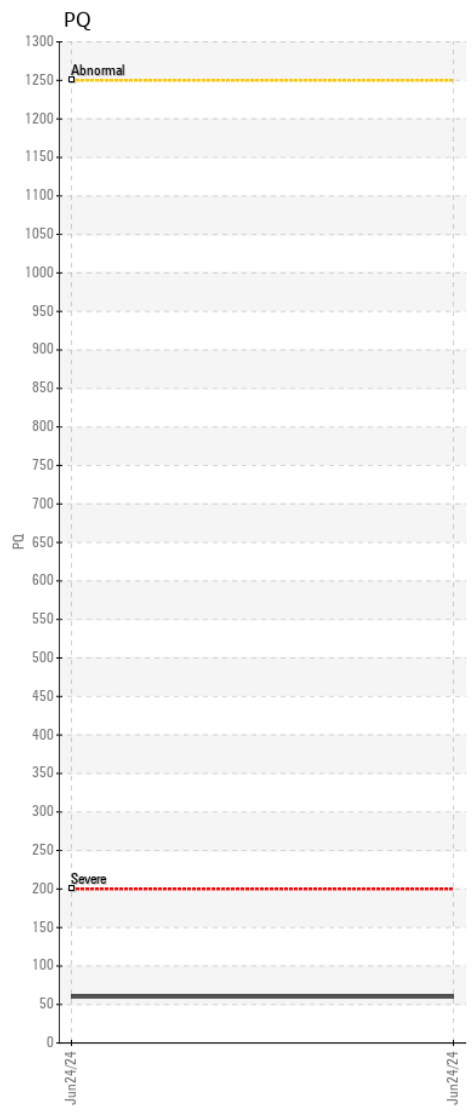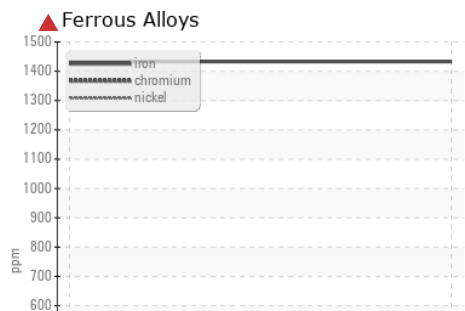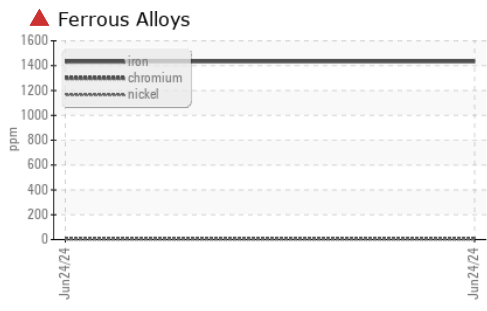

Certificate L2367

**Laboratory** : WearCheck USA - 501 Madison Ave., Cary, NC 27513  
**Sample No.** : LEC0049341 **Received** : 03 Jul 2024  
**Lab Number** : 06227756 **Tested** : 05 Jul 2024  
**Unique Number** : 11111249 **Diagnosed** : 06 Jul 2024 - Don Baldrige  
**Test Package** : CONST ( Additional Tests: PQ )

**LANE PIPELINE**  
 2946 E MAIN ST  
 BRIDGEPORT, WV  
 US 26330

Contact: JESSE WILBURN  
 jessewilburn@gmail.com  
 T: (740)440-0927

To discuss this sample report, contact Customer Service at 1-800-237-1369.

\* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)