HUTCHENS RENTZ-EDEN

OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	ABNORMAL
FLUID CONDITION	ABNORMAL

Machine Id
7702
Component
Diesel Engine
Fluid
DIESEL ENGINE OIL SAE 15W40 (--- GAL)

RECOMMENDATION

The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition. Please specify the component make and model with your next sample. Please specify the brand, type, and viscosity of the oil on your next sample.

WEAR

All component wear rates are normal.

CONTAMINATION

There is a moderate amount of fuel present in the oil. Tests confirm the presence of fuel in the oil.

FLUID CONDITION

The BN result indicates that there is suitable alkalinity remaining in the oil. Fuel is present in the oil and is lowering the viscosity. The oil is no longer serviceable due to the presence of contaminants.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		HRE0000493	WC0887528	WC0887584
Sample Date		Client Info		19 Jun 2024	20 Feb 2024	05 Feb 2024
Machine Age	mls	Client Info		472690	467566	467301
Oil Age	mls	Client Info		0	300	6000
Filter Age	mls	Client Info		0	300	6000
Oil Changed		Client Info		Changed	Changed	Changed
Filter Changed		Client Info		Changed	Changed	Changed
Sample Status				ABNORMAL	MARGINAL	SEVERE
Iron	ppm	ASTM D5185m	>100	16	2	23
Chromium	ppm	ASTM D5185m	>20	0	<1	<1
Nickel	ppm	ASTM D5185m	>4	0	0	0
Titanium	ppm	ASTM D5185m		<1	1	<1
Silver	ppm	ASTM D5185m	>3	0	0	0
Aluminum	ppm	ASTM D5185m	>20	2	2	3
Lead	ppm	ASTM D5185m	>40	0	0	1
Copper	ppm	ASTM D5185m	>330	0	<1	2
Tin	ppm	ASTM D5185m	>15	0	0	0
Vanadium	ppm	ASTM D5185m		0	0	<1
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Silicon	ppm	ASTM D5185m	>25	10	7	11
Potassium	ppm	ASTM D5185m	>20	0	2	<1
Fuel	%	ASTM D3524	>5	▲ 5.4	▲ 3.2	▲ 8.3
Water		WC Method	>0.2	NEG	NEG	NEG
Glycol		WC Method		NEG	NEG	NEG
Soot %	%	*ASTM D7844	>3	1.8	0.4	1.7
Nitration	Abs/cm	*ASTM D7624	>20	10.3	6.0	11.5
Sulfation	Abs/.1mm	*ASTM D7415	>30	23.4	19.5	24.7
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	NEG
Sodium	ppm	ASTM D5185m	>158	10	11	14
Boron	ppm	ASTM D5185m	250	118	165	14
Barium	ppm	ASTM D5185m	10	0	0	0
Molybdenum	ppm	ASTM D5185m	100	67	71	67
Manganese	ppm	ASTM D5185m		0	0	0
Magnesium	ppm	ASTM D5185m	450	381	335	304
Calcium	ppm	ASTM D5185m	3000	1372	1508	1766
Phosphorus	ppm	ASTM D5185m	1150	982	969	988
Zinc	ppm	ASTM D5185m	1350	1158	1142	1197
Sulfur	ppm	ASTM D5185m	4250	3560	3294	3271
Oxidation	Abs/.1mm	*ASTM D7414	>25	18.1	14.3	20.3
Base Number (BN)	mg KOH/g	ASTM D2896	8.5	5.8	7.6	6.2
Visc @ 100°C	cSt	ASTM D445	14.4	▲ 12.1	13.0	▲ 11.2

Fuel Dilution

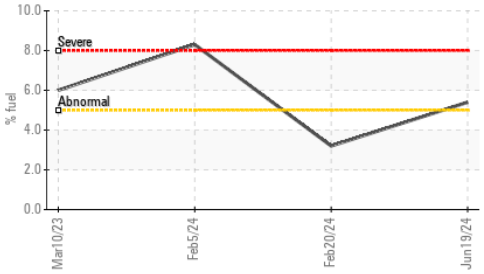

Viscosity @ 100°C

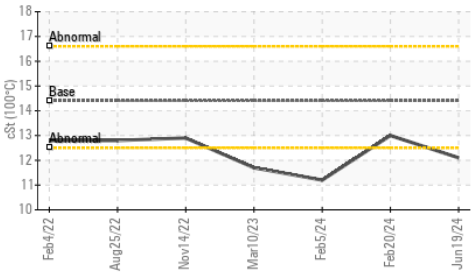

FT-IR (Direct Trend)

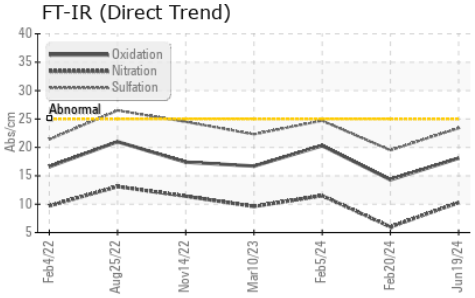

Base Number

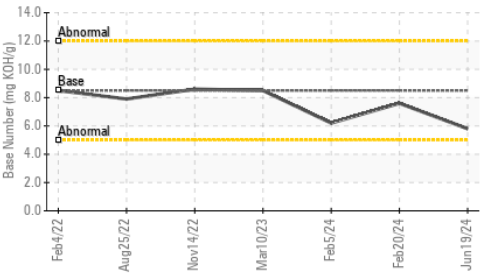

Ferrous Alloys

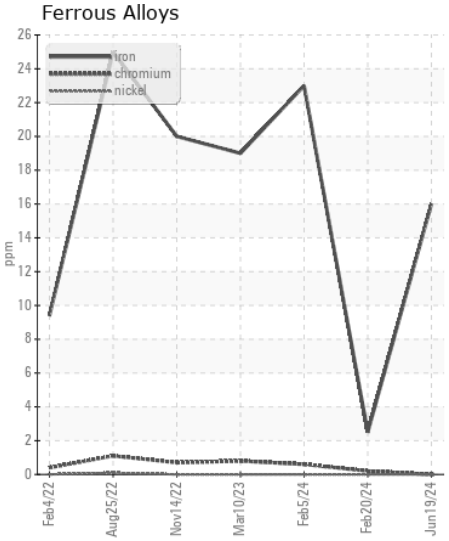

Non-ferrous Metals

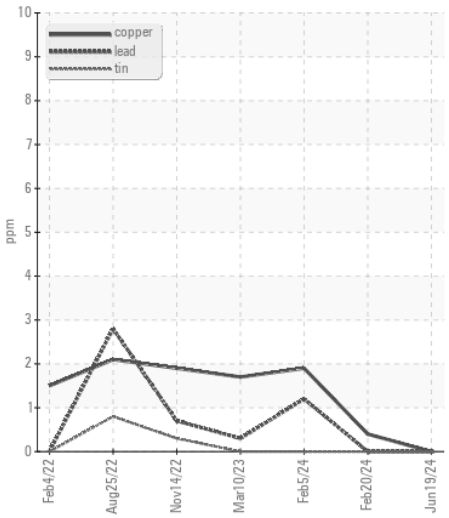

Viscosity @ 100°C

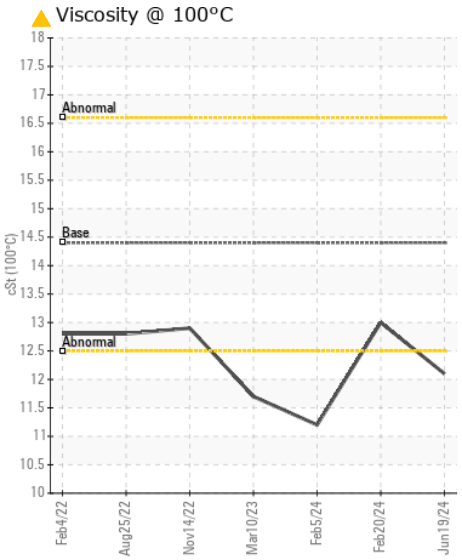

Base Number

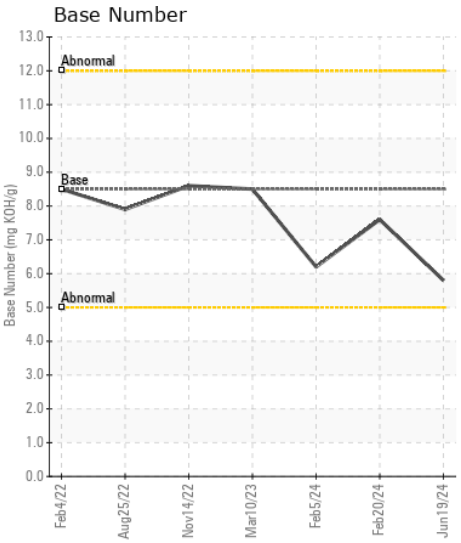

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : HRE0000493 **Received** : 11 Jul 2024
Lab Number : 06232960 **Tested** : 12 Jul 2024
Unique Number : 11116453 **Diagnosed** : 12 Jul 2024 - Wes Davis
Test Package : FLEET (Additional Tests: FuelDilution, PercentFuel)

To discuss this sample report, contact Customer Service at 1-800-237-1369.
** - Denotes test methods that are outside of the ISO 17025 scope of accreditation.*
Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

TOWN OF CHAPEL HILL
6900 MILLHOUSE RD
CHAPEL HILL, NC
US 27516
Contact: Lisa DePasqua
ldepasqua@townofchapelhill.org
T: (919)696-4941
F: