



OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	MARGINAL
FLUID CONDITION	ATTENTION

Machine Id
846-5220
 Component
Diesel Engine
 Fluid
MOBIL DELVAC 1300 SUPER15W40 (--- GAL)

RECOMMENDATION

No corrective action is recommended at this time. Confirm the source of the lubricant being utilized for top-up/fill. Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		RPL0021841	RPL0019427	---
Sample Date		Client Info		15 Jun 2024	15 Mar 2024	---
Machine Age	mls	Client Info		15843	7430	---
Oil Age	mls	Client Info		15843	0	---
Filter Age	mls	Client Info		15843	0	---
Oil Changed		Client Info		Not Changd	Not Changd	---
Filter Changed		Client Info		Not Changd	Not Changd	---
Sample Status				ATTENTION	NORMAL	---

WEAR

Metal levels are typical for a new component breaking in.

Iron	ppm	ASTM D5185m	>100	70	32	---
Chromium	ppm	ASTM D5185m	>20	2	<1	---
Nickel	ppm	ASTM D5185m	>4	<1	<1	---
Titanium	ppm	ASTM D5185m		<1	0	---
Silver	ppm	ASTM D5185m	>3	0	0	---
Aluminum	ppm	ASTM D5185m	>20	9	6	---
Lead	ppm	ASTM D5185m	>40	0	0	---
Copper	ppm	ASTM D5185m	>330	48	38	---
Tin	ppm	ASTM D5185m	>15	1	0	---
Vanadium	ppm	ASTM D5185m		0	0	---
White Metal	scalar	*Visual	NONE	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	---

CONTAMINATION











Light fuel dilution occurring. No other contaminants were detected in the oil.

Silicon	ppm	ASTM D5185m	>25	33	30	---
Potassium	ppm	ASTM D5185m	>20	21	11	---
Fuel	%	ASTM D3524	>5	▲ 4.1	<1.0	---
Water		WC Method	>0.2	NEG	NEG	---
Glycol		WC Method		NEG	NEG	---
Soot %	%	*ASTM D7844	>3	0.5	0.2	---
Nitration	Abs/cm	*ASTM D7624	>20	11.5	8.0	---
Sulfation	Abs/.1mm	*ASTM D7415	>30	24.7	22.9	---
Silt	scalar	*Visual	NONE	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG	---

FLUID CONDITION

Additive levels indicate the addition of a different brand, or type of oil. The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		5	4	---
Boron	ppm	ASTM D5185m	0	● 111	228	---
Barium	ppm	ASTM D5185m	0	2	0	---
Molybdenum	ppm	ASTM D5185m	0	108	110	---
Manganese	ppm	ASTM D5185m		7	5	---
Magnesium	ppm	ASTM D5185m	0	672	696	---
Calcium	ppm	ASTM D5185m		1461	1529	---
Phosphorus	ppm	ASTM D5185m		● 634	695	---
Zinc	ppm	ASTM D5185m		816	828	---
Sulfur	ppm	ASTM D5185m		2699	2714	---
Oxidation	Abs/.1mm	*ASTM D7414	>25	21.9	18.1	---
Base Number (BN)	mg KOH/g	ASTM D2896	9.4	5.9	7.8	---
Visc @ 100°C	cSt	ASTM D445	14	12.0	12.3	---

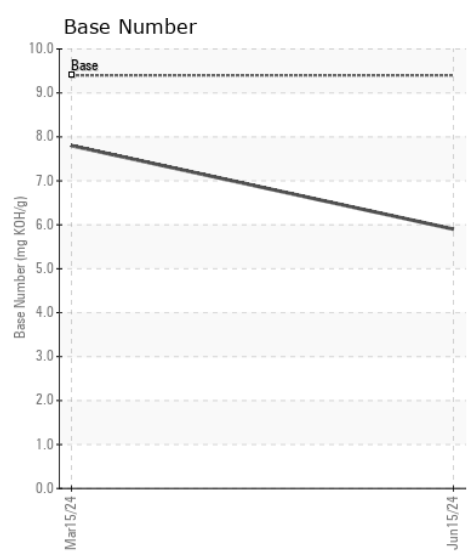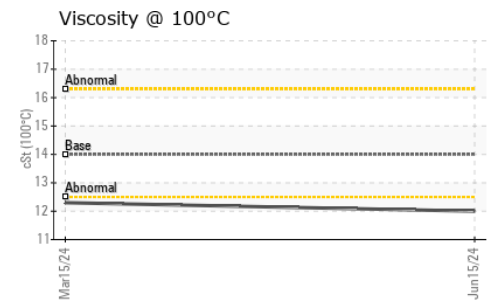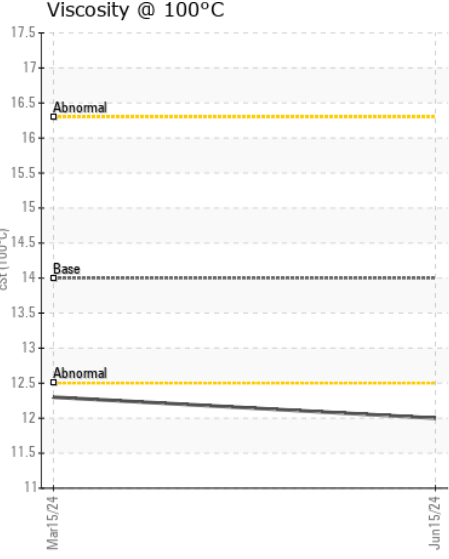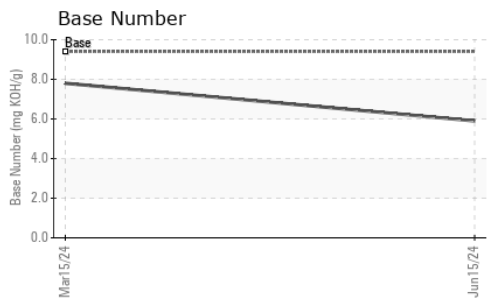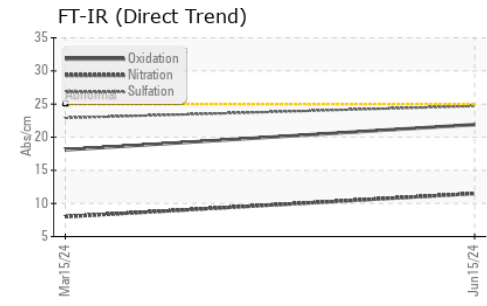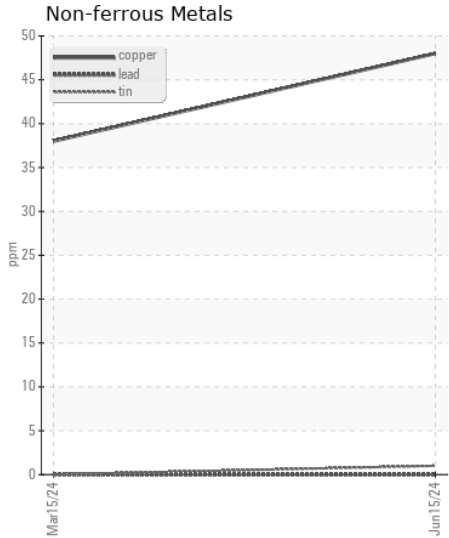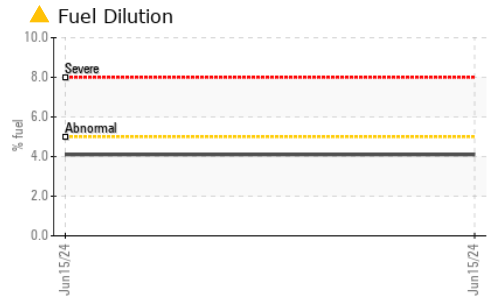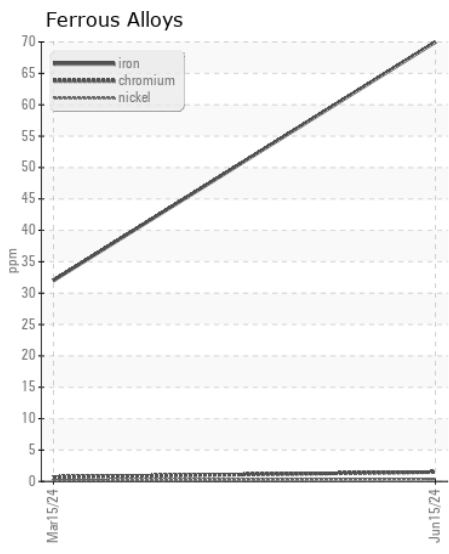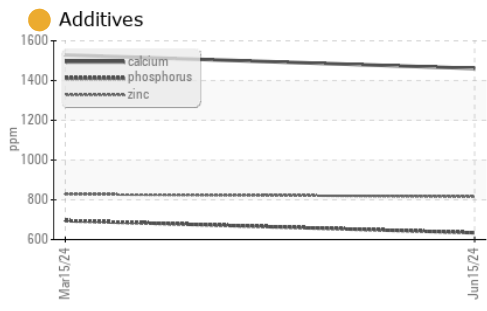

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : RPL0021841 **Received** : 12 Jul 2024
Lab Number : 06234465 **Tested** : 16 Jul 2024
Unique Number : 11123299 **Diagnosed** : 16 Jul 2024 - Wes Davis
Test Package : FLEET (Additional Tests: FuelDilution, PercentFuel)

RTL PACLEASE - 7006 - Pico Rivera
 7837 Telegraph Rd
 Pico Rivera, CA
 US 90660
 Contact: GERARDO CARROLA
 carrolag@rushenterprises.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:
F: