



WEAR	NORMAL
CONTAMINATION	ATTENTION
FLUID CONDITION	NORMAL

Area
[TINSMANS LANDSCAPING]
 Machine Id
JOHN DEERE 333G 1T0333GMCPF445757
 Component
Hydraulic System
 Fluid
JOHN DEERE HYDRAU (--- GAL)

RECOMMENDATION

No corrective action is recommended at this time. Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0221345	---	---
Sample Date		Client Info		15 Jul 2024	---	---
Machine Age	hrs	Client Info		267	---	---
Oil Age	hrs	Client Info		267	---	---
Filter Age	hrs	Client Info		267	---	---
Oil Changed		Client Info		Not Chngd	---	---
Filter Changed		Client Info		Not Chngd	---	---
Sample Status				ATTENTION	---	---

WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
PQ		ASTM D8184		16	---	---
Iron	ppm	ASTM D5185m	>20	10	---	---
Chromium	ppm	ASTM D5185m	>10	<1	---	---
Nickel	ppm	ASTM D5185m	>10	0	---	---
Titanium	ppm	ASTM D5185m		0	---	---
Silver	ppm	ASTM D5185m		0	---	---
Aluminum	ppm	ASTM D5185m	>10	3	---	---
Lead	ppm	ASTM D5185m	>10	<1	---	---
Copper	ppm	ASTM D5185m	>75	12	---	---
Tin	ppm	ASTM D5185m	>10	0	---	---
Vanadium	ppm	ASTM D5185m		0	---	---
White Metal	scalar	*Visual	NONE	NONE	---	---
Yellow Metal	scalar	*Visual	NONE	NONE	---	---

CONTAMINATION











There is a moderate amount of silt (particulates < 14 microns in size) present in the oil.

Silicon	ppm	ASTM D5185m	>20	2	---	---
Potassium	ppm	ASTM D5185m	>20	1	---	---
Water		WC Method	>0.1	NEG	---	---
Particles >4µm		ASTM D7647	>5000	6466	---	---
Particles >6µm		ASTM D7647	>1300	1691	---	---
Particles >14µm		ASTM D7647	>160	117	---	---
Particles >21µm		ASTM D7647	>40	23	---	---
Particles >38µm		ASTM D7647	>10	1	---	---
Particles >71µm		ASTM D7647	>3	1	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	20/18/14	---	---
Silt	scalar	*Visual	NONE	NONE	---	---
Debris	scalar	*Visual	NONE	NONE	---	---
Sand/Dirt	scalar	*Visual	NONE	NONE	---	---
Appearance	scalar	*Visual	NORML	NORML	---	---
Odor	scalar	*Visual	NORML	NORML	---	---
Emulsified Water	scalar	*Visual	>0.1	NEG	---	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oils additive package is suitable for further service.

Sodium	ppm	ASTM D5185m		2	---	---
Boron	ppm	ASTM D5185m		5	---	---
Barium	ppm	ASTM D5185m		0	---	---
Molybdenum	ppm	ASTM D5185m		3	---	---
Manganese	ppm	ASTM D5185m		0	---	---
Magnesium	ppm	ASTM D5185m		17	---	---
Calcium	ppm	ASTM D5185m	87	314	---	---
Phosphorus	ppm	ASTM D5185m	727	716	---	---
Zinc	ppm	ASTM D5185m	900	1033	---	---
Sulfur	ppm	ASTM D5185m	1500	2102	---	---
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.89	---	---
Visc @ 40°C	cSt	ASTM D445	65	55.54	---	---

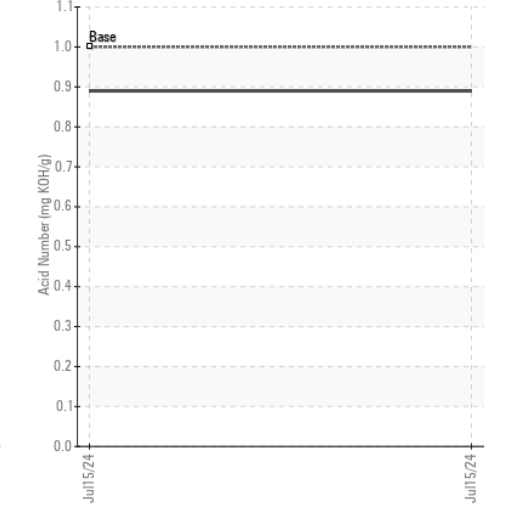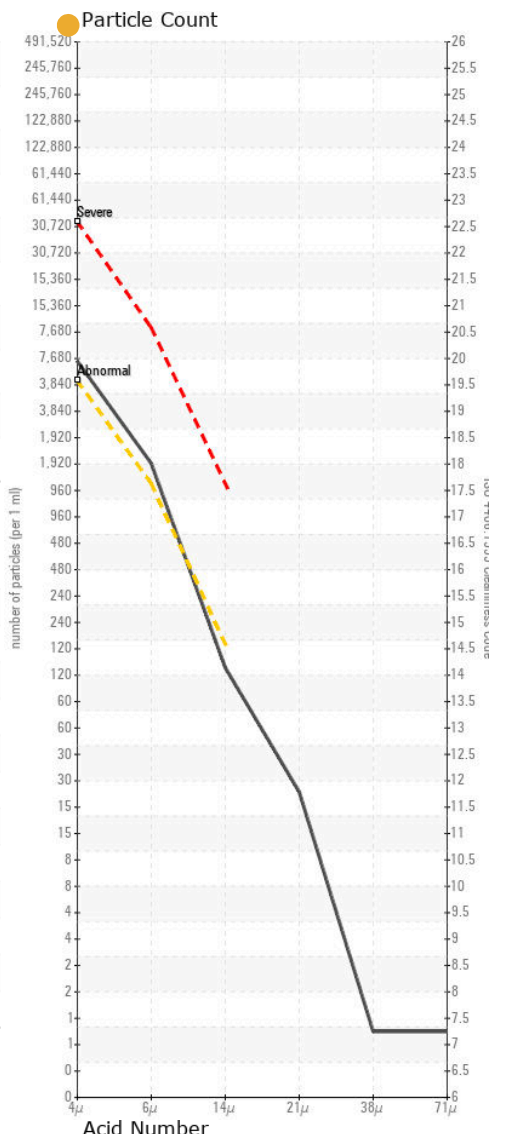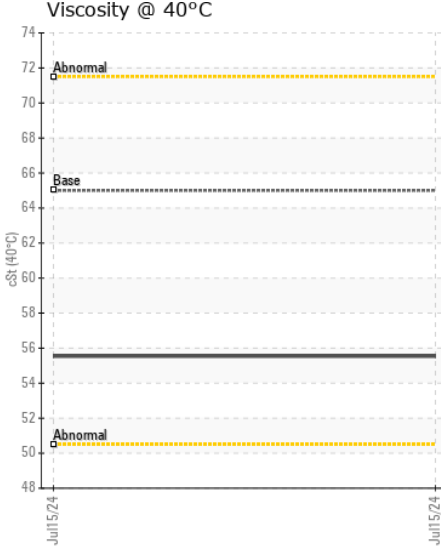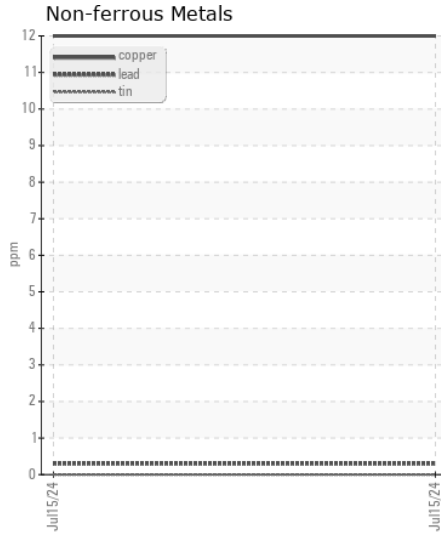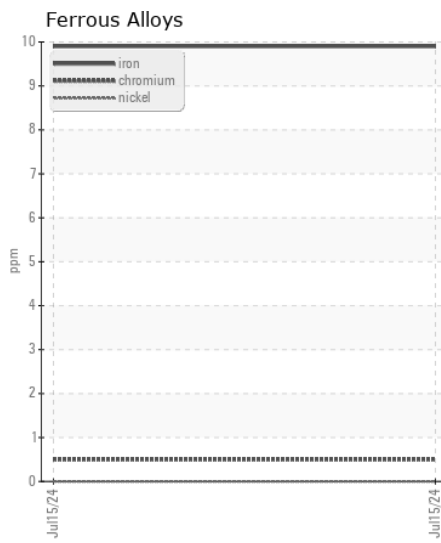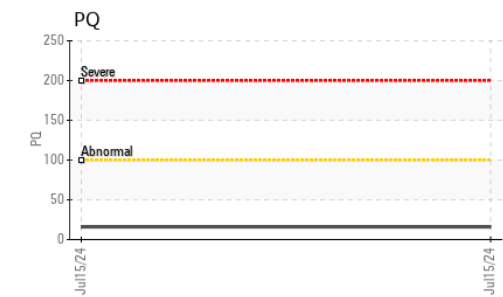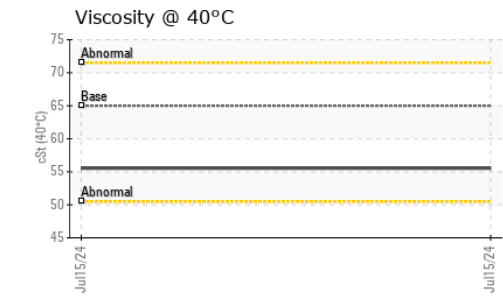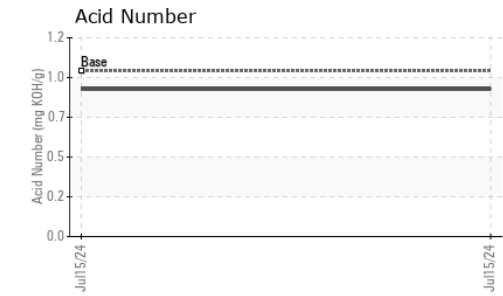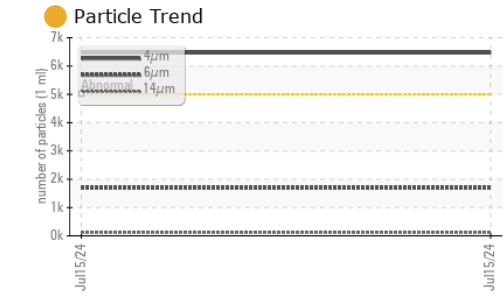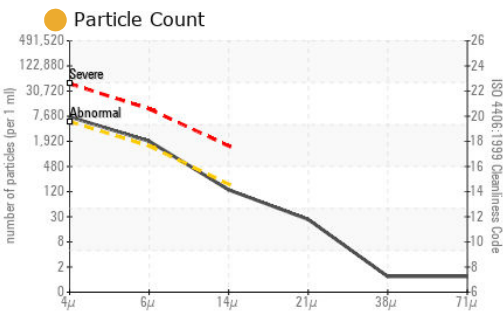

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : JR0221345 **Received** : 16 Jul 2024
Lab Number : 06238348 **Tested** : 16 Jul 2024
Unique Number : 11127182 **Diagnosed** : 16 Jul 2024 - Doug Bogart
Test Package : CONST (Additional Tests: PQ)

JRE - STEPHENSON
 245 YARDMASTER COURT
 STEPHENSON, VA
 US 22656-1761
 Contact: PHIL DAUGHERTY
 pdaugherty@jamesriverequipment.com
 T: x:
 F: (540)693-2588

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)