



VOLVO

OIL ANALYSIS REPORT

WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL



Area
[730409 RENTALS]
 Machine Id
VOLVO A25G 752678
 Component
Hydraulic System
 Fluid
VOLVO SUPER HYDRAULIC OIL 46 (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		VCP439982	VCP440255	---
Sample Date		Client Info		08 Jul 2024	06 Oct 2023	---
Machine Age	hrs	Client Info		2073	803	---
Oil Age	hrs	Client Info		0	0	---
Filter Age	hrs	Client Info		0	0	---
Oil Changed		Client Info		Not Changed	Changed	---
Filter Changed		Client Info		Changed	Changed	---
Sample Status				NORMAL	NORMAL	---

WEAR

All component wear rates are normal.

Iron	ppm	ASTM D5185m	>50	7	<1	---
Chromium	ppm	ASTM D5185m	>20	0	0	---
Nickel	ppm	ASTM D5185m	>10	0	0	---
Titanium	ppm	ASTM D5185m		0	0	---
Silver	ppm	ASTM D5185m		0	0	---
Aluminum	ppm	ASTM D5185m	>20	2	0	---
Lead	ppm	ASTM D5185m	>20	1	<1	---
Copper	ppm	ASTM D5185m	>150	3	2	---
Tin	ppm	ASTM D5185m	>20	<1	<1	---
Vanadium	ppm	ASTM D5185m		0	0	---
White Metal	scalar	*Visual	NONE	NONE	NONE	---
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	---

CONTAMINATION










The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>20	5	2	---
Potassium	ppm	ASTM D5185m	>20	0	0	---
Water		WC Method	>0.1	NEG	NEG	---
Particles >4µm		ASTM D7647		3238	6588	---
Particles >6µm		ASTM D7647	>5000	629	1343	---
Particles >14µm		ASTM D7647	>160	41	65	---
Particles >21µm		ASTM D7647	>40	10	14	---
Particles >38µm		ASTM D7647	>10	0	0	---
Particles >71µm		ASTM D7647	>3	0	0	---
Oil Cleanliness		ISO 4406 (c)	>-/19/14	19/16/13	20/18/13	---
Silt	scalar	*Visual	NONE	NONE	NONE	---
Debris	scalar	*Visual	NONE	NONE	NONE	---
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	---
Appearance	scalar	*Visual	NORML	NORML	NORML	---
Odor	scalar	*Visual	NORML	NORML	NORML	---
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG	---

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		1	1	---
Boron	ppm	ASTM D5185m	14	0	0	---
Barium	ppm	ASTM D5185m	0.0	0	0	---
Molybdenum	ppm	ASTM D5185m	0.0	0	0	---
Manganese	ppm	ASTM D5185m	0.0	0	<1	---
Magnesium	ppm	ASTM D5185m	2.6	1	1	---
Calcium	ppm	ASTM D5185m	49	70	60	---
Phosphorus	ppm	ASTM D5185m	354	338	316	---
Zinc	ppm	ASTM D5185m	419	431	409	---
Sulfur	ppm	ASTM D5185m	3719	2138	1676	---
Acid Number (AN)	mg KOH/g	ASTM D8045		0.37	0.27	---
Visc @ 40°C	cSt	ASTM D445	46	42.6	43.8	---

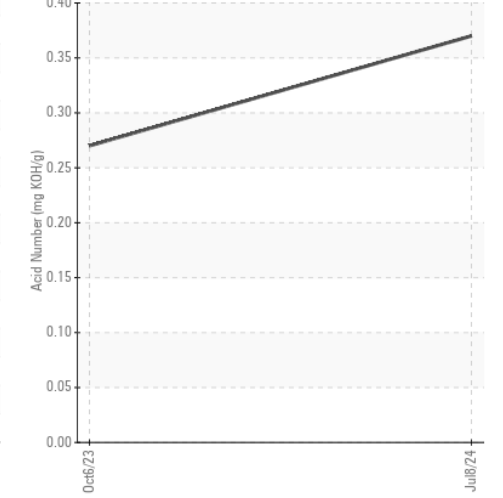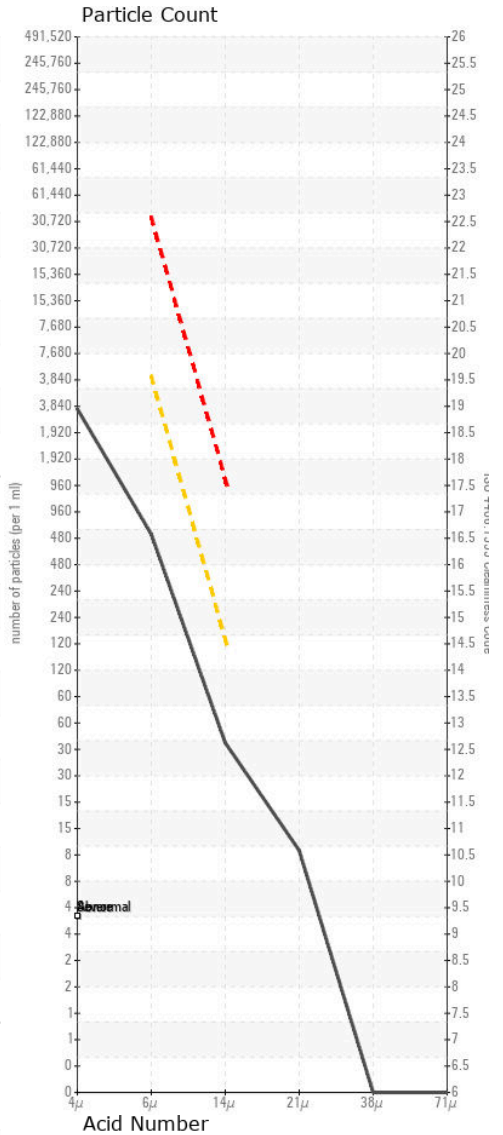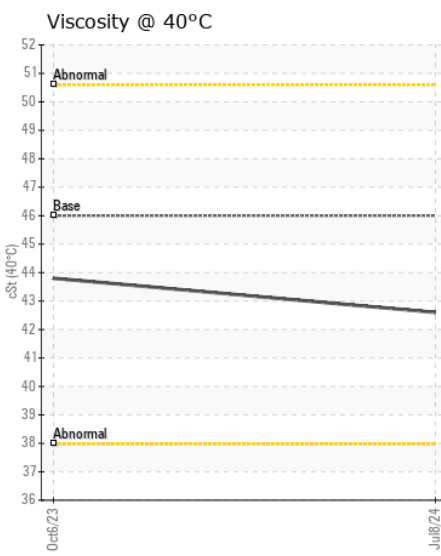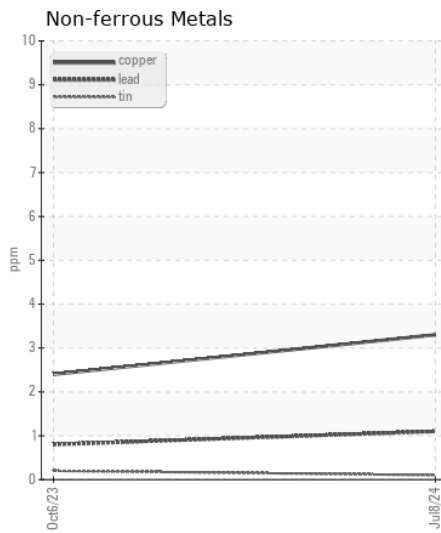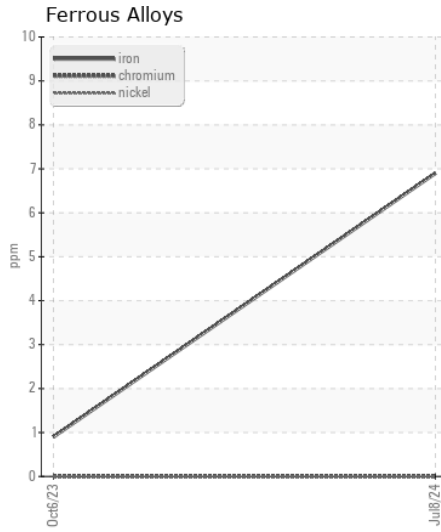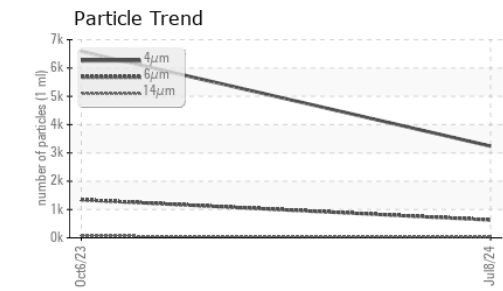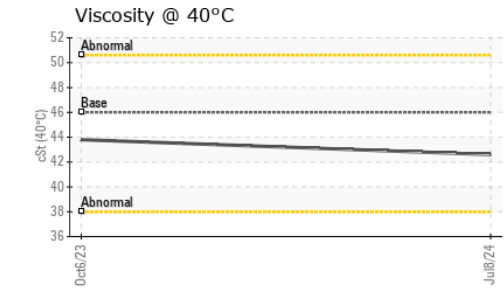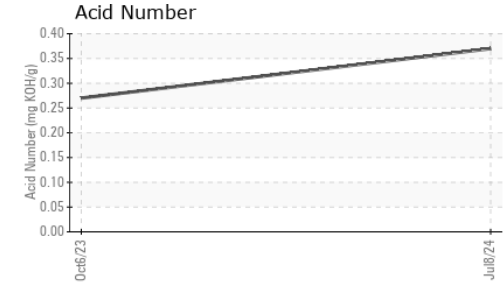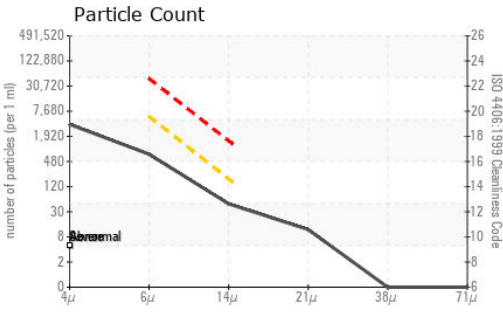

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : VCP439982 **Received** : 17 Jul 2024
Lab Number : 06239096 **Tested** : 18 Jul 2024
Unique Number : 11127930 **Diagnosed** : 18 Jul 2024 - Wes Davis
Test Package : MOB 2

ALTA EQUIPMENT COMPANY
 5210 REESE ROAD
 DAVIE, FL
 US 33314
 Contact: N. FACEY
 nfacey@altaequipfl.com
 T: (954)581-4744
 F: (954)583-0318

To discuss this sample report, contact Customer Service at 1-800-237-1369.
 * - Denotes test methods that are outside of the ISO 17025 scope of accreditation.
 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)