

Machine Id JOHN DEERE 260E 1DW260ETCMF711642 Component Front Differential Fluid JOHN DEERE HY-GARD HYD/TRANS (--- GAL)

RECOMMENDATION

The oil change at the time of sampling has been noted. No corrective action is recommended at this time. Resample at the next service interval to monitor.

.....

WEAR

Bearing and/or bushing wear is indicated.

CONTAMINATION


There is no indication of any contamination in the oil.

FLUID CONDITION

The condition of the oil is acceptable for the time in service.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0224571	JR0148682	JR0125730
Sample Date		Client Info		11 Jul 2024	22 Feb 2023	02 Sep 2022
Machine Age	hrs	Client Info		1985	915	461
Oil Age	hrs	Client Info		0	454	461
Filter Age	hrs	Client Info		0	454	0
Oil Changed		Client Info		Changed	Not Changd	Changed
Filter Changed		Client Info		Changed	Changed	N/A
Sample Status				ABNORMAL	NORMAL	NORMAL
PQ		ASTM D8184		107	120	78
Iron	ppm	ASTM D5185m	>500	277	150	133
Chromium	ppm	ASTM D5185m	>10	2	1	2
Nickel	ppm	ASTM D5185m	>10	12	9	7
Titanium	ppm	ASTM D5185m	210	<1	0	0
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m	>25	3	3	4
Lead	ppm	ASTM D5185m	>25	ح 1	<1	-
Copper	ppm	ASTM D5185m	>100	288	88	115
Tin	ppm	ASTM D5185m	>10	10	4	3
Vanadium	ppm	ASTM D5185m	210	0	0	0
White Metal	scalar	*Visual	NONE	LIGHT	MODER	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Silicon	ppm	ASTM D5185m	>75	16	12	12
Potassium	ppm	ASTM D5185m	>20	2	0	0
Water		WC Method	>.2	NEG	NEG	NEG
Silt	scalar	*Visual	NONE	MODER	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>.2	NEG	NEG	NEG
Sodium	ppm	ASTM D5185m		8	12	21
Boron	ppm	ASTM D5185m	6	33	32	107
Barium	ppm	ASTM D5185m	0	2	<1	3
Molybdenum	ppm	ASTM D5185m	0	1	<1	<1
Manganese	ppm	ASTM D5185m		30	27	43
Magnesium	ppm	ASTM D5185m	145	77	63	21
Calcium	ppm	ASTM D5185m	3570	3543	3056	3377
Phosphorus	ppm	ASTM D5185m	1290	948	895	1108
Zinc	ppm	ASTM D5185m	1640	1301	1053	1382
Sulfur	ppm	ASTM D5185m		3524	3340	3122
Visc @ 40°C	cSt	ASTM D445	57.0	53.3		62.3

Contact/Location: DAVID ZIEG - JAMASH

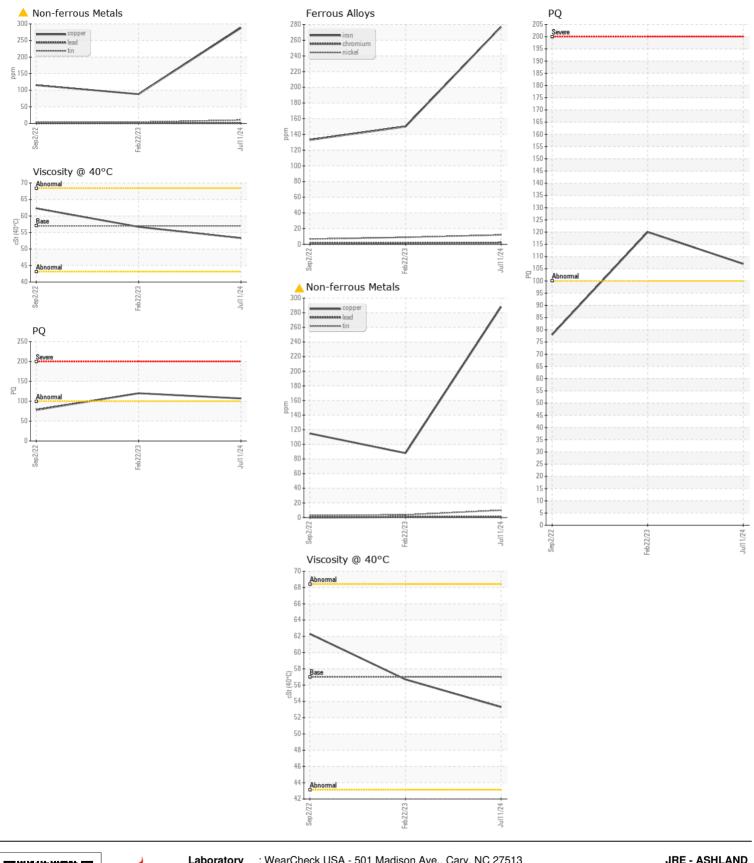

JRE - ASHLAND Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513 Sample No. : JR0224571 Received 11047 LEADBETTER RD : 17 Jul 2024 Ø Lab Number : 06239383 Tested ASHLAND, VA : 18 Jul 2024 Diagnosed Unique Number : 11128217 : 19 Jul 2024 - Don Baldridge US 23005 Test Package : CONST (Additional Tests: PQ) Contact: DAVID ZIEG Certificate L2367 To discuss this sample report, contact Customer Service at 1-800-237-1369. dzieg@jamesriverequipment.com * - Denotes test methods that are outside of the ISO 17025 scope of accreditation. T: (804)798-6001 F: (804)798-0292 Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

Contact/Location: DAVID ZIEG - JAMASH Page 2 of 2