
WEAR CONTAMINATION **FLUID CONDITION** **NORMAL SEVERE NORMAL**

Machine Id 10371C

Component Hydraulic System

AW HYDRAULIC OIL ISO 68 (--- GAL)

AW HYDRAULIC OIL ISO 68 (GAL)							
RECOMMENDATION	Test	UOM	Method	Limit/Abn	Current	History1	History2
We advise that you check all areas where contaminants can enter the system. We advise that you perform a filter service, and use off-line filtration to improve the cleanliness of the system fluid. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. Resample in 30-45 days to monitor this situation. The fluid was not specified, however, a fluid match indicates that this fluid is (GENERIC) AW HYDRAULIC OIL ISO 68. Please confirm.	Sample Number		Client Info		GFL0123362		
	Sample Date		Client Info		16 Jul 2024		
	Machine Age	hrs	Client Info		0		
	Oil Age	hrs	Client Info		0		
	Filter Age	hrs	Client Info		0		
	Oil Changed		Client Info		N/A		
	Filter Changed		Client Info		N/A		
	Sample Status				SEVERE		
WEAD			AOTM DEGOE				
WEAR All component wear rates are normal.	Iron	ppm	ASTM D5185m		3		
	Chromium	ppm	ASTM D5185m		1		
	Nickel	ppm	ASTM D5185m	>10	0		
	Titanium	ppm	ASTM D5185m		<1		
	Silver	ppm	ASTM D5185m	10	<1		
	Aluminum	ppm	ASTM D5185m		4		
	Lead	ppm	ASTM D5185m		0		
	Copper	ppm	ASTM D5185m		3		
	Tin	ppm	ASTM D5185m	>10	<1		
	Vanadium White Metal	ppm	ASTM D5185m	NONE	<1		
	White Metal	scalar	*Visual	NONE	NONE NONE		
	Yellow Metal	scalar	visuai	NONE	NONE		
CONTAMINATION	Silicon	ppm	ASTM D5185m	>20	<1		
CONTAMINATION	Potassium	ppm	ASTM D5185m		3		
There is a high amount of particulates (2 to 100 microns in size) present in the oil.	Water	le le · · ·	WC Method	>0.1	NEG		
	Particles >4µm		ASTM D7647		▲ 110464		
	Particles >6µm		ASTM D7647		▲ 28293		
	Particles >14µm		ASTM D7647		<u> </u>		
	Particles >21µm		ASTM D7647		A 89		
	Particles >38µm		ASTM D7647		2		
	Particles >71µm		ASTM D7647		0		
	Oil Cleanliness		ISO 4406 (c)	>19/17/14	24/22/16		
	Silt	scalar	*Visual	NONE	NONE		
	Debris	scalar	*Visual	NONE	NONE		
	Sand/Dirt	scalar	*Visual	NONE	NONE		
	Appearance	scalar	*Visual	NORML	NORML		
	Odor	scalar	*Visual	NORML	NORML		
	Emulsified Water	scalar	*Visual	>0.1	NEG		
FLUID CONDITION							
	Sodium	ppm	ASTM D5185m	_	0		
The AN level is acceptable for this fluid. The oil is still serviceable	Boron	ppm	ASTM D5185m		0		
provided that the contaminant(s) can be reduced to acceptable levels.	Barium	ppm	ASTM D5185m		0		
	Molybdenum	ppm	ASTM D5185m	5	<1		
	Manganese	ppm	ASTM D5185m		0		
	Magnesium	ppm	ASTM D5185m		3		
	Calcium	ppm	ASTM D5185m	200	49		
	Phosphorus	ppm	ASTM D5185m		312		
	Zinc	ppm	ASTM D5185m	370	448		
	Sulfur	ppm	ASTM D5185m		872		
	Acid Number (AN)	mg KOH/g	ASTM D8045		0.49		
	Visc @ 40°C	cSt	ASTM D445	68	63.0		

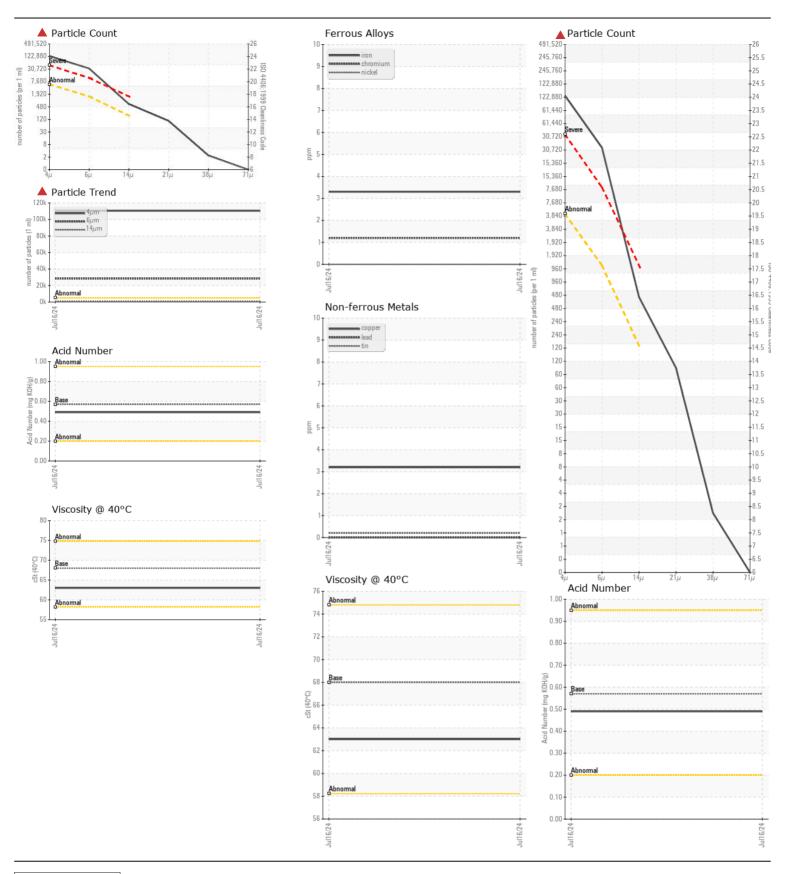



Report Id: GFL007 [WUSCAR] 06240217 (Generated: 07/19/2024 11:31:56) Rev: 1

Laboratory Sample No.

Lab Number : 06240217

: WearCheck USA - 501 Madison Ave., Cary, NC 27513 : GFL0123362

Received **Tested** Unique Number : 11129051 Diagnosed

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

: 18 Jul 2024 : 19 Jul 2024

: 19 Jul 2024 - Wes Davis

GFL Environmental - 007 - Brunswick 2809 Galloway Road Bolivia, NC

> US 28422 Contact: DONALD CRAVEN

Test Package : FLEET (Additional Tests: PrtCount) To discuss this sample report, contact Customer Service at 1-800-237-1369. dcraven@gflenv.com * - Denotes test methods that are outside of the ISO 17025 scope of accreditation. T:

Submitted By: DONALD CRAVEN

F: (910)253-4179