



WEAR	NORMAL
CONTAMINATION	NORMAL
FLUID CONDITION	NORMAL

Machine Id
JOHN DEERE 333G 1T0333GKPKF362405

Component
Hydraulic System

Fluid
JOHN DEERE HYDRAU (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Sample Number		Client Info		JR0216519	JR0216522	JR0047576
Sample Date		Client Info		18 Jul 2024	10 Jul 2024	23 Jul 2020
Machine Age	hrs	Client Info		1976	1971	444
Oil Age	hrs	Client Info		0	0	0
Filter Age	hrs	Client Info		0	0	0
Oil Changed		Client Info		N/A	N/A	N/A
Filter Changed		Client Info		N/A	N/A	N/A
Sample Status				NORMAL	ATTENTION	NORMAL

WEAR

All component wear rates are normal.

PQ	UOM	Method	Limit/Abn	Current	History1	History2
Iron	ppm	ASTM D5185m	>20	11	13	11
Chromium	ppm	ASTM D5185m	>10	0	0	<1
Nickel	ppm	ASTM D5185m	>10	0	0	<1
Titanium	ppm	ASTM D5185m		0	0	0
Silver	ppm	ASTM D5185m		0	0	0
Aluminum	ppm	ASTM D5185m	>10	1	1	1
Lead	ppm	ASTM D5185m	>10	0	0	4
Copper	ppm	ASTM D5185m	>75	3	1	6
Tin	ppm	ASTM D5185m	>10	0	0	0
Vanadium	ppm	ASTM D5185m		0	0	0
White Metal	scalar	*Visual	NONE	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE	NONE

CONTAMINATION











The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicon	ppm	ASTM D5185m	>20	3	4	4
Potassium	ppm	ASTM D5185m	>20	0	0	2
Water		WC Method	>0.1	NEG	NEG	NEG
Particles >4µm		ASTM D7647	>5000	3710	9402	1327
Particles >6µm		ASTM D7647	>1300	1204	1308	365
Particles >14µm		ASTM D7647	>160	92	25	32
Particles >21µm		ASTM D7647	>40	21	5	7
Particles >38µm		ASTM D7647	>10	1	1	0
Particles >71µm		ASTM D7647	>3	0	0	0
Oil Cleanliness		ISO 4406 (c)	>19/17/14	19/17/14	20/18/12	18/16/12
Silt	scalar	*Visual	NONE	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE	VLITE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.1	NEG	NEG	NEG

FLUID CONDITION

The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185m		4	7	2
Boron	ppm	ASTM D5185m		<1	1	1
Barium	ppm	ASTM D5185m		0	0	<1
Molybdenum	ppm	ASTM D5185m		<1	0	<1
Manganese	ppm	ASTM D5185m		<1	0	<1
Magnesium	ppm	ASTM D5185m		7	14	2
Calcium	ppm	ASTM D5185m	87	240	293	95
Phosphorus	ppm	ASTM D5185m	727	678	715	548
Zinc	ppm	ASTM D5185m	900	829	781	766
Sulfur	ppm	ASTM D5185m	1500	1982	2033	2338
Acid Number (AN)	mg KOH/g	ASTM D8045	1.0	0.74	0.84	0.948
Visc @ 40°C	cSt	ASTM D445	65	56.0	60.7	54.1

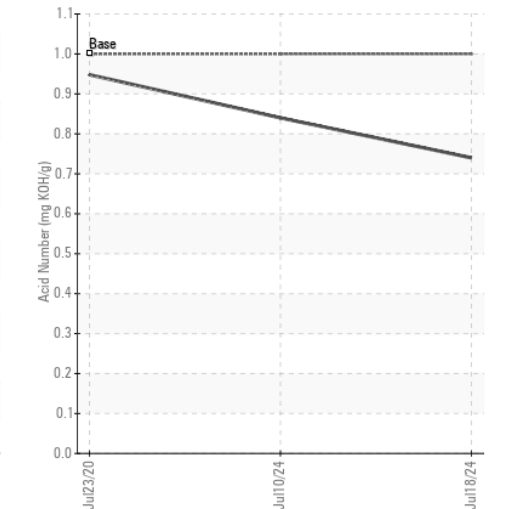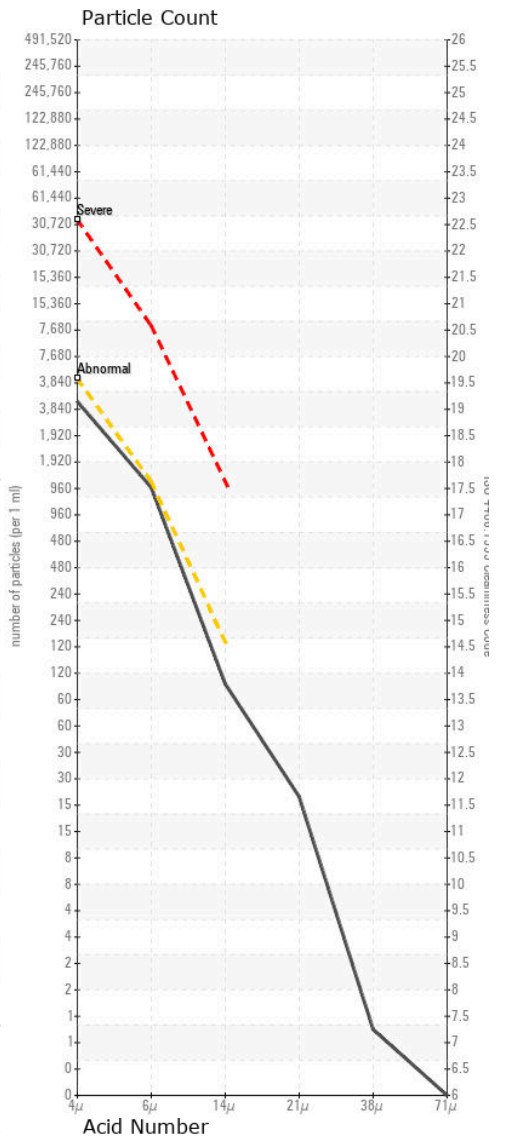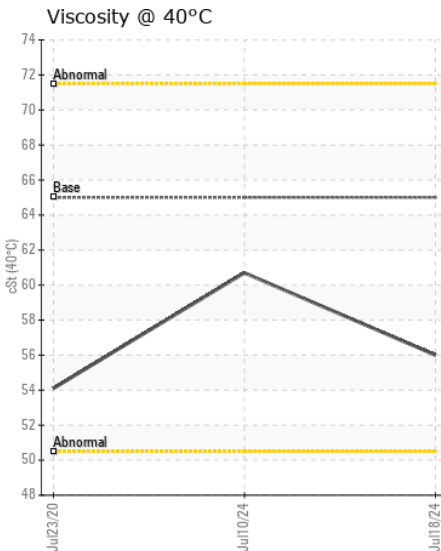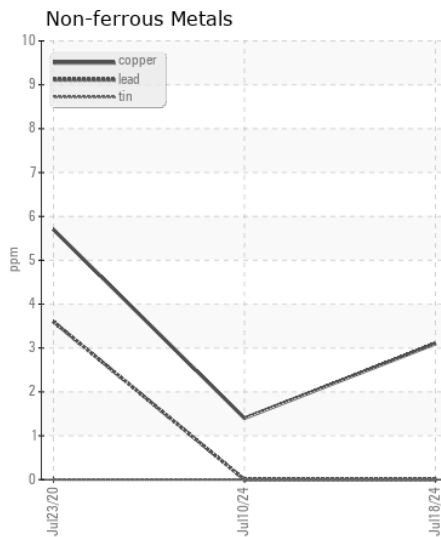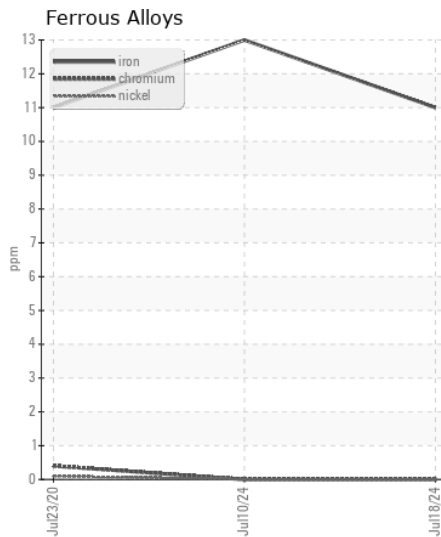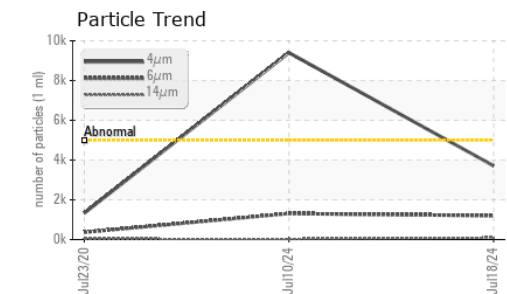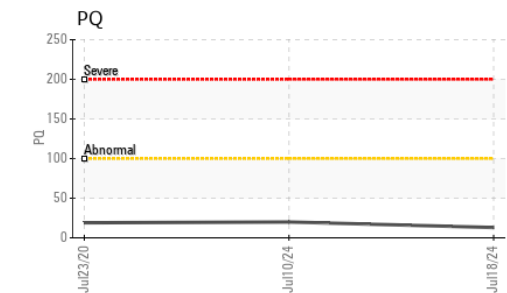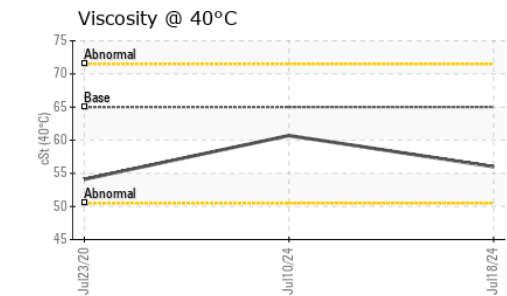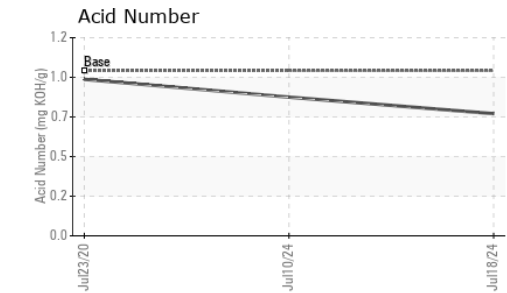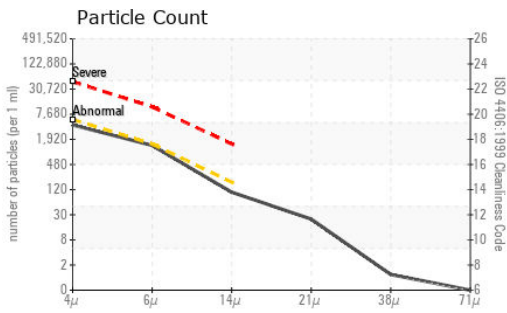

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513

Sample No. : JR0216519

Lab Number : 06241590

Unique Number : 11130424

Test Package : MOBCE (Additional Tests: PQ)

Received : 19 Jul 2024

Tested : 22 Jul 2024

Diagnosed : 22 Jul 2024 - Wes Davis

JRE - FISHERSVILLE

98 EXPO ROAD

FISHERSVILLE, VA

US 22939

Contact: MIKE JENKINS

MIKE.JENKINS@JAMESRIVEREQUIPMENT.COM

T: (540)292-3494

F: (540)337-1495

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)