



RAPPORT D'ANALYSE D'HUILE

USURE	NORMAL
CONTAMINATION	NORMAL
ÉTAT DU FLUIDE	NORMAL

Secteur
MICHAUDVILLE
Identité de la machine

1208
Composant
Transmission (Auto)
Fluide
DEXRON III (--- GAL)

RECOMMENDATION

Resample at the next service interval to monitor. The fluid was not specified, however, a fluid match indicates that this fluid is (GENERIC) DEXRON III. Please confirm. Please specify the component make and model with your next sample.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Numéro d'échant.		Client Info		PC0082569	PC0075868	PC0075815
Date d'échant.		Client Info		24 Oct 2023	10 Oct 2023	07 Jun 2023
Âge d la Machine	hrs	Client Info		13147	17362	12696
Âge de l'huile	hrs	Client Info		0	0	0
Âge du filtre	hrs	Client Info		0	0	0
Huile changée		Client Info		N/A	N/A	N/A
Filtre changé		Client Info		N/A	N/A	N/A
Statut de l'échant.				NORMAL	ABNORMAL	NORMAL

USURE

All component wear rates are normal.

Fer	ppm	ASTM D5185(m)	>160	8	▲ 179	64
Chrome	ppm	ASTM D5185(m)	>5	0	0	0
Nickel	ppm	ASTM D5185(m)	>5	0	0	0
Titane	ppm	ASTM D5185(m)		0	0	0
Argent	ppm	ASTM D5185(m)	>5	<1	<1	0
Aluminium	ppm	ASTM D5185(m)	>50	3	29	19
Plomb	ppm	ASTM D5185(m)	>50	1	14	12
Cuivre	ppm	ASTM D5185(m)	>225	2	41	10
Étain	ppm	ASTM D5185(m)	>10	0	2	2
Vanadium	ppm	ASTM D5185(m)		0	0	0
Métal blanc	scalar	Visual*	NONE	NONE	VLITE	NONE
Bronze	scalar	Visual*	NONE	NONE	NONE	NONE

CONTAMINATION












The water content is negligible. There is no indication of any contamination in the fluid.

Silicium	ppm	ASTM D5185(m)	>20	8	10	7
Potassium	ppm	ASTM D5185(m)	>20	0	<1	<1
Eau	%	ASTM D6304*	>0.1	0.065	---	0.023
ppm d'eau	ppm	ASTM D6304*	>1000	653.6	---	234.3
Limon	scalar	Visual*	NONE	NONE	NONE	NONE
Débris	scalar	Visual*	NONE	NONE	NONE	NONE
Saleté	scalar	Visual*	NONE	NONE	NONE	NONE
Apparence	scalar	Visual*	NORML	NORML	NORML	NORML
Odeur	scalar	Visual*	NORML	NORML	NORML	NORML
Eau émulsifiée	scalar	Visual*	>0.1	.2%	NEG	.2%

ÉTAT DU FLUIDE

The condition of the fluid is acceptable for the time in service.

Sodium	ppm	ASTM D5185(m)		2	6	4
Bore	ppm	ASTM D5185(m)		82	144	93
Baryum	ppm	ASTM D5185(m)		<1	<1	0
Molybdène	ppm	ASTM D5185(m)		<1	0	0
Manganèse	ppm	ASTM D5185(m)		0	1	<1
Magnésium	ppm	ASTM D5185(m)		2	1	<1
Calcium	ppm	ASTM D5185(m)		104	82	110
Phosphore	ppm	ASTM D5185(m)		217	357	293
Zinc	ppm	ASTM D5185(m)		9	5	23
Soufre	ppm	ASTM D5185(m)		1479	1389	1134
Visc 40°C	cSt	ASTM D7279(m)	26.0	34.1	35.1	34.5
Visc 100°C	cSt	ASTM D7279(m)	5.5	6.8	7	6.8
Indice de viscosité (VI)	Scale	ASTM D2270*	155	162	165	159

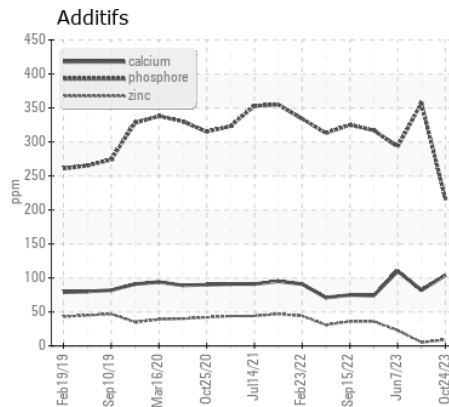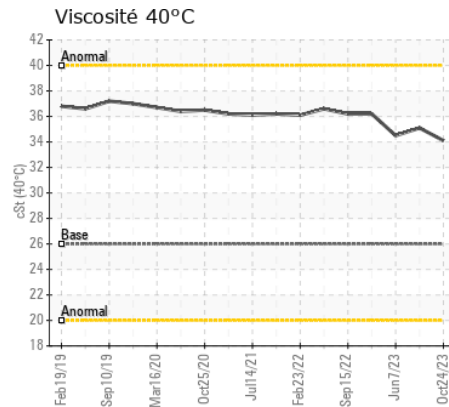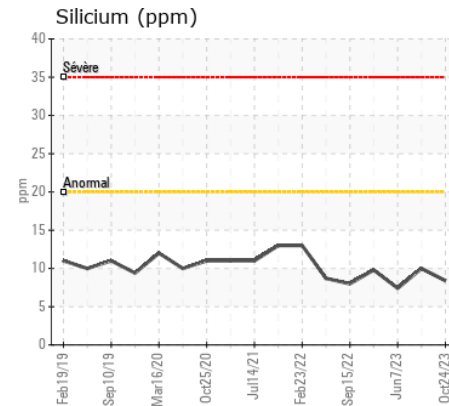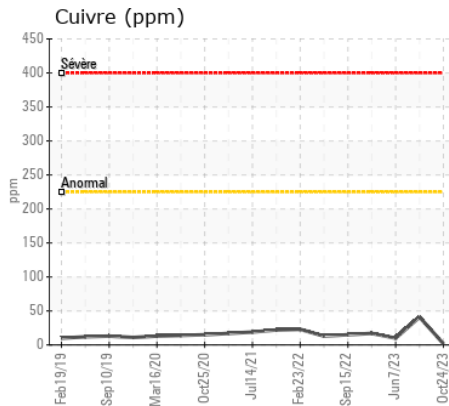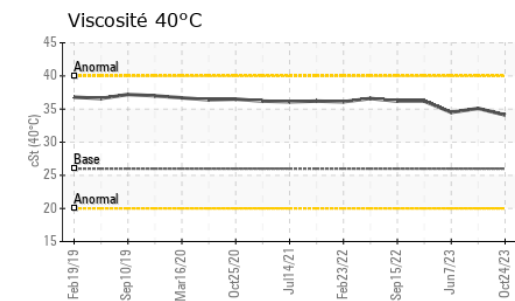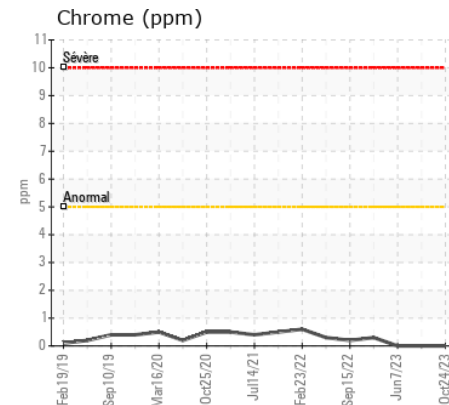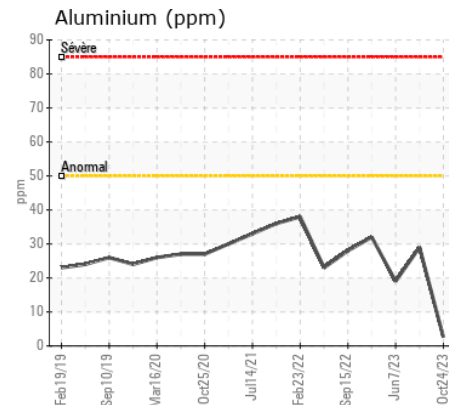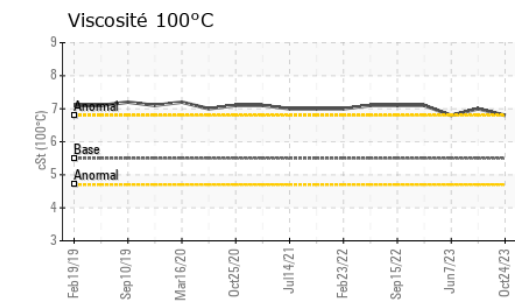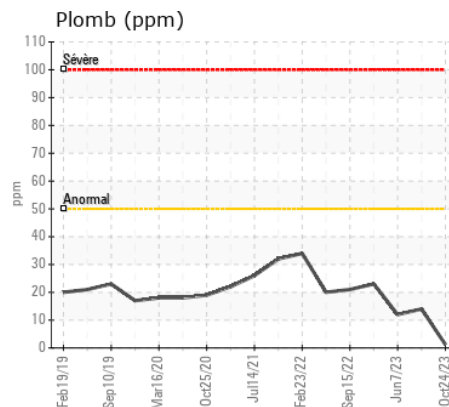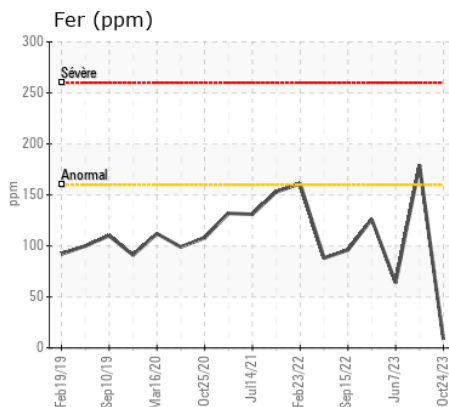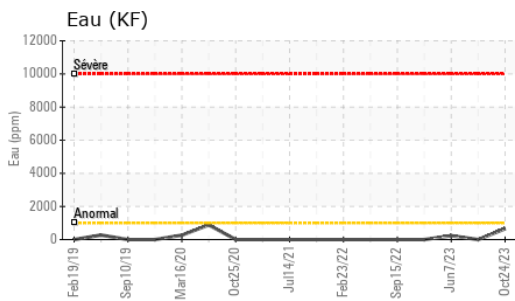

Laboratoire : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 LES ENTREPRISES MICHAUDVILLE INC.
N° d'échantillon : PC0082569 **Reçu** : 25 Oct 2023
N° de laboratoire : 02591796 **Diagnostiqué** : 26 Oct 2023
Numéro unique : 5668875 **Diagnostiqueur** : Kevin Marson
Analyse : MOB 1 (Additional Tests: KF, KV100, VI)

Pour discuter ce rapport, contacter le service à la clientèle au 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 La validez de los resultados y la interpretación se basan en la muestra y la información proporcionada.