



RAPPORT D'ANALYSE D'HUILE

USURE	NORMAL
CONTAMINATION	NORMAL
ÉTAT DU FLUIDE	NORMAL

Secteur

Equipment de Pont

Identité de la machine

17C01F#01 Grue avant bâbord (S/N L1149A)

Composant

Grue Avant gauche

Fluid

PETRO CANADA HYDREX MV ARCTIC 15 (800 LTR)

RECOMMENDATION

Resample at the next service interval to monitor.

Test	UOM	Method	Limit/Abn	Current	History1	History2
Numéro d'échant.		Client Info		WC0878492	WC0627040	WC0627048
Date d'échant.		Client Info		20 Mar 2024	18 Oct 2022	26 Aug 2022
Âge d la Machine	hrs	Client Info		361	240	204
Âge de l'huile	hrs	Client Info		0	240	204
Âge du filtre	hrs	Client Info		0	39	3
Huile changée		Client Info		Not Changd	Not Changd	Not Changd
Filtre changé		Client Info		Not Changd	Not Changd	Not Changd
Statut de l'échant.				NORMAL	NORMAL	NORMAL

USURE

All component wear rates are normal.

Fer	ppm	ASTM D5185(m)	>20	<1	<1	<1
Chrome	ppm	ASTM D5185(m)	>10	0	0	0
Nickel	ppm	ASTM D5185(m)	>10	0	0	<1
Titane	ppm	ASTM D5185(m)		0	0	0
Argent	ppm	ASTM D5185(m)		0	0	0
Aluminium	ppm	ASTM D5185(m)	>10	0	<1	0
Plomb	ppm	ASTM D5185(m)	>20	0	<1	<1
Cuivre	ppm	ASTM D5185(m)	>20	<1	<1	<1
Étain	ppm	ASTM D5185(m)	>10	0	0	0
Vanadium	ppm	ASTM D5185(m)		0	0	0
Métal blanc	scalar	Visual*	NONE	NONE	NONE	NONE
Bronze	scalar	Visual*	NONE	NONE	NONE	NONE

CONTAMINATION










The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Silicium	ppm	ASTM D5185(m)	>15	0	0	0
Potassium	ppm	ASTM D5185(m)	>20	0	<1	<1
L'eau		WC Method	>0.05	NEG	NEG	NEG
Particules >4µ		ASTM D7647	>5000	739	3301	2146
Particules >6µ		ASTM D7647	>1300	95	641	258
Particules >14µ		ASTM D7647	>160	5	36	8
Particules >21µ		ASTM D7647	>40	2	12	2
Particules >38µ		ASTM D7647	>10	1	0	1
Particules >71µ		ASTM D7647	>3	0	0	0
Propreté de l'huile		ISO 4406 (c)	>19/17/14	17/14/10	19/17/12	18/15/10
Limon	scalar	Visual*	NONE	NONE	NONE	NONE
Débris	scalar	Visual*	NONE	NONE	NONE	NONE
Saleté	scalar	Visual*	NONE	NONE	NONE	NONE
Apparence	scalar	Visual*	NORML	NORML	NORML	NORML
Odeur	scalar	Visual*	NORML	NORML	NORML	NORML
Eau émulsifiée	scalar	Visual*	>0.05	NEG	NEG	NEG

ÉTAT DU FLUIDE

The oil viscosity is higher than typical. The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Sodium	ppm	ASTM D5185(m)		<1	<1	<1
Bore	ppm	ASTM D5185(m)	0	0	0	<1
Baryum	ppm	ASTM D5185(m)	0	0	0	0
Molybdène	ppm	ASTM D5185(m)	0	0	0	0
Manganèse	ppm	ASTM D5185(m)	0	0	0	0
Magnésium	ppm	ASTM D5185(m)	0	<1	0	0
Calcium	ppm	ASTM D5185(m)	50	51	53	50
Phosphore	ppm	ASTM D5185(m)	330	335	358	349
Zinc	ppm	ASTM D5185(m)	430	427	412	403
Soufre	ppm	ASTM D5185(m)	760	1999	2093	2030
Indice d'acidité	mg KOH/g	ASTM D974*	0.70	0.44	0.44	0.50
Visc 40°C	cSt	ASTM D7279(m)	13.6	15.8	16.1	16.1

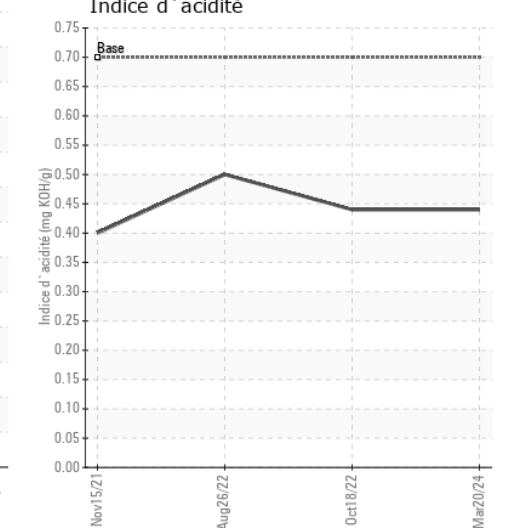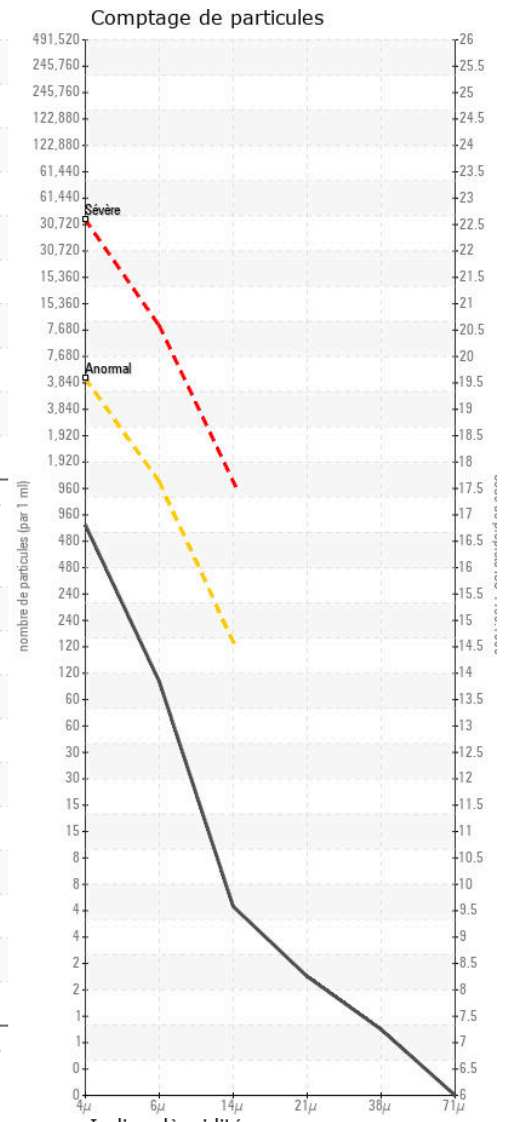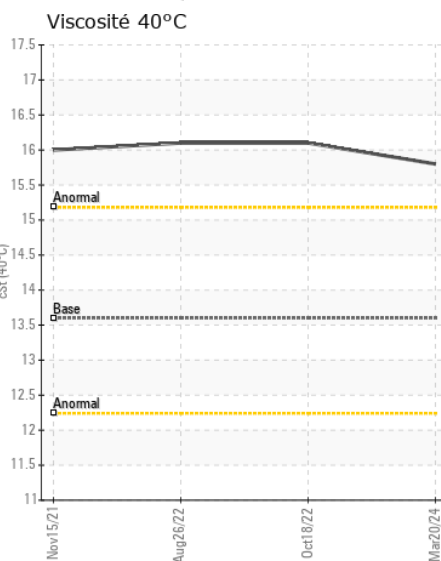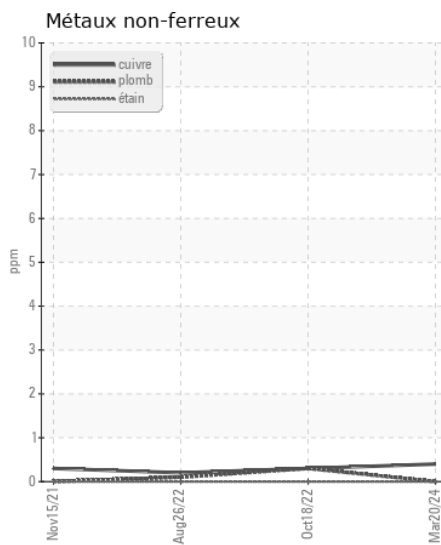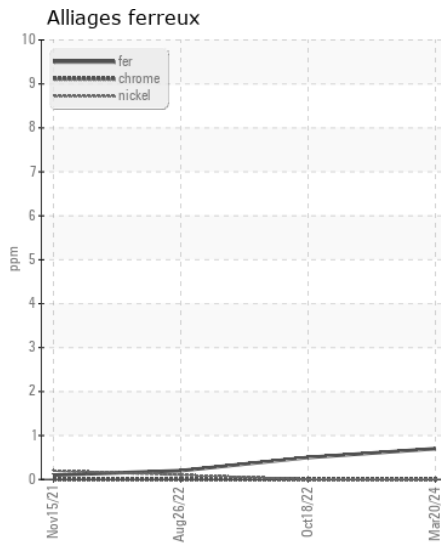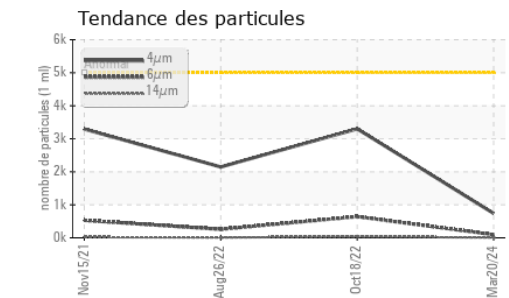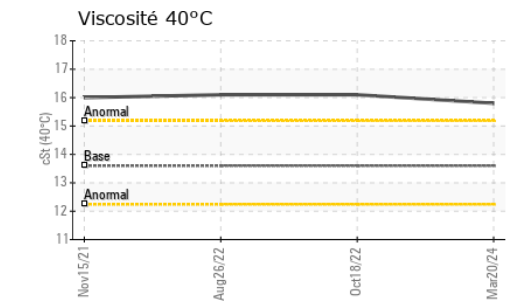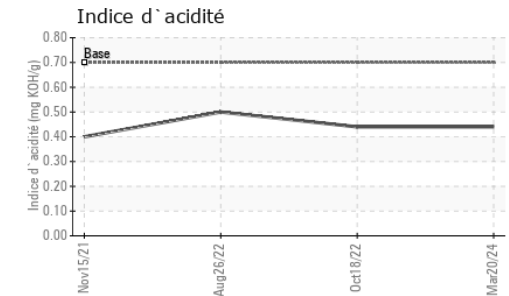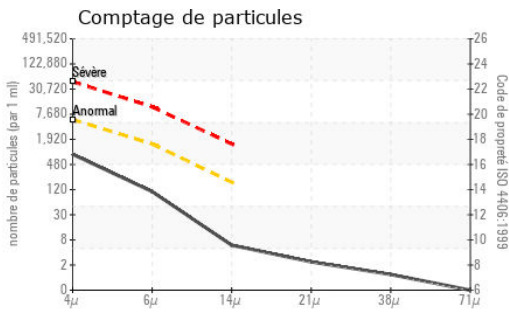

Laboratoire : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
N° d'échantillon : WC0878492
N° de laboratoire : 02624281
Numéro unique : 5749400
Analyse : MAR 2

Reçu : 25 Mar 2024
Tested : 26 Mar 2024
Diagnostiqué : 26 Mar 2024 - Kevin Marson

Canadian Coast Guard
 CCGS Amundsen, 101 Boul. Champlain
 Quebec, QC
 CA G1K 7Y7
 Contact: Chief Engineer
 amundsense@ccgs-ngcc.gc.ca
 T: (418)953-8233
 F: x:

Pour discuter ce rapport, contacter le service à la clientèle au 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 La validez de los resultados y la interpretación se basan en la muestra y la información proporcionada.