


WANSON BH/INC 1200


Customer: PTRHTF40127	System Information	Sample Information
Dalco Foods B.V	System Volume: 4200 gal	Lab No: 02436771
Everdenberg 50	Bulk Operating Temp: 518F / 270C	Analyst: Bill Quesnel CLS,OMA II,MLA-
Oosterhout, 4902TT Netherlands	Heating Source:	III,LLA-I
Attn: Wilbert Snijers	Blanket:	Sample Date: 07/30/21
Tel:	Fluid: PETRO CANADA PURITY FG HEAT TRANSFER FLUID	Received Date: 08/04/21
E-Mail: w.snijers@klt.nl	Make: WANSON	Completed: 08/10/21
		Bill Quesnel CLS,OMA II,MLA-III,LLA-I

Recommendation: Flash Point (COC) is very low and off specification. Recommend venting the system in order to reduce number of low boilers and recover flash point.

Comments: COC Flash Point is severely low. (GCD) 10% Distillation Point is abnormally low. (GCD) % < 335°C is marginally high.

Sample Date	Received Date	Fluid Age	Sample Location	Flash Point (COC)	Water (KF)	Viscosity (40°C)	Acid Number	Solids	GCD 10%	GCD 50%	GCD 90%	GCD % < 335°C
	mm/dd/yy			°F/°C	ppm	cSt	mg/KOH/ g	%wt	°F/°C	°F/°C	°F/°C	%
07/30/21	08/04/21	3.3y		313 / 156	26.1	25.1	0.32	0.136	647 / 341	797 / 425	896 / 480	8.86
04/07/21	04/13/21	3.0y		306 / 152	22.8	23.0	0.26	0.128	592 / 311	788 / 420	908 / 486	11.83
11/02/20	11/09/20	2.5y		298 / 148	9.6	24.6	0.30	0.136	649 / 343	798 / 425	899 / 482	8.68
04/10/20	04/17/20	1.9y		324 / 162	19.3	25.7	0.28	0.065	677 / 358	800 / 427	898 / 481	6.44
11/14/19	11/26/19	1.5y		338 / 170	10.4	25.9	0.284	0.106	616 / 325	780 / 416	883 / 473	<mark>10.68</mark>

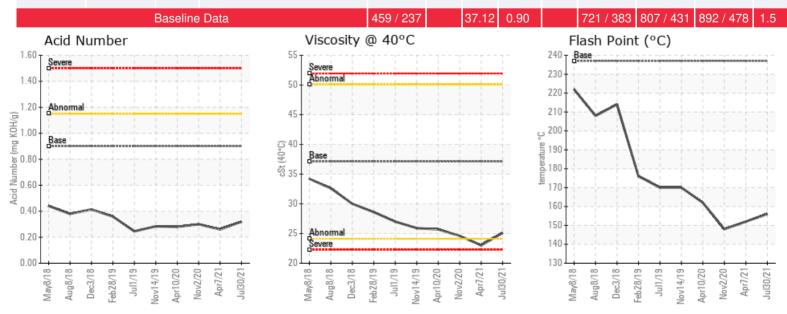

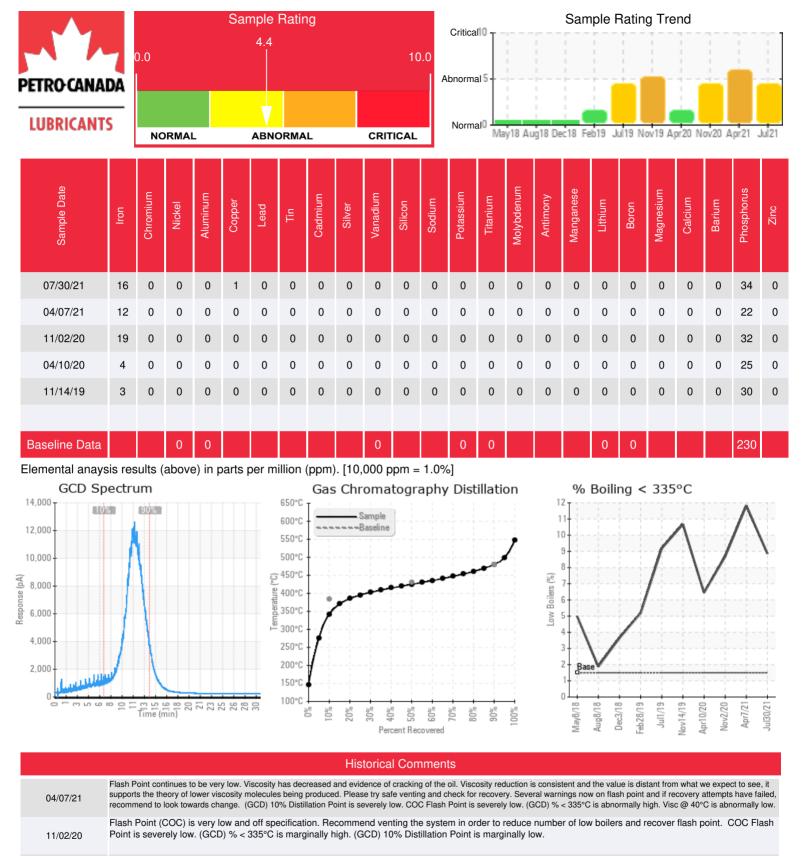

04/10/20	Whilst sample rating looks to have recovered, other parameters, namely Flash Point and viscosity continue to decline. Viscosity has decreased and evidence of cracking of the oil (shape of curve), also reducing flash point. Please try safe venting and check for recovery. Otherwise, operating at 270C is well above the current flash point which has reduced down to 162C. Several warnings now on flash point and if recovery attempts have failed, recommend to look towards change. Viscosity reduction is consistent and the value is distant from what we expect to see, it supports the theory of lower viscosity molecules being produced. COC Flash Point is severely low.
11/1//10	Sample continues to deteriorate. How long has the system been running as there are inconsistent values of age input against previous samples. Viscosity has decreased and evidence of cracking of the oil (shape of curve), also reducing flash point and 10% distillation. Please try safe venting and check for recovery. Otherwise, operating at 270C is well above the current flash point which has reduced down to

11/14/19 (shape of curve), also reducing flash point and 10% distillation. Please try safe venting and check for recovery. Otherwise, operating at 270C is well above the current flash point which has reduced down to 170C. Recommned venting and re-sample to check recovery. If continues to deteriorate look towards a change. Please, again, clarify the actual operating time as the sequence does not make sense in previous samples (GCD) 10% Distillation Point is severely low. COC Flash Point is severely low. (GCD) % < 335°C is marginally high.

Petro-Canada makes no representation or warranty of any kind, either express or implied, as to the accuracy or completeness of the analysis and assumes no responsibility and shall have no liability whatsoever with respect to such analysis, or a party's use of it. Petro-Canada is a division of HollyFrontier Corporation.