

[Sandeno East Asphalt Plant] DCONSTRUCTIONEAST

Customer: PTRHTF30107
 D-CONSTRUCTION
 16805 QUARRY RD
 MORRIS, IL 60450 USA
 Attn: Chris Lenzie
 Tel: (815)405-6831
 E-Mail: clenzie@sandenoinc.com




System Information
 System Volume: 350 gal
 Bulk Operating Temp: 500F / 260C
 Heating Source:
 Blanket:
 Fluid: PETRO CANADA PETRO-THERM
 Make: BURKE



Sample Information
 Lab No: 02542196
 Analyst: Yvette Trzcinski
 Sample Date: 02/08/23
 Received Date: 02/28/23
 Completed: 03/06/23
 Yvette Trzcinski
 yvette.trzcinski@HFSinclair.com

Recommendation: Pentane Solids are very high as is the acid number I recommend resampling to ensure this is a representative sample of the oil in the system before making any recommendations.

Comments: Pentane Insolubles levels are severely high. Acid Number (AN) is abnormally high. Visc @ 40°C is abnormally low.




Sample Date	Received Date	Fluid Age	Sample Location	Flash Point (COC)	Water (KF)	Viscosity (40°C)	Acid Number	Solids	GCD 10%	GCD 50%	GCD 90%	GCD % < 335°C
	mm/dd/yy			°F/°C	ppm	cSt	mg/KOH/g	%wt	°F/°C	°F/°C	°F/°C	%
02/08/23	02/28/23	2.0y		385 / 196	460.6	28.2	0.69	0.656	678 / 359	805 / 430	915 / 491	6.01
03/25/22	04/01/22	2.0y	SANDENO EAST	388 / 198	45.8	28.3	0.59	0.166	676 / 358	805 / 430	917 / 492	6.03
12/21/21	12/30/21	3.0y	return,before pump	403 / 206	24.9	28.1	0.45	0.145	677 / 358	806 / 430	917 / 492	6.09
06/24/20	06/25/20	0.0y	EXPANSION	396 / 202	44.9	26.5	0.61	0.440	662 / 350	800 / 426	913 / 490	7.44
10/25/19	11/22/19	5.0y		410 / 210	20.5	28.2	0.813	0.517	641 / 339	748 / 398	880 / 471	8.26
Baseline Data				433 / 223		34.2	0.03		720 / 382	817 / 436	900 / 482	1.00

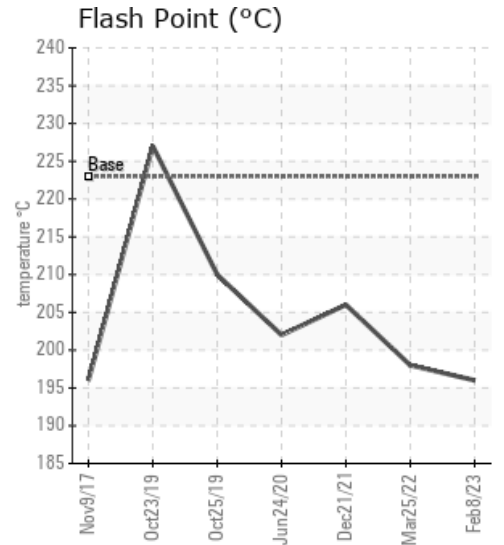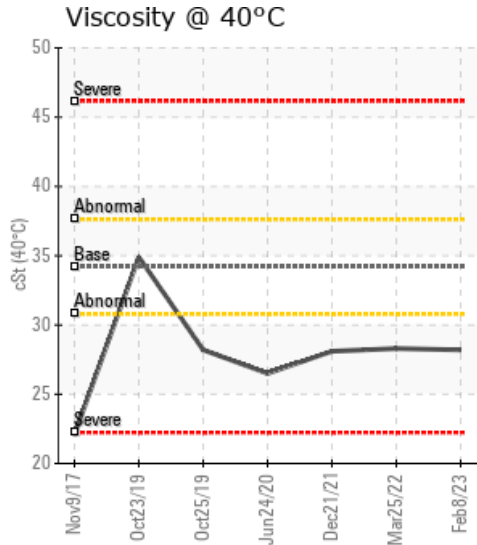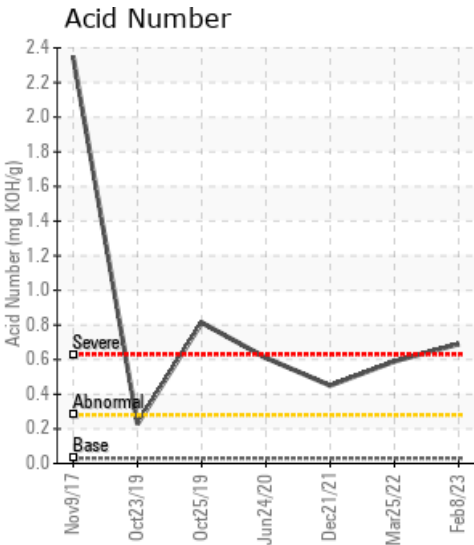

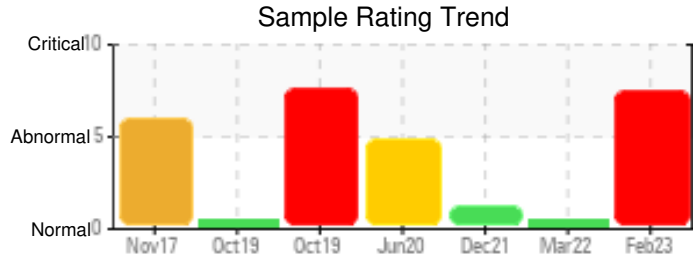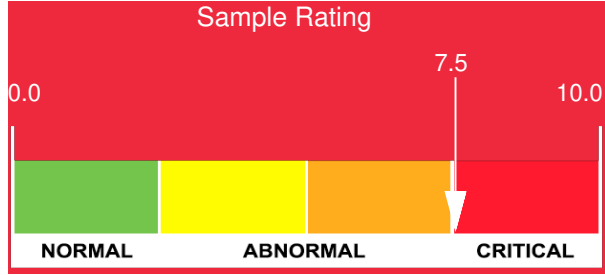

Sample Date	Iron	Chromium	Nickel	Aluminum	Copper	Lead	Tin	Cadmium	Silver	Vanadium	Silicon	Sodium	Potassium	Titanium	Molybdenum	Antimony	Manganese	Lithium	Boron	Magnesium	Calcium	Barium	Phosphorus	Zinc	
02/08/23	28	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	3
03/25/22	45	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	2	0	0	0	4
12/21/21	25	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	0	1	0	0	0	2
06/24/20	144	0	0	0	0	0	0	0	0	0	0	2	0	0	0	0	0	0	0	0	6	3	1	16	
10/25/19	169	0	0	0	0	0	0	0	0	0	0	6	0	0	0	0	1	0	0	0	12	6	4	42	
Baseline Data			0	0						0			0	0					0				0		

Elemental analysis results (above) in parts per million (ppm). [10,000 ppm = 1.0%]

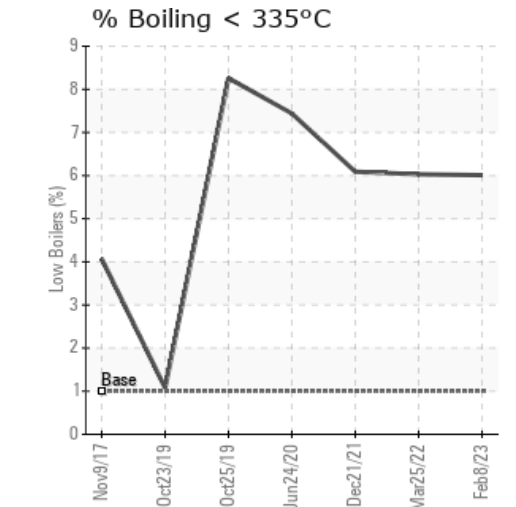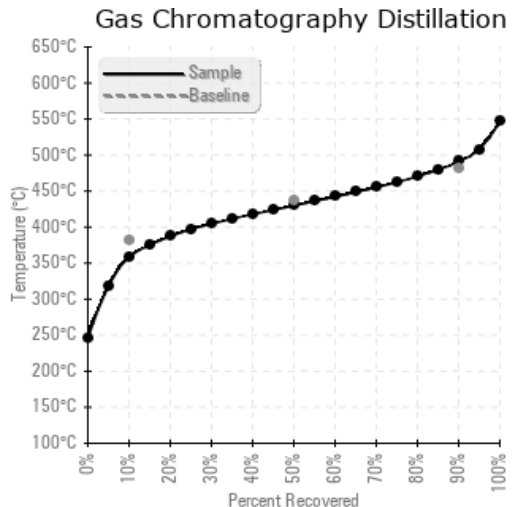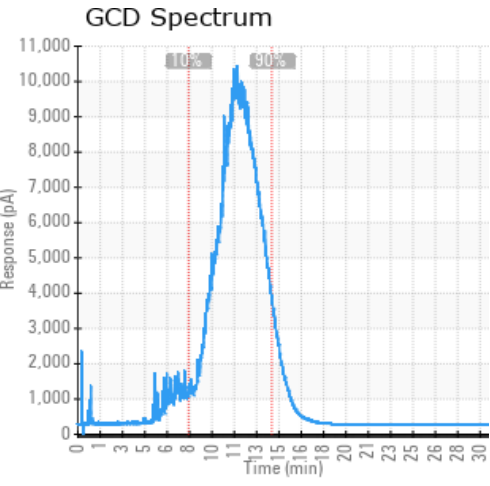

Historical Comments	
03/25/22	The fluid viscosity, boiling points and insolubles are all within specification. There is a slight decrease in the flash point due to some low boilers (GCD % < 335 C) which are low viscosity components due to degradation in the system. Venting of the low boilers is an option if they continue to increase. Fluid is acceptable for continued usage resample in 6-12 months.
12/21/21	The fluid parameters are all in specification except for the high acid number I suggest resampling in 6 months to monitor the acid number if it continues to increase look to sweeten the system with new heat transfer fluid. Acid Number (AN) is abnormally high.
06/24/20	acceptable for continued service - sample in 1-2 months to monitor total acid number and low boilers - operating temperature of the system is 325 F Pentane Insolubles levels are abnormally high. Acid Number (AN) is abnormally high. (GCD) % < 335°C is marginally high. (GCD) 10% Distillation Point is marginally low.
10/25/19	Fluid shows signs of degradation - acid number is high the pentane insoluble are high and there are low boilers in the system that can cause pump cavitation if not removed. There also seems to be contamination of the heat transfer system with either hydraulic or engine oil due to the zinc contamination. Recommend venting the system to remove low boilers for this fluid now and consider scheduling a system changeout - drain, clean and recharge of the system Pentane Insolubles levels are abnormally high. Zinc ppm levels are severely high. Acid Number (AN) is abnormally high. (GCD) 90% Distillation Point is abnormally low. (GCD) % < 335°C is marginally high. (GCD) 10% Distillation Point is marginally low. (GCD) 50% Distillation Point is marginally low.

Petro-Canada makes no representation or warranty of any kind, either express or implied, as to the accuracy or completeness of the analysis and assumes no responsibility and shall have no liability whatsoever with respect to such analysis, or a party's use of it. Petro-Canada is a division of HollyFrontier Corporation.