LIEBHERR
CONSTRUCTION EQUIPMENT

LIEBHERR L580 52139-1414 - Hydraulic System

Sample No: LH0268676

Oil Type: LIEBHERR HYDRAULIC HVI

LIEBHERR EQUIPMENT SOURCE
8200 FAYETTEVILLE ROAD
RALEIGH, NC
US 27603
Contact: TAYLOR BLALOCK
taylor.blalock@liebherr.com
T: (757)718-0491
F: (919)329-0084

SAMPLE INFORMATION

Sample Number		**LH0268676**	---	---	---
Sample Date		**07 Mar 2024**	---	---	---
Machine Hours		**3560**	---	---	---
Oil Hours		**1000**	---	---	---
Oil Changed		**N/A**	---	---	---
Sample Status		**ABNORMAL**	---	---	---

OIL CONDITION

Visc @ 40°C	cSt	**42.6**	---	---	---
Acid Number (AN)	mg KOH/g	**0.78**	---	---	---

CONTAMINATION

Water	%	**NEG**	---	---	---
Particles >4µm		**12993**	---	---	---
Particles >6µm		**2617**	---	---	---
Particles >14µm		**203**	---	---	---
ISO 4406:1999 (c)		**21/19/15**	---	---	---
Silicon	ppm	**2**	---	---	---
Sodium	ppm	**2**	---	---	---
Potassium	ppm	**1**	---	---	---

WEAR METALS

Iron	ppm	**51**	---	---	---
Copper	ppm	**7**	---	---	---
Lead	ppm	**8**	---	---	---
Tin	ppm	**<1**	---	---	---
Aluminum	ppm	**<1**	---	---	---
Chromium	ppm	**8**	---	---	---
Molybdenum	ppm	**0**	---	---	---
Nickel	ppm	**0**	---	---	---
Titanium	ppm	**0**	---	---	---
Silver	ppm	**0**	---	---	---
Manganese	ppm	**<1**	---	---	---
Vanadium	ppm	**0**	---	---	---

ADDITIVES

Calcium	ppm	**913**	---	---	---
Magnesium	ppm	**8**	---	---	---
Zinc	ppm	**555**	---	---	---
Phosphorus	ppm	**434**	---	---	---
Barium	ppm	**0**	---	---	---
Boron	ppm	**0**	---	---	---

Diagnosis

No corrective action is recommended at this time. We recommend an early resample to monitor this condition.The iron level is abnormal. All other component wear rates are normal. There is no indication of any contamination in the oil. The amount and size of particulates present in the system are acceptable. The AN level is acceptable for this fluid. The condition of the oil is suitable for further service.

Depot: LIEBHERRNC
Unique No: 10917019
Signed: Jonathan Hester
Report Date: 12 Mar 2024

LIEBHERR
CONSTRUCTION EQUIPMENT

GRAPHS

Ferrous Alloys

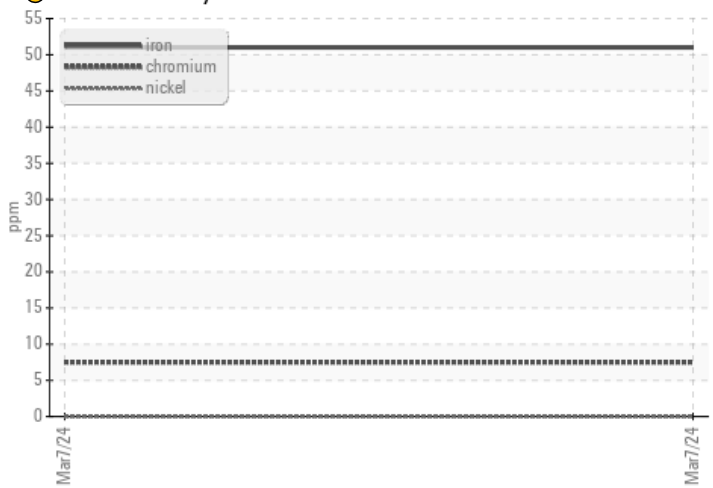

Non-ferrous Metals

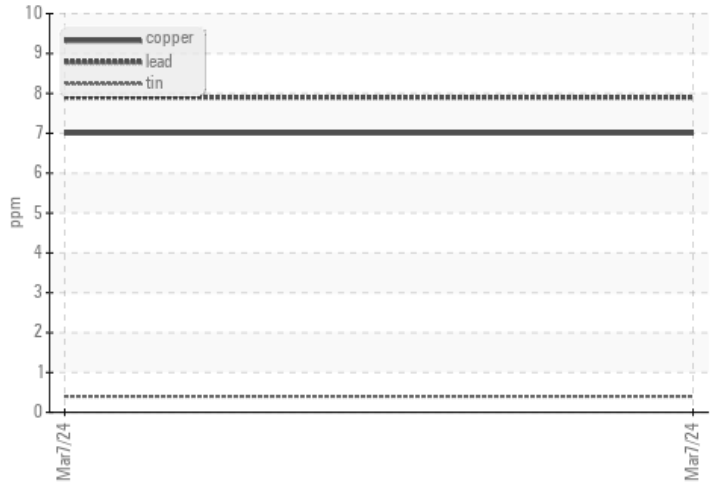

Viscosity @ 40°C

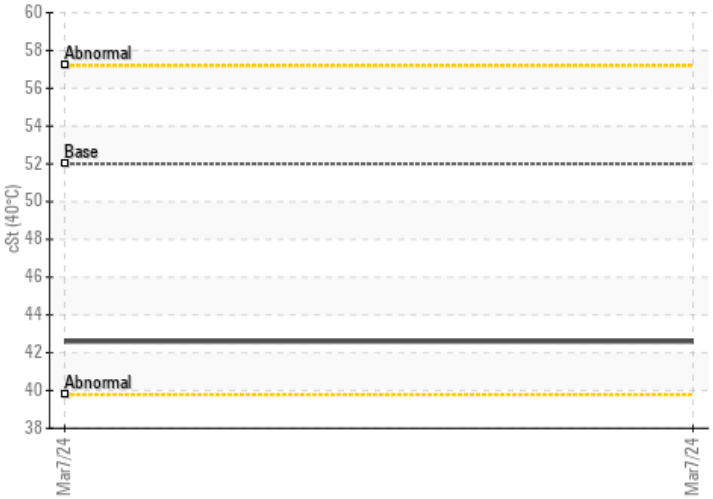

Particle Count

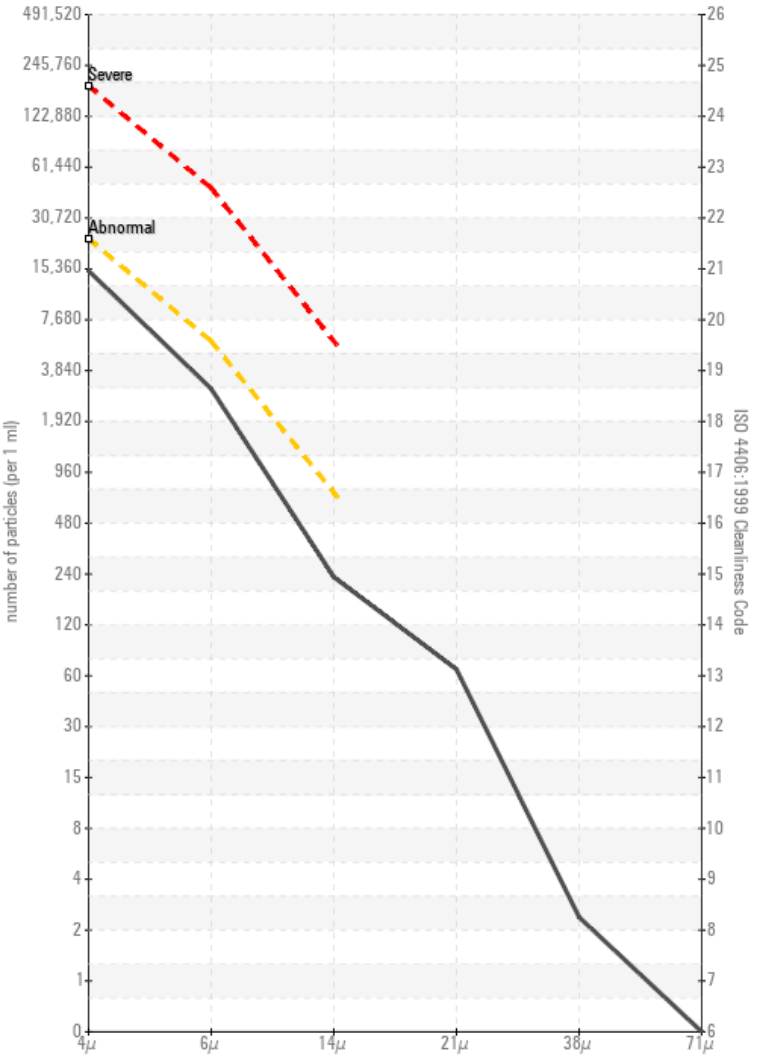

Acid Number