


Machine Id
6019
Component
Rear Diesel Engine
Fluid
PETRO CANADA DURON HP 15W40 (18 LTR)

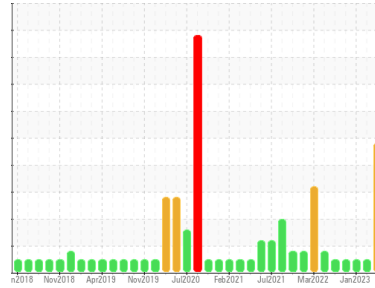

DIAGNOSIS

Recommendation

Nous vous recommandons de vérifier le filtre à air, le système d'induction d'air et tout endroit où la saleté peut entrer dans le composant. Nous avons pris note que l'huile a été vidangée et le filtre remplacé au moment de l'échantillonnage. Nous vous recommandons d'échantillonner de nouveau dès que possible afin de contrôler la situation.

Wear

Les taux d'usure de tous les composants sont normaux.

Contamination

Concentration élevée de saleté dans l'huile.

Fluid Condition

Le résultat pour le BN indique que la réserve d'alcalinité est acceptable pour l'huile. l'huile ne peut plus être utilisée en raison de la présence de contaminants.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		PC0073583	PC0074641	PC0063229
Sample Date	Client Info		29 Jun 2023	09 Mar 2023	09 Jan 2023
Machine Age	kms	Client Info	0	0	0
Oil Age	kms	Client Info	11516	7024	6893
Oil Changed	Client Info		Changed	Changed	Changed
Sample Status			SEVERE	NORMAL	NORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>3.0	<1.0	<1.0	<1.0

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m) >130	95	30	17
Chromium	ppm	ASTM D5185(m) >10	6	<1	<1
Nickel	ppm	ASTM D5185(m) >4	<1	<1	<1
Titanium	ppm	ASTM D5185(m) >2	<1	<1	<1
Silver	ppm	ASTM D5185(m) >2	0	0	0
Aluminum	ppm	ASTM D5185(m) >20	10	7	3
Lead	ppm	ASTM D5185(m) >20	1	0	0
Copper	ppm	ASTM D5185(m) >125	50	<1	<1
Tin	ppm	ASTM D5185(m) >4	<1	0	0
Antimony	ppm	ASTM D5185(m)	0	<1	<1
Vanadium	ppm	ASTM D5185(m)	0	0	0
Beryllium	ppm	ASTM D5185(m)	0	0	0
Cadmium	ppm	ASTM D5185(m)	0	0	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m) 0	2	1	2
Barium	ppm	ASTM D5185(m) 0	0	0	0
Molybdenum	ppm	ASTM D5185(m) 60	58	63	60
Manganese	ppm	ASTM D5185(m) 0	2	<1	<1
Magnesium	ppm	ASTM D5185(m) 1010	955	1022	979
Calcium	ppm	ASTM D5185(m) 1070	1048	1160	1087
Phosphorus	ppm	ASTM D5185(m) 1150	1016	1100	1064
Zinc	ppm	ASTM D5185(m) 1270	1200	1248	1202
Sulfur	ppm	ASTM D5185(m) 2060	2305	2521	2566
Lithium	ppm	ASTM D5185(m)	<1	<1	<1


CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m) >25	85	5	4
Sodium	ppm	ASTM D5185(m)	3	3	2
Potassium	ppm	ASTM D5185(m) >20	7	0	0
Glycol	%	ASTM D7922*	0.0	NEG	NEG

INFRA-RED

	method	limit/base	current	history1	history2
Soot %	%	ASTM D7844* >6	1.8	0.3	0.1
Nitration	Abs/cm	ASTM D7624* >20	10.9	6.5	6.1
Sulfation	Abs./1mm	ASTM D7415* >30	23.6	18.9	17.9

OIL ANALYSIS REPORT












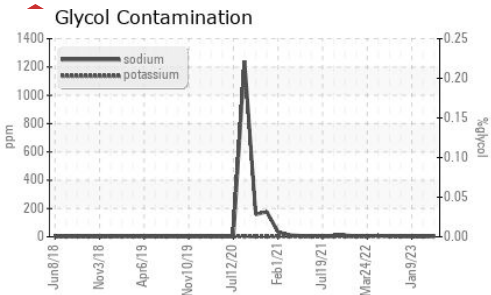


FLUID DEGRADATION		method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	ASTM D7414*	>25	18.0	10.8	11.2
Base Number (BN)	mg KOH/g	ASTM D2896*	9.8	8.10	8.29	8.85

VISUAL		method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	118.2	108	107	106
Visc @ 100°C	cSt	ASTM D7279(m)	15.6	14.6	14.4	14.6
Viscosity Index (VI)	Scale	ASTM D2270*	139	139	137	141

GRAPHS

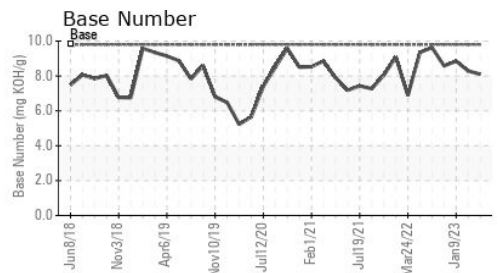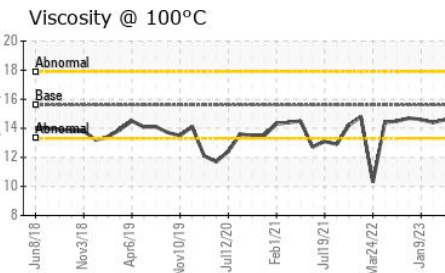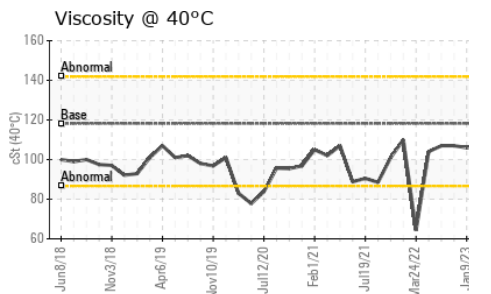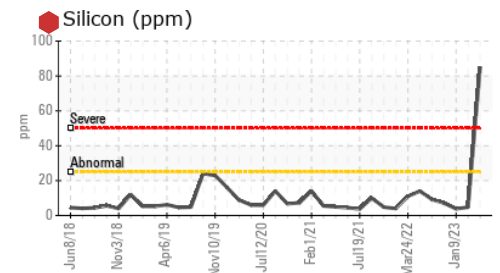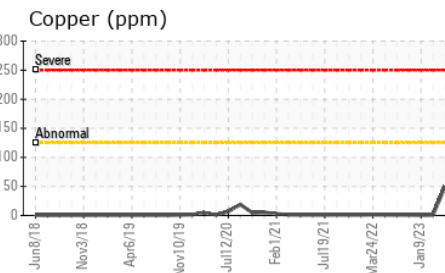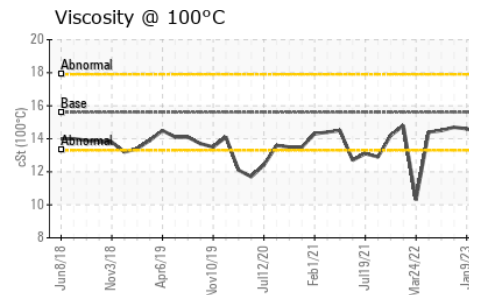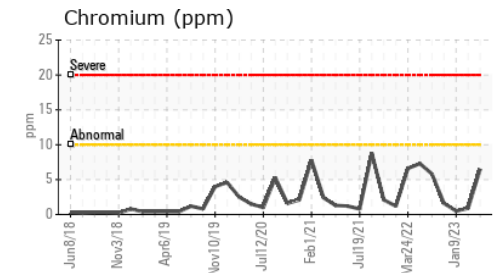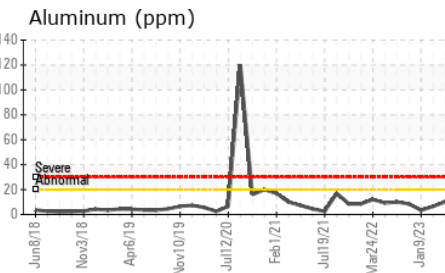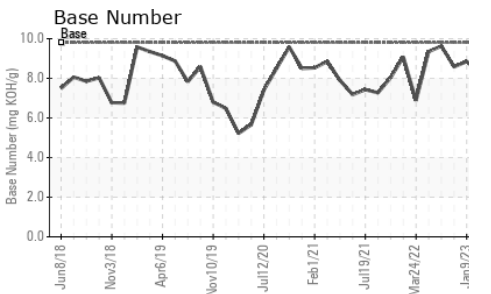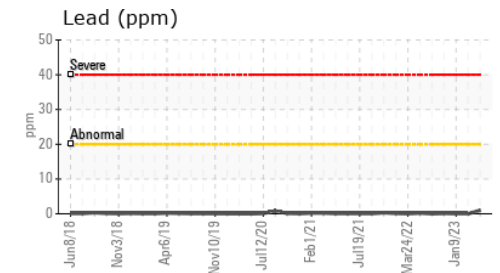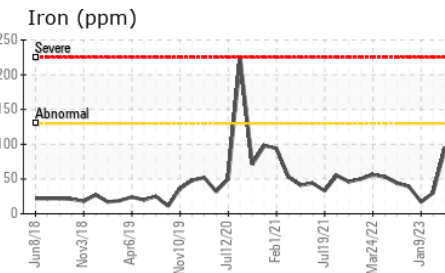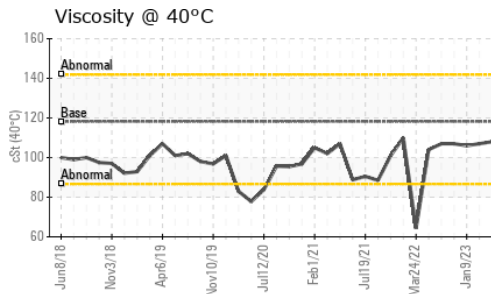

ISO 17025:2017
Accredited
Laboratory

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : PC0073583 **Received** : 18 Jul 2023
Lab Number : **02570542** **Diagnosed** : 19 Jul 2023
Unique Number : 5607588 **Diagnostician** : Kevin Marson
Test Package : MOB 2 (Additional Tests: Glycol, KV40, VI)

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.

TRANSDEV ST-JEAN
 720 TROTTER
 ST-JEAN-SUR-RICHELIEU, QC
 CA J3B 8T2
 Contact: Eric Breton
 eric.breton@transdev.com

T:
F: