




OIL ANALYSIS REPORT

Sample Rating Trend

COOL CHEMICALS



Machine Id
801145
Component
Natural Gas Engine
Fluid
PETRO CANADA DURON GEO LD 15W40 (--- GAL)

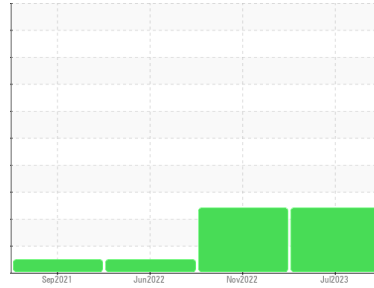

DIAGNOSIS

Recommendation

Check for low coolant level. The oil change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

Contamination

Water treatment chemicals present, indicating slow coolant leak. Test for glycol is negative.

Fluid Condition

The condition of the oil is acceptable for the time in service (see recommendation).

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	GFL0084168	GFL0057442	GFL0050538
Sample Date	Client Info	15 Jul 2023	13 Nov 2022	10 Jun 2022
Machine Age	hrs	129897	12594	0
Oil Age	hrs	1200	600	1200
Oil Changed	Client Info	Changed	Changed	Changed
Sample Status		ABNORMAL	ABNORMAL	NORMAL

WEAR METALS

method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185(m) >50	15	12	20
Chromium	ppm	ASTM D5185(m) >4	1	<1	1
Nickel	ppm	ASTM D5185(m) >2	<1	<1	<1
Titanium	ppm	ASTM D5185(m)	0	<1	<1
Silver	ppm	ASTM D5185(m) >3	0	0	0
Aluminum	ppm	ASTM D5185(m) >9	2	2	2
Lead	ppm	ASTM D5185(m) >30	4	3	7
Copper	ppm	ASTM D5185(m) >35	10	47	5
Tin	ppm	ASTM D5185(m) >4	0	<1	<1
Antimony	ppm	ASTM D5185(m)	0	0	0
Vanadium	ppm	ASTM D5185(m)	0	0	0
Beryllium	ppm	ASTM D5185(m)	0	0	0
Cadmium	ppm	ASTM D5185(m)	0	0	0

ADDITIVES

method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185(m) 50	6	6	6
Barium	ppm	ASTM D5185(m) 5	0	0	0
Molybdenum	ppm	ASTM D5185(m) 50	64	66	55
Manganese	ppm	ASTM D5185(m) 0	<1	<1	<1
Magnesium	ppm	ASTM D5185(m) 560	538	491	519
Calcium	ppm	ASTM D5185(m) 1510	1509	1499	1583
Phosphorus	ppm	ASTM D5185(m) 780	693	656	689
Zinc	ppm	ASTM D5185(m) 870	881	855	908
Sulfur	ppm	ASTM D5185(m) 2040	1965	2005	2092
Lithium	ppm	ASTM D5185(m)	<1	<1	<1

CONTAMINANTS

method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185(m) >+100	12	17	6
Sodium	ppm	ASTM D5185(m)	▲ 176	▲ 180	21
Potassium	ppm	ASTM D5185(m) >20	▲ 227	▲ 278	41
Glycol	%	ASTM D7922*	0.0	0.0	0.0

INFRA-RED



method	limit/base	current	history1	history2	
Soot %	%	ASTM D7844*	0	0	0
Nitration	Abs/cm	ASTM D7624*	>20	11.4	12.6
Sulfation	Abs/.1mm	ASTM D7415*	>30	22.4	27.2

FLUID DEGRADATION

method	limit/base	current	history1	history2	
Oxidation	Abs/.1mm	ASTM D7414*	>25	18.8	20.0











OIL ANALYSIS REPORT

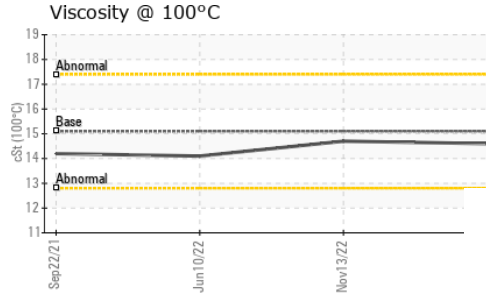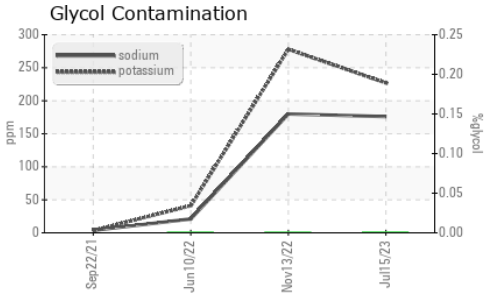

VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	---
Yellow Metal	scalar	Visual*	NONE	NONE	---
Precipitate	scalar	Visual*	NONE	NONE	---
Silt	scalar	Visual*	NONE	NONE	---
Debris	scalar	Visual*	NONE	VLITE	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---
Appearance	scalar	Visual*	NORML	NORML	---
Odor	scalar	Visual*	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.1	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D7279(m)	15.1	14.6	14.7

GRAPHS

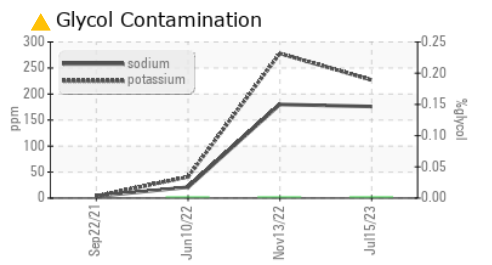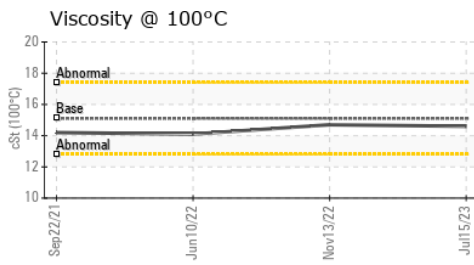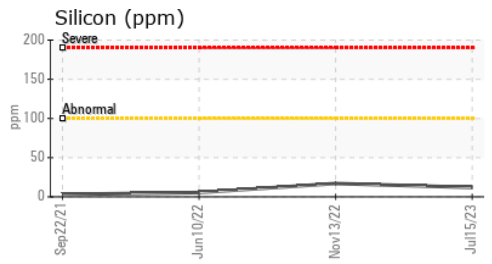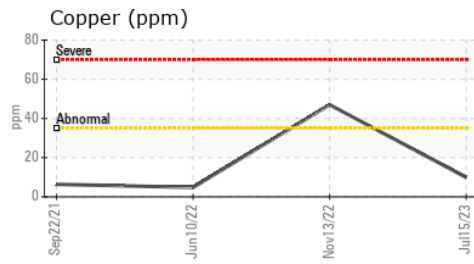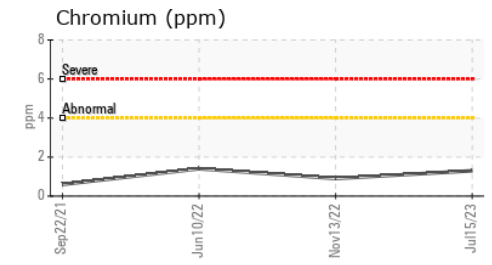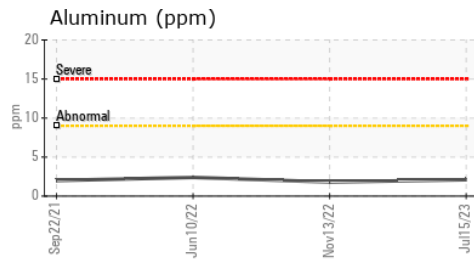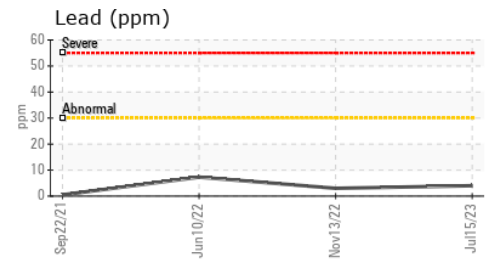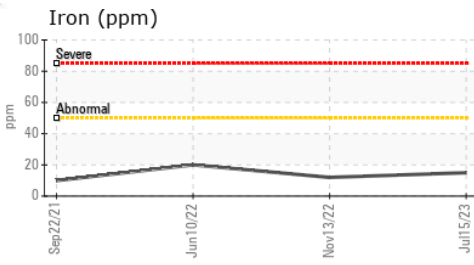

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 GFL Environmental - 574 - Vancouver Fleet
Sample No. : GFL0084168 **Received** : 02 Aug 2023
Lab Number : 02573640 **Diagnosed** : 03 Aug 2023
Unique Number : 5618691 **Diagnostician** : Kevin Marson
Test Package : MOB 1 (Additional Tests: Glycol, Visual)

70 Golden Drive,
 Coquitlam, BC
 CA V3K 6B5
 Contact: Allison Adams
 aadams@gflenv.com
 T: (604)529-4023
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.