




# OIL ANALYSIS REPORT

Sample Rating Trend

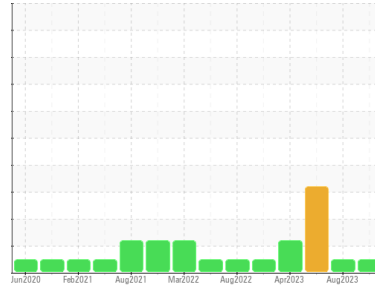

**NORMAL**



Machine Id  
**727003**  
Component  
**Diesel Engine**  
Fluid  
**PETRO CANADA DURON SHP 15W40 (--- GAL)**

## DIAGNOSIS

### Recommendation

Confirm the source of the lubricant being utilized for top-up/fill. Resample at the next service interval to monitor.

### Wear

All component wear rates are normal.

### Contamination

There is no indication of any contamination in the oil.

### Fluid Condition

Additive levels indicate the addition of a different brand, or type of oil. The condition of the oil is acceptable for the time in service.

## SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	<b>GFL0090851</b>	GFL0090867	GFL0082546
Sample Date	Client Info	<b>22 Aug 2023</b>	02 Aug 2023	11 May 2023
Machine Age	hrs	<b>37451</b>	0	36831
Oil Age	hrs	<b>0</b>	38853	0
Oil Changed	Client Info	<b>N/A</b>	Changed	N/A
Sample Status		<b>NORMAL</b>	NORMAL	ABNORMAL

## CONTAMINATION

method	limit/base	current	history1	history2
Fuel	WC Method >3.0	<b>&lt;1.0</b>	<1.0	▲ 2.7
Glycol	WC Method	<b>NEG</b>	NEG	NEG

## WEAR METALS

method	limit/base	current	history1	history2
Iron	ppm ASTM D5185(m) >120	<b>12</b>	13	4
Chromium	ppm ASTM D5185(m) >20	<b>&lt;1</b>	<1	0
Nickel	ppm ASTM D5185(m) >5	<b>0</b>	0	<1
Titanium	ppm ASTM D5185(m) >2	<b>0</b>	0	<1
Silver	ppm ASTM D5185(m) >2	<b>0</b>	0	0
Aluminum	ppm ASTM D5185(m) >20	<b>&lt;1</b>	1	<1
Lead	ppm ASTM D5185(m) >40	<b>&lt;1</b>	3	<1
Copper	ppm ASTM D5185(m) >330	<b>5</b>	4	2
Tin	ppm ASTM D5185(m) >15	<b>0</b>	0	0
Antimony	ppm ASTM D5185(m)	<b>0</b>	0	<1
Vanadium	ppm ASTM D5185(m)	<b>0</b>	0	0
Beryllium	ppm ASTM D5185(m)	<b>0</b>	0	0
Cadmium	ppm ASTM D5185(m)	<b>0</b>	0	0

## ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185(m) 0	<b>72</b>	4	▲ 50
Barium	ppm ASTM D5185(m) 0	<b>0</b>	0	0
Molybdenum	ppm ASTM D5185(m) 60	<b>11</b>	52	38
Manganese	ppm ASTM D5185(m) 0	<b>&lt;1</b>	<1	<1
Magnesium	ppm ASTM D5185(m) 1010	<b>119</b>	856	▲ 473
Calcium	ppm ASTM D5185(m) 1070	<b>1909</b>	1004	▲ 1615
Phosphorus	ppm ASTM D5185(m) 1150	<b>943</b>	956	▲ 776
Zinc	ppm ASTM D5185(m) 1270	<b>1060</b>	1061	▲ 830
Sulfur	ppm ASTM D5185(m) 2060	<b>2660</b>	2316	2102
Lithium	ppm ASTM D5185(m)	<b>&lt;1</b>	<1	<1

## CONTAMINANTS

method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185(m) >25	<b>2</b>	2	3
Sodium	ppm ASTM D5185(m)	<b>2</b>	1	2
Potassium	ppm ASTM D5185(m) >20	<b>4</b>	<1	0

## INFRA-RED



method	limit/base	current	history1	history2
Soot %	% ASTM D7844* >4	<b>2.9</b>	3.2	0.5
Nitration	Abs/cm ASTM D7624* >20	<b>10.2</b>	10.1	5.2
Sulfation	Abs/.1mm ASTM D7415* >30	<b>26.8</b>	24.9	22.1

## FLUID DEGRADATION

method	limit/base	current	history1	history2
Oxidation	Abs/.1mm ASTM D7414* >25	<b>17.1</b>	15.3	18.0











# OIL ANALYSIS REPORT

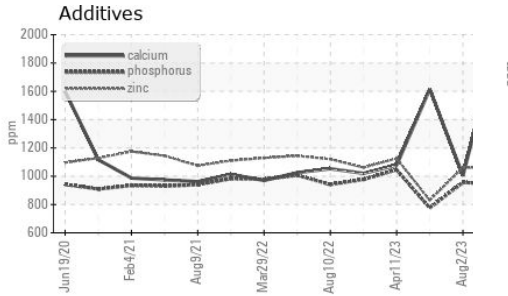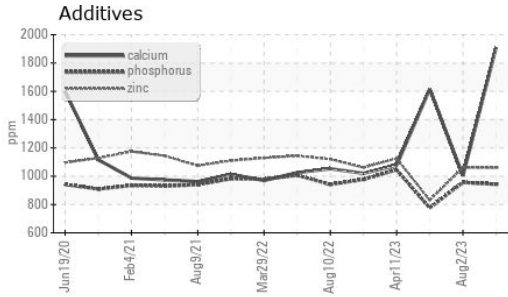

VISUAL	method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D7279(m)	15.4	13.5	13.2 ▲ 11.0

## GRAPHS

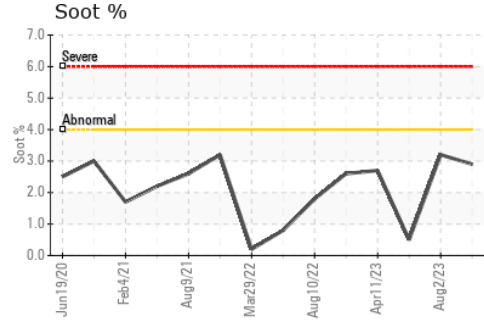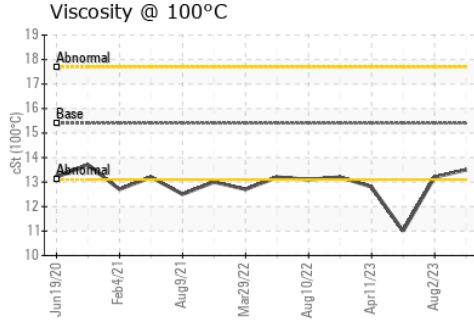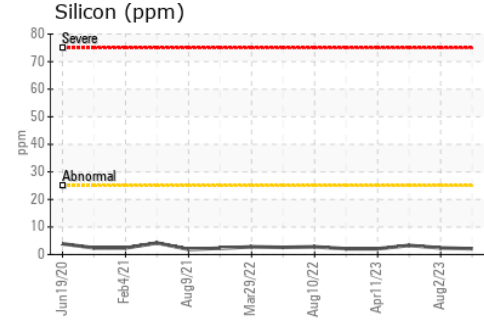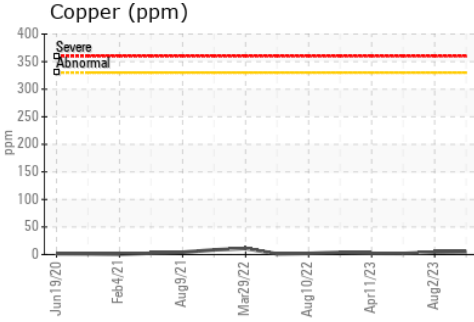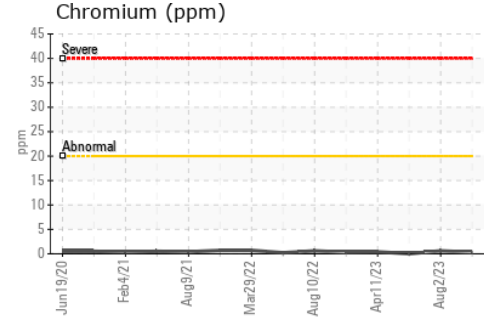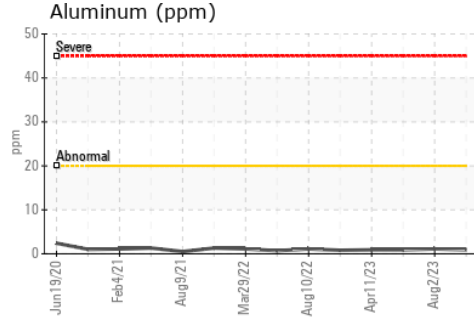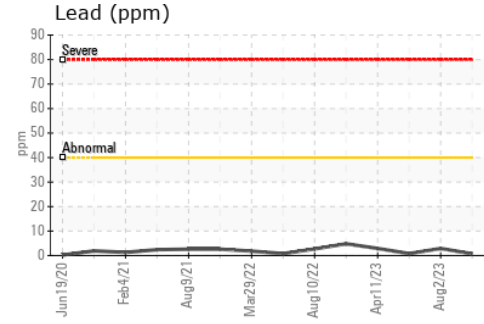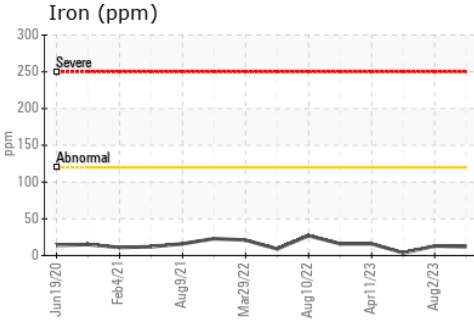

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 **GFL Environmental - 246 - Windsor**  
**Sample No.** : GFL0090851 **Received** : 24 Aug 2023  
**Lab Number** : 02577859 **Diagnosed** : 24 Aug 2023  
**Unique Number** : 5630919 **Diagnostician** : Kevin Marson  
**Test Package** : MOB 1

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.