




Machine Id
NO UNIT PC0048710

Component
Hydraulic System
Fluid
NOT GIVEN (--- GAL)

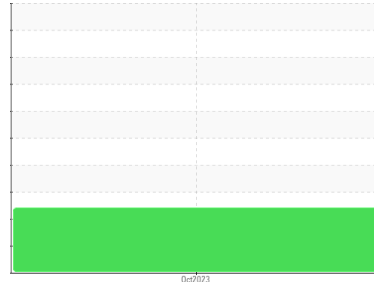

DIAGNOSIS

▲ Recommendation

We advise that you check for the source of water entry. Check seals and/or filters for points of contaminant entry. We recommend that you drain the oil from the component if this has not already been done. We recommend an early resample to monitor this condition. Please specify the component make and model with your next sample. Please specify the brand, type, and viscosity of the oil on your next sample. NOTE: Please provide information regarding reservoir capacity, filter type and micron rating with next sample. Please contact your representative for information regarding the proper sampling kits for your service. NOTE: We recommend using MOB 2 test kits, this testkit includes Particle Count to determine the ISO cleanliness of the fluid.

Wear

All component wear rates are normal.

▲ Contamination

There is a moderate concentration of water present in the oil.

Fluid Condition

The oil is no longer serviceable due to the presence of contaminants.




SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			PC0048710	---	---
Sample Date	Client Info			15 Oct 2023	---	---
Machine Age	hrs	Client Info		0	---	---
Oil Age	hrs	Client Info		0	---	---
Oil Changed	Client Info			N/A	---	---
Sample Status				ABNORMAL	---	---

WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>20	8	---	---
Chromium	ppm	ASTM D5185(m)	>10	<1	---	---
Nickel	ppm	ASTM D5185(m)	>10	0	---	---
Titanium	ppm	ASTM D5185(m)		0	---	---
Silver	ppm	ASTM D5185(m)		<1	---	---
Aluminum	ppm	ASTM D5185(m)	>10	1	---	---
Lead	ppm	ASTM D5185(m)	>10	<1	---	---
Copper	ppm	ASTM D5185(m)	>75	4	---	---
Tin	ppm	ASTM D5185(m)	>10	0	---	---
Antimony	ppm	ASTM D5185(m)		0	---	---
Vanadium	ppm	ASTM D5185(m)		0	---	---
Beryllium	ppm	ASTM D5185(m)		0	---	---
Cadmium	ppm	ASTM D5185(m)		0	---	---

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)		7	---	---
Barium	ppm	ASTM D5185(m)		<1	---	---
Molybdenum	ppm	ASTM D5185(m)		0	---	---
Manganese	ppm	ASTM D5185(m)		0	---	---
Magnesium	ppm	ASTM D5185(m)		1	---	---
Calcium	ppm	ASTM D5185(m)		386	---	---
Phosphorus	ppm	ASTM D5185(m)		416	---	---
Zinc	ppm	ASTM D5185(m)		528	---	---
Sulfur	ppm	ASTM D5185(m)		941	---	---
Lithium	ppm	ASTM D5185(m)		<1	---	---

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	>20	12	---	---
Sodium	ppm	ASTM D5185(m)		2	---	---
Potassium	ppm	ASTM D5185(m)	>20	<1	---	---
Water	%	ASTM D6304*	>0.1	▲ 0.770	---	---
ppm Water	ppm	ASTM D6304*	>1000	▲ 7704.1	---	---

OIL ANALYSIS REPORT





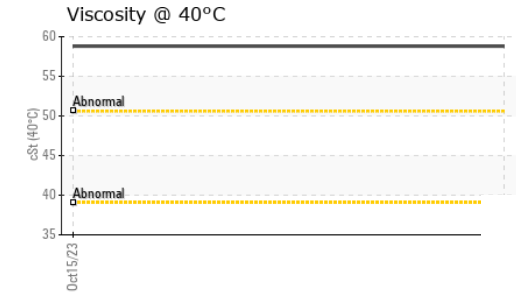
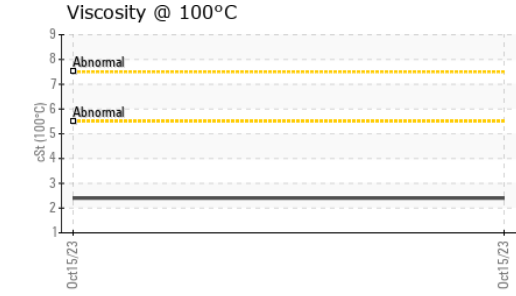
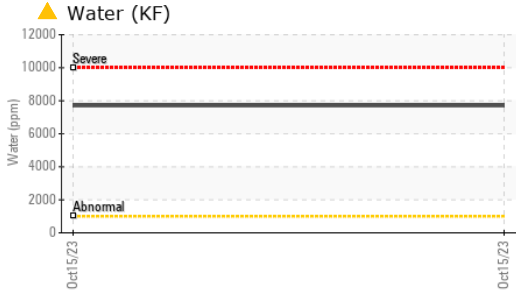


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	---
Yellow Metal	scalar	Visual*	NONE	NONE	---
Precipitate	scalar	Visual*	NONE	NONE	---
Silt	scalar	Visual*	NONE	NONE	---
Debris	scalar	Visual*	NONE	NONE	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---
Appearance	scalar	Visual*	NORML	▲ MILKY	---
Odor	scalar	Visual*	NORML	NORML	---
Emulsified Water	scalar	Visual*	>0.1	▲ 1%	---
Free Water	scalar	Visual*		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	58.8	---	---
Visc @ 100°C	cSt	ASTM D7279(m)	2.4	---	---

SAMPLE IMAGES	method	limit/base	current	history1	history2
Color				no image	no image
Bottom				no image	no image

GRAPHS

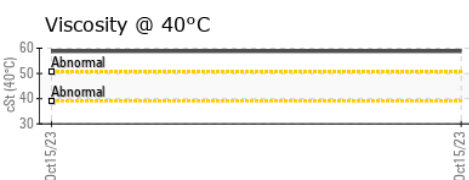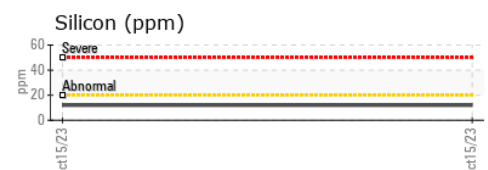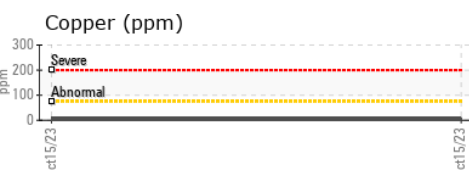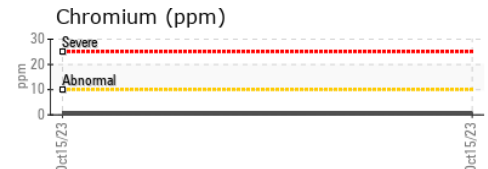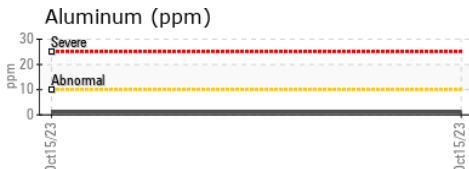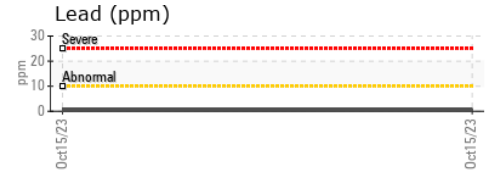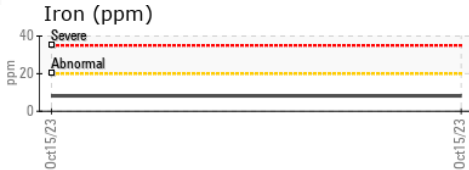

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : PC0048710 **Received** : 16 Oct 2023
Lab Number : 02589344 **Diagnosed** : 17 Oct 2023
Unique Number : 5658410 **Diagnostician** : Kevin Marson
Test Package : MOB 1 (Additional Tests: KF, KV100, VI)

Lakeshore Gold Timmins West
 Timmins, ON
 CA
 Contact: Glenn Thornhill
 gthornhill@ca.panamericansilver.com
 T: (705)269-4344
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.