




OIL ANALYSIS REPORT

Sample Rating Trend

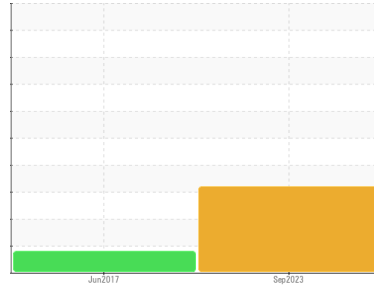

Machine Id
OR132
Component
Diesel Engine
Fluid
SAE 0W40 (--- GAL)

DIAGNOSIS

Recommendation

We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. We recommend that you drain the oil from the component if this has not already been done. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

Iron ppm levels are abnormal. Aluminum ppm levels are noted. Cylinder, crank, or cam shaft wear is indicated.

Contamination

Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. High amount of ingressed dirt has caused abrasive wear to the component.

Fluid Condition

The oil is no longer serviceable as a result of the abnormal and/or severe wear.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	GFL0038130	GFL11261257	---
Sample Date	Client Info	26 Sep 2023	01 Jun 2017	---
Machine Age	hrs	9636	4775	---
Oil Age	hrs	600	310	---
Oil Changed	Client Info	Changed	Changed	---
Sample Status		ABNORMAL	MARGINAL	---

CONTAMINATION

method	limit/base	current	history1	history2
Fuel	WC Method >2.1	<1.0	▲ 3.01	---
Glycol	WC Method	NEG	NEG	---

WEAR METALS

method	limit/base	current	history1	history2
PQ	ASTM D8184* >50	13	---	---
Iron	ppm ASTM D5185(m) >51	▲ 141	30	---
Chromium	ppm ASTM D5185(m) >11	3	1	---
Nickel	ppm ASTM D5185(m) >5	4	0	---
Titanium	ppm ASTM D5185(m)	0	0	---
Silver	ppm ASTM D5185(m) >3	<1	0	---
Aluminum	ppm ASTM D5185(m) >31	▲ 6	0	---
Lead	ppm ASTM D5185(m) >26	<1	0	---
Copper	ppm ASTM D5185(m) >26	6	4	---
Tin	ppm ASTM D5185(m) >4	0	1	---
Antimony	ppm ASTM D5185(m)	0	0	---
Vanadium	ppm ASTM D5185(m)	0	0	---
Beryllium	ppm ASTM D5185(m)	0	0	---
Cadmium	ppm ASTM D5185(m)	0	---	---

ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185(m)	1	3	---
Barium	ppm ASTM D5185(m)	<1	0	---
Molybdenum	ppm ASTM D5185(m)	74	2	---
Manganese	ppm ASTM D5185(m)	<1	---	---
Magnesium	ppm ASTM D5185(m)	1076	7	---
Calcium	ppm ASTM D5185(m)	1190	2460	---
Phosphorus	ppm ASTM D5185(m)	1074	1020	---
Zinc	ppm ASTM D5185(m)	1365	1160	---
Sulfur	ppm ASTM D5185(m)	2251	---	---
Lithium	ppm ASTM D5185(m)	<1	0	---

CONTAMINANTS


method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185(m) >22	▲ 23	5	---
Sodium	ppm ASTM D5185(m) >31	3	4	---
Potassium	ppm ASTM D5185(m) >20	<1	0	---

INFRA-RED

method	limit/base	current	history1	history2
Soot %	% ASTM D7844* >3	2.4	0.19	---
Nitration	Abs/cm ASTM D7624* >20	10.8	---	---
Sulfation	Abs.1mm ASTM D7415* >30	24.1	---	---



OIL ANALYSIS REPORT












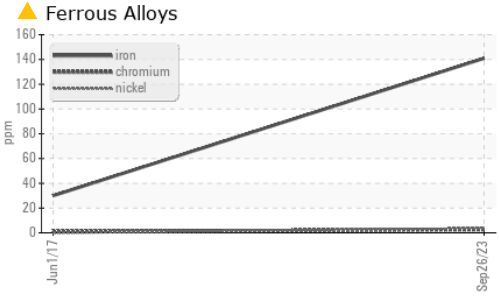


FLUID DEGRADATION	method	limit/base	current	history1	history2
Oxidation	Abs./1mm	ASTM D7414*	>25	18.7	---

VISUAL	method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.21	NEG	---
Free Water	scalar	Visual*		NEG	---

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D7279(m)	14.8	14.3	12.83

GRAPHS

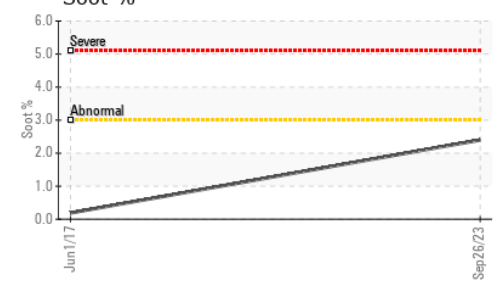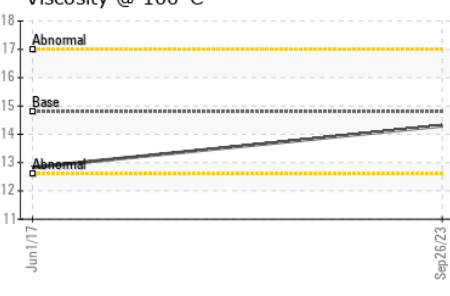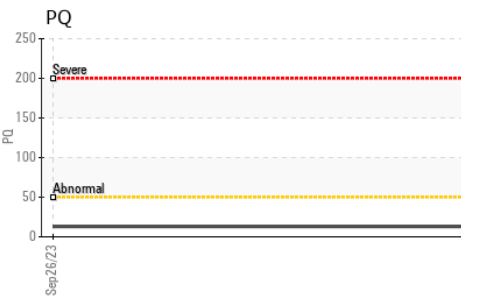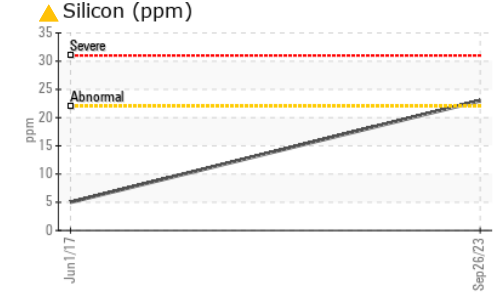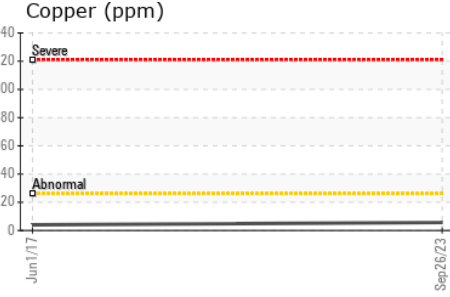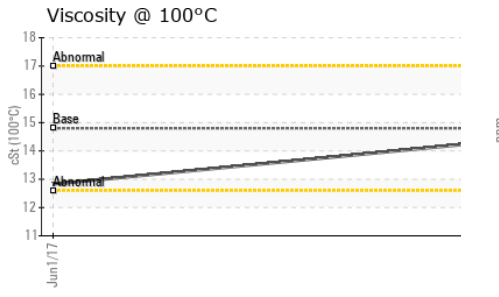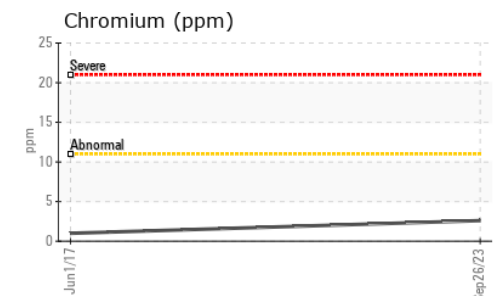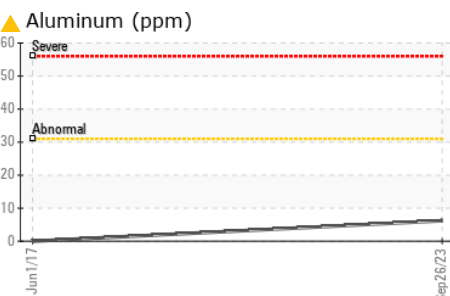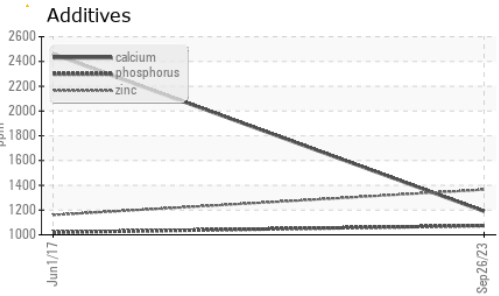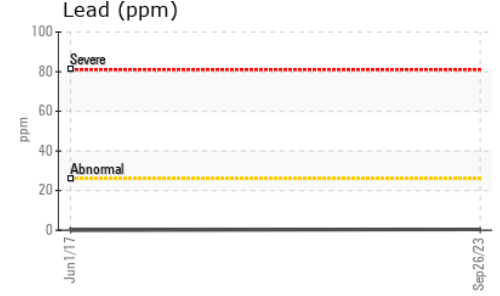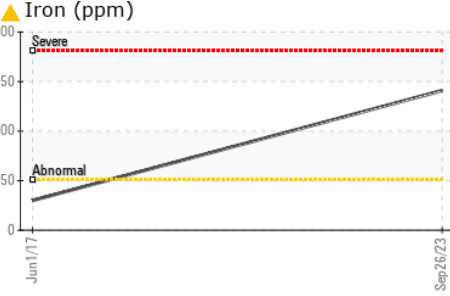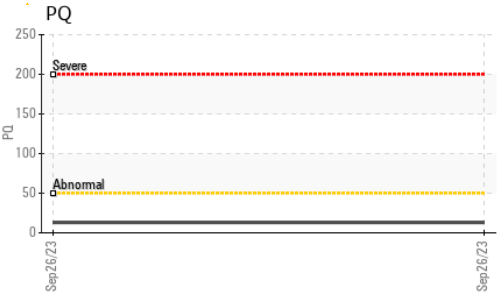

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 **GFL Environmental - 555 - Slave Lake**
Sample No. : GFL0038130 **Received** : 18 Oct 2023 **240 Balsam Rd NE, P.O. 362**
Lab Number : 02589938 **Diagnosed** : 19 Oct 2023 **Slave Lake, AB**
Unique Number : 5659004 **Diagnostician** : Kevin Marson **CA T0G 2A0**
Test Package : MOB 1 (Additional Tests: PQ) **Contact: William Barker**
wbarker@gflenv.com

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.