




OIL ANALYSIS REPORT

Sample Rating Trend

NORMAL

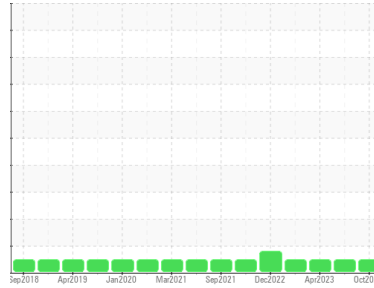

Machine Id
801036
 Component
Diesel Engine
 Fluid
PETRO CANADA DURON SHP 15W40 (19 LTR)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor.

Wear

All component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The condition of the oil is acceptable for the time in service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		GFL0094202	GFL0091040	GFL0077198
Sample Date	Client Info		10 Oct 2023	03 Aug 2023	25 Apr 2023
Machine Age	kms	Client Info	120211	120211	120211
Oil Age	kms	Client Info	0	0	95948
Oil Changed	Client Info		N/A	Changed	Changed
Sample Status			NORMAL	NORMAL	NORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<1.0	<1.0	<1.0

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m) >80	30	35	37
Chromium	ppm	ASTM D5185(m) >5	<1	1	1
Nickel	ppm	ASTM D5185(m) >2	0	<1	<1
Titanium	ppm	ASTM D5185(m)	0	<1	<1
Silver	ppm	ASTM D5185(m) >3	<1	<1	0
Aluminum	ppm	ASTM D5185(m) >30	4	6	5
Lead	ppm	ASTM D5185(m) >30	0	0	0
Copper	ppm	ASTM D5185(m) >150	1	2	2
Tin	ppm	ASTM D5185(m) >5	0	0	<1
Antimony	ppm	ASTM D5185(m)	0	0	<1
Vanadium	ppm	ASTM D5185(m)	0	0	0
Beryllium	ppm	ASTM D5185(m)	0	0	0
Cadmium	ppm	ASTM D5185(m)	0	0	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m) 0	6	8	7
Barium	ppm	ASTM D5185(m) 0	<1	0	0
Molybdenum	ppm	ASTM D5185(m) 60	59	61	62
Manganese	ppm	ASTM D5185(m) 0	0	<1	<1
Magnesium	ppm	ASTM D5185(m) 1010	910	957	942
Calcium	ppm	ASTM D5185(m) 1070	1023	1065	1169
Phosphorus	ppm	ASTM D5185(m) 1150	962	1047	1052
Zinc	ppm	ASTM D5185(m) 1270	1134	1226	1202
Sulfur	ppm	ASTM D5185(m) 2060	2384	2410	2446
Lithium	ppm	ASTM D5185(m)	<1	<1	<1

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m) >20	6	9	6
Sodium	ppm	ASTM D5185(m)	135	25	10
Potassium	ppm	ASTM D5185(m) >20	4	6	5
Glycol	%	ASTM D7922*	0.0	0.0	NEG

INFRA-RED



	method	limit/base	current	history1	history2
Soot %	%	ASTM D7844* >3	0.8	1	0.7
Nitration	Abs/cm	ASTM D7624* >20	10.4	11.0	10.8
Sulfation	Abs/.1mm	ASTM D7415* >30	21.1	23.4	23.2

FLUID DEGRADATION

	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	ASTM D7414* >25	17.2	18.2	19.9











OIL ANALYSIS REPORT

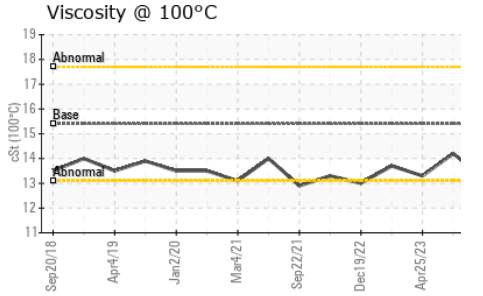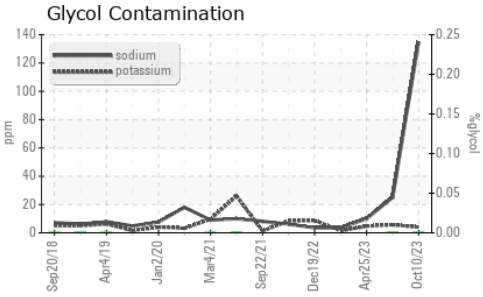

PARAMETER	method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.2	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG

PARAMETER	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D7279(m)	15.4	13.2	14.2

GRAPHS

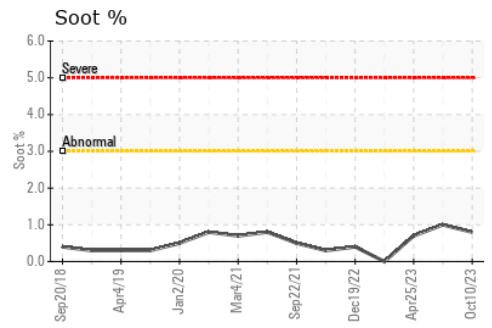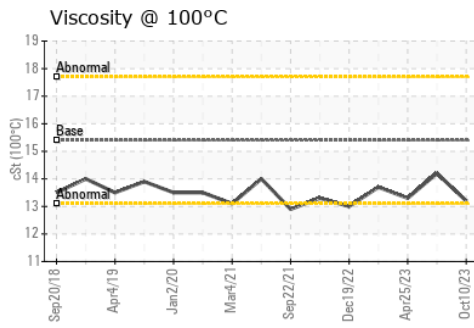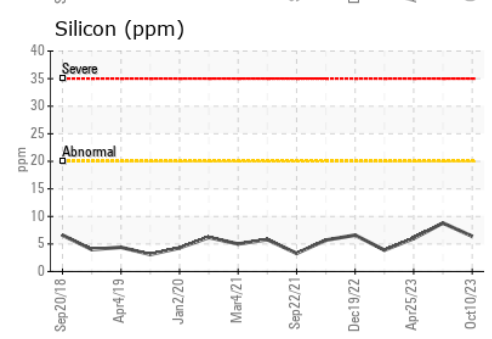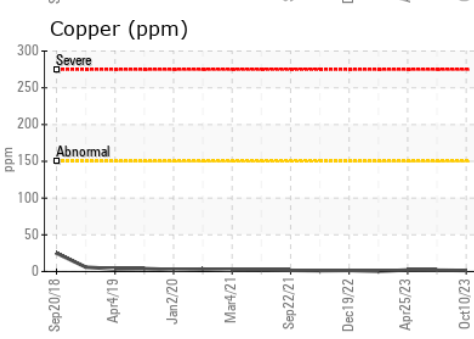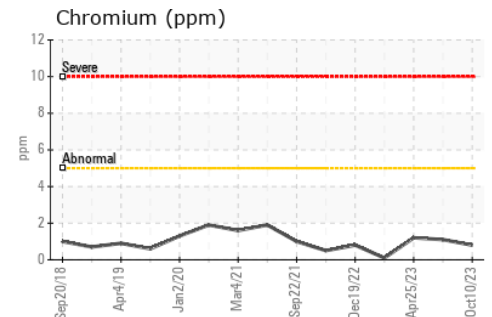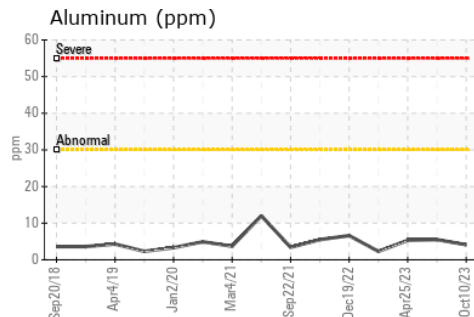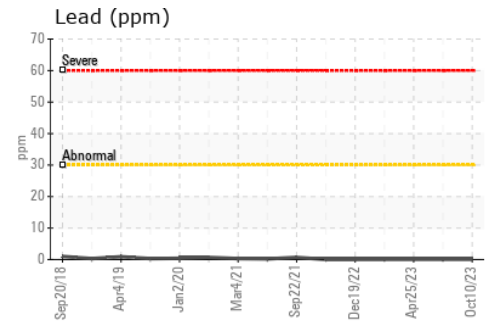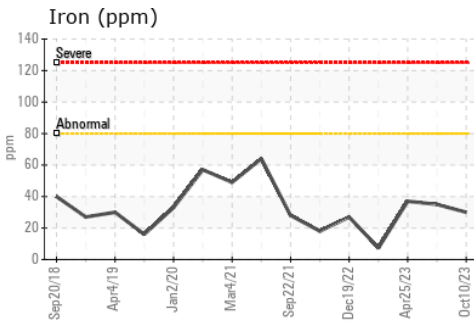

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : GFL0094202
Lab Number : 02591629
Unique Number : 5668708
Test Package : MOB 1 (Additional Tests: Glycol)

GFL Environmental - 217 - Aurora
 14131 BAYVIEW AVE, AURORA YARD
 AURORA, ON
 CA L4G 0K6
 Contact: Mike Havens
 MHavens@gflenv.com
 T:
 F: (905)713-2445

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.