







Machine Id
PRESS #5 (S/N MPR-49611)

Component
Hydraulic System

Fluid
PETRO CANADA HYDREX AW 68 (4000 GAL)

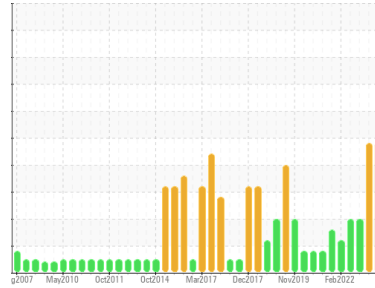

COMPONENT CONDITION SUMMARY

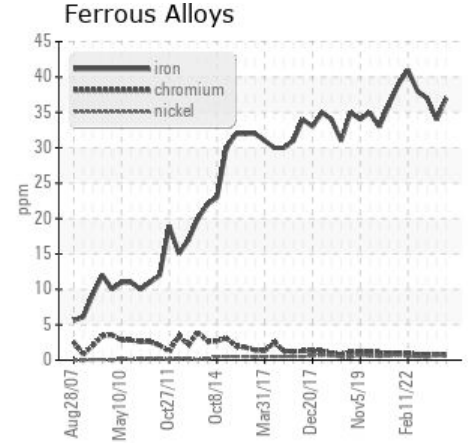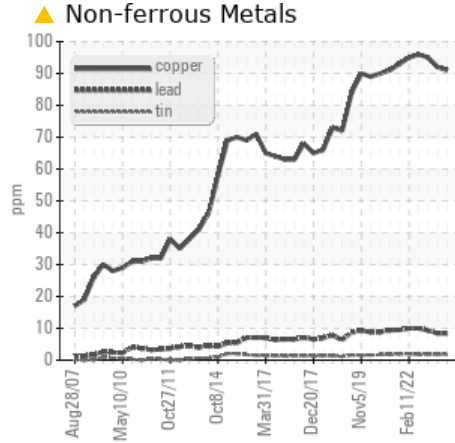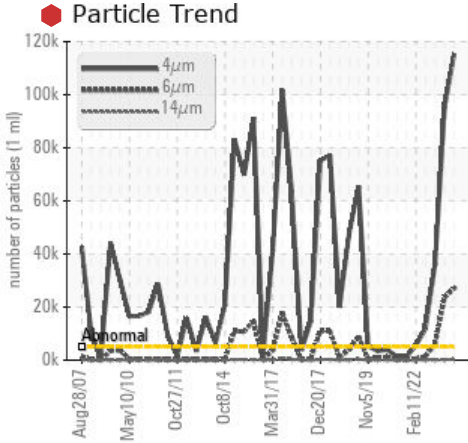

RECOMMENDATION

Check seals and/or filters for points of contaminant entry. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. We recommend you service the filters on this component. Resample in 30-45 days to monitor this situation. Please contact your representative for information regarding the proper sampling kits for your service. NOTE: We recommend using Advanced Oil Monitoring (AOM) kits for this system. The AOM test package includes advanced level testing to determine the suitability of turbine and large industrial compressor oils for continued use.

PROBLEMATIC TEST RESULTS

Sample Status		SEVERE	SEVERE	ABNORMAL
Copper	ppm ASTM D5185(m) >20	▲ 91	▲ 92	▲ 95
Particles >4µm	ASTM D7647 >5000	● 115408	● 95394	▲ 36251
Particles >6µm	ASTM D7647 >1300	● 27014	● 23627	▲ 5993
Particles >14µm	ASTM D7647 >160	▲ 311	▲ 187	115
Oil Cleanliness	ISO 4406 (c) >19/17/14	● 24/22/15	● 24/22/15	▲ 22/20/14

Customer Id: EXTWOO
Sample No.: PC0062180
Lab Number: 02600531
Test Package: IND 2



To manage this report scan the QR code

To discuss the diagnosis or test data:
Kevin Marson +1 (289)291-4644 x4644
Kevin.Marson@wearcheck.com

To change component or sample information:
Gloria Gonzalez +1 (289)291-4643 x4643
gloria.gonzalez@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Filter	---	---	?	We recommend you service the filters on this component.
Resample	---	---	?	Resample in 30-45 days to monitor this situation.
Contact Required	---	---	?	Please contact your representative for information regarding the proper sampling kits for your service.
Alert	---	---	?	NOTE: We recommend using Advanced Oil Monitoring (AOM) kits for this system. The AOM test package includes advanced level testing to determine the suitability of turbine and large industrial compressor oils for continued use.
Check Breathers	---	---	?	The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather.
Check Seals	---	---	?	Check seals and/or filters for points of contaminant entry.

HISTORICAL DIAGNOSIS

ISO



02 Jun 2023 Diag: Kevin Marson

Check seals and/or filters for points of contaminant entry. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. We recommend you service the filters on this component. Resample in 30-45 days to monitor this situation. Please contact your representative for information regarding the proper sampling kits for your service. NOTE: We recommend using Advanced Oil Monitoring (AOM) kits for this system. The AOM test package includes advanced level testing to determine the suitability of turbine and large industrial compressor oils for continued use. Copper ppm levels are noted. All other component wear rates are normal. There is a high amount of silt (particulates < 14 microns in size) present in the oil. The AN level is acceptable for this fluid. The condition of the oil is acceptable for the time in service (unconfirmed). The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

view report



WEAR



02 Nov 2022 Diag: Kevin Marson

We recommend you service the filters on this component. We recommend an early resample to monitor this condition. Please contact your representative for information regarding the proper sampling kits for your service. NOTE: We recommend using Advanced Oil Monitoring (AOM) kits for this system. The AOM test package includes advanced level testing to determine the suitability of turbine and large industrial compressor oils for continued use. this testkit includes Analytical Ferrography which provides a detailed morphological analysis of wear particles present in the fluid. Copper ppm levels are noted. All other component wear rates are normal. Particles >4µm are abnormally high. Particles >6µm and oil cleanliness are abnormally high. The AN level is acceptable for this fluid. The condition of the oil is acceptable for the time in service (unconfirmed). The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

view report



WEAR



22 Jun 2022 Diag: Kevin Marson

We recommend you service the filters on this component. We recommend an early resample to monitor this condition. Please contact your representative for information regarding the proper sampling kits for your service. NOTE: We recommend using Advanced Oil Monitoring (AOM) kits for this system. The AOM test package includes advanced level testing to determine the suitability of turbine and large industrial compressor oils for continued use. Copper ppm levels are noted. All other component wear rates are normal. Particles >4µm and oil cleanliness are abnormally high. Particles >6µm are notably high. The AN level is acceptable for this fluid. The condition of the oil is acceptable for the time in service (unconfirmed). The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

view report






Machine Id
PRESS #5 (S/N MPR-49611)

Component
Hydraulic System

Fluid
PETRO CANADA HYDREX AW 68 (4000 GAL)

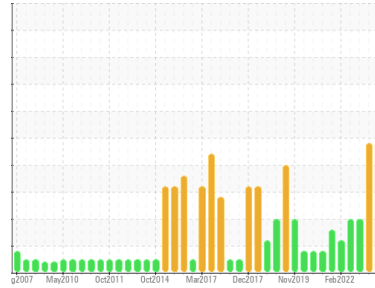

DIAGNOSIS

Recommendation
Check seals and/or filters for points of contaminant entry. The air breather requires service. If unrated, we recommend that you replace with a suitable micron rated and/or desiccant air breather. If rated, we recommend that you service/replace the breather. We recommend you service the filters on this component. Resample in 30-45 days to monitor this situation. Please contact your representative for information regarding the proper sampling kits for your service. NOTE: We recommend using Advanced Oil Monitoring (AOM) kits for this system. The AOM test package includes advanced level testing to determine the suitability of turbine and large industrial compressor oils for continued use.

Wear
Copper ppm levels are noted. All other component wear rates are normal.

Contamination
There is a high amount of silt (particulates < 14 microns in size) present in the oil.

Fluid Condition
The AN level is acceptable for this fluid. The condition of the oil is acceptable for the time in service (unconfirmed). The oil is still serviceable provided that the contaminant(s) can be reduced to acceptable levels.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	PC0062180	PC0076109	PC0062183
Sample Date	Client Info	30 Nov 2023	02 Jun 2023	02 Nov 2022
Machine Age	yrs	0	0	0
Oil Age	yrs	0	0	0
Oil Changed	Client Info	N/A	N/A	N/A
Sample Status		SEVERE	SEVERE	ABNORMAL

CONTAMINATION

method	limit/base	current	history1	history2
Water	WC Method >0.05	NEG	NEG	NEG

WEAR METALS

method	limit/base	current	history1	history2
PQ	ASTM D8184*	0	0	0
Iron	ppm ASTM D5185(m) >20	37	34	37
Chromium	ppm ASTM D5185(m) >20	<1	<1	<1
Nickel	ppm ASTM D5185(m) >20	<1	<1	<1
Titanium	ppm ASTM D5185(m)	0	0	0
Silver	ppm ASTM D5185(m)	<1	0	0
Aluminum	ppm ASTM D5185(m) >20	8	8	9
Lead	ppm ASTM D5185(m) >20	8	8	9
Copper	ppm ASTM D5185(m) >20	91	92	95
Tin	ppm ASTM D5185(m) >20	2	2	2
Antimony	ppm ASTM D5185(m)	0	<1	<1
Vanadium	ppm ASTM D5185(m)	0	0	0
Beryllium	ppm ASTM D5185(m)	0	0	0
Cadmium	ppm ASTM D5185(m)	0	0	0






ADDITIVES

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185(m) 0	<1	<1	<1
Barium	ppm ASTM D5185(m) 0	<1	<1	<1
Molybdenum	ppm ASTM D5185(m) 0	0	0	0
Manganese	ppm ASTM D5185(m) 0	<1	1	1
Magnesium	ppm ASTM D5185(m) 0	69	66	61
Calcium	ppm ASTM D5185(m) 50	107	108	106
Phosphorus	ppm ASTM D5185(m) 330	575	598	596
Zinc	ppm ASTM D5185(m) 430	558	534	533
Sulfur	ppm ASTM D5185(m) 760	1868	1834	1937
Lithium	ppm ASTM D5185(m)	<1	<1	<1

CONTAMINANTS

method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185(m) >15	3	2	2
Sodium	ppm ASTM D5185(m)	4	4	4
Potassium	ppm ASTM D5185(m) >20	<1	<1	<1

OIL ANALYSIS REPORT

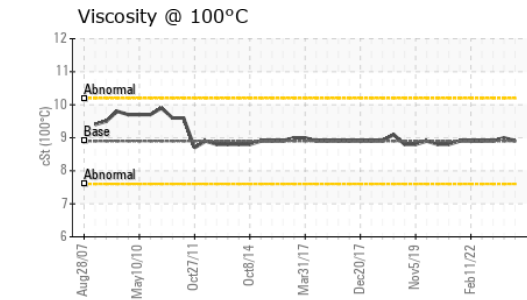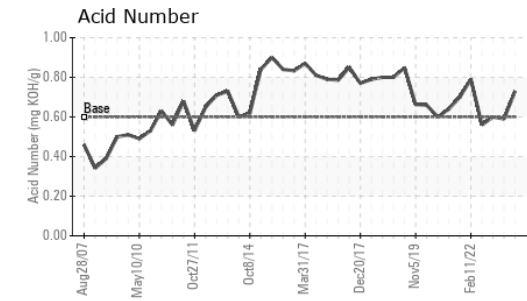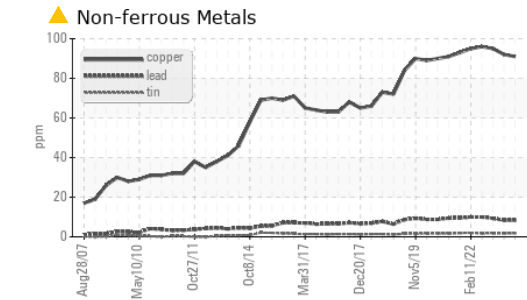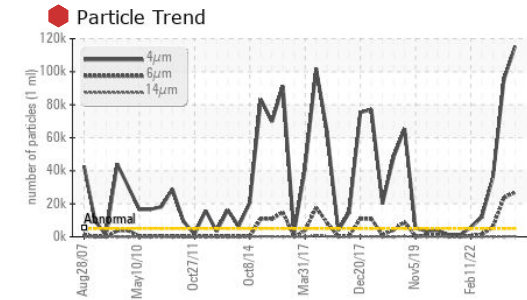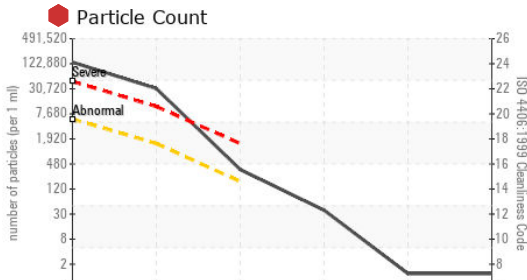

ISO 17025:2017
Accredited
Laboratory

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : PC0062180 **Received** : 04 Dec 2023
Lab Number : 02600531 **Diagnosed** : 05 Dec 2023
Unique Number : 5685611 **Diagnostician** : Kevin Marson
Test Package : IND 2 (Additional Tests: KV100, PQ, VI)

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.


FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm	ASTM D7647	>5000	115408	95394	36251	
Particles >6µm	ASTM D7647	>1300	27014	23627	5993	
Particles >14µm	ASTM D7647	>160	311	187	115	
Particles >21µm	ASTM D7647	>40	33	14	17	
Particles >38µm	ASTM D7647	>10	1	1	2	
Particles >71µm	ASTM D7647	>3	1	1	1	
Oil Cleanliness	ISO 4406 (c)	>19/17/14	24/22/15	24/22/15	22/20/14	

FLUID DEGRADATION		method	limit/base	current	history1	history2
Acid Number (AN)	mg KOH/g	ASTM D974*	0.60	0.73	0.59	0.60

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	NONE	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE	NONE
Precipitate	scalar	Visual*	NONE	NONE	NONE	NONE
Silt	scalar	Visual*	NONE	NONE	NONE	NONE
Debris	scalar	Visual*	NONE	NONE	NONE	NONE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.05	NEG	NEG	NEG
Free Water	scalar	Visual*		NEG	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	67.4	66.1	66.4	66.2
Visc @ 100°C	cSt	ASTM D7279(m)	8.9	8.9	9	8.9
Viscosity Index (VI)	Scale	ASTM D2270*	105	108	110	108

SAMPLE IMAGES

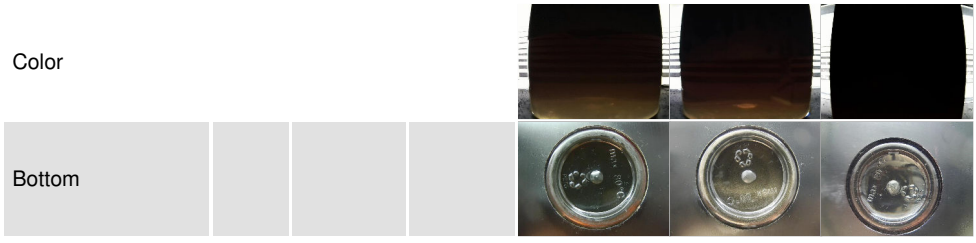

EXTRUDEX ALUMINIUM
 411 CHRISLEA ROAD
 WOODBRIDGE, ON
 CA L4L 8N4
 Contact: Daljeet Munday
 dmunday@extrudex.com
 T: (416)745-4444
 F: (416)745-0925