


OIL ANALYSIS REPORT



Area
Scoop 6 Yard
Machine Id
LHD6103
Component
Front Left Wheel Hub
Fluid
PETRO CANADA TRAXON 80W90 (4 LTR)

Sample Rating Trend

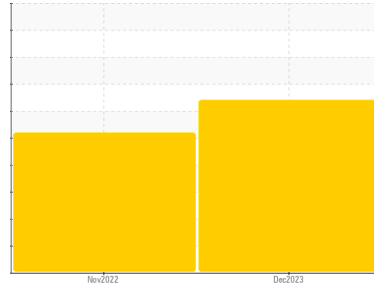

DIAGNOSIS

Recommendation
We advise that you check all areas where dirt can enter the system. We recommend that you drain the oil from the component if this has not already been done. Confirm the source of the lubricant being utilized for top-up/fill. We recommend an early resample to monitor this condition.

Wear
Chromium and copper and iron and lead ppm levels are abnormal. Tin ppm levels are marginal. Aluminum ppm levels are are. Gear wear is indicated. Bearing and/or bushing wear is indicated.

Contamination
There is a moderate concentration of dirt present in the oil. High amount of ingressed dirt has caused abrasive wear to the component.

Fluid Condition
Additive levels indicate the addition of a different brand, or type of oil. The oil is no longer serviceable as a result of the abnormal and/or severe wear.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	PC0074997	PC0051053	---
Sample Date	Client Info	02 Dec 2023	16 Nov 2022	---
Machine Age	hrs	7269	0	---
Oil Age	hrs	0	0	---
Oil Changed	Client Info	N/A	N/A	---
Sample Status		ABNORMAL	ABNORMAL	---

CONTAMINATION

method	limit/base	current	history1	history2
Water	WC Method	>0.2	NEG	---

WEAR METALS

method	limit/base	current	history1	history2
PQ	ASTM D8184*	272	---	---
Iron	ppm	>500	404	---
Chromium	ppm	>8	4	---
Nickel	ppm	>5	2	---
Titanium	ppm	2	4	---
Silver	ppm	0	0	---
Aluminum	ppm	>5	45	---
Lead	ppm	>5	2	---
Copper	ppm	>50	77	---
Tin	ppm	>5	3	---
Antimony	ppm	>5	<1	---
Vanadium	ppm	0	<1	---
Beryllium	ppm	0	0	---
Cadmium	ppm	0	0	---

ADDITIVES


method	limit/base	current	history1	history2
Boron	ppm	243	33	---
Barium	ppm	1	<1	---
Molybdenum	ppm	<1	<1	---
Manganese	ppm	18	6	---
Magnesium	ppm	2	21	---
Calcium	ppm	6	84	---
Phosphorus	ppm	987	693	---
Zinc	ppm	1	35	---
Sulfur	ppm	21530	23127	---
Lithium	ppm	<1	<1	---

CONTAMINANTS


method	limit/base	current	history1	history2
Silicon	ppm	>25	163	---
Sodium	ppm	28	22	---
Potassium	ppm	>20	19	---

OIL ANALYSIS REPORT


▲ Non-ferrous Metals

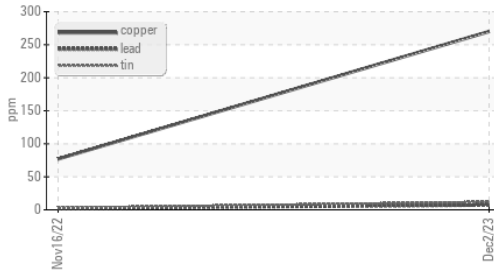


▲ Ferrous Alloys

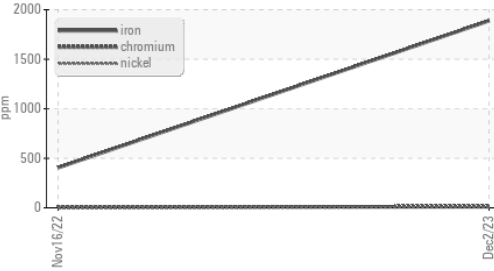


● Viscosity @ 100°C

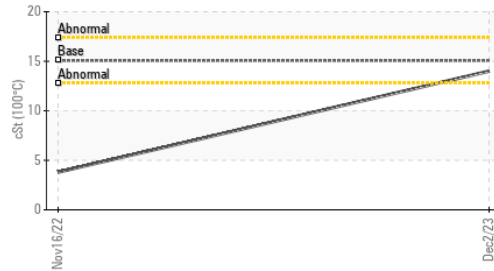

Additives

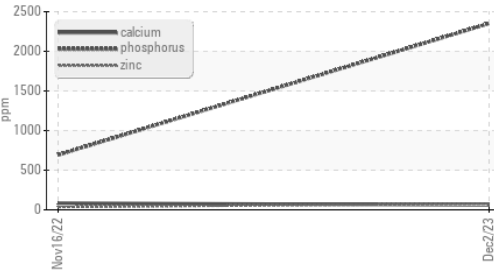


● Viscosity @ 100°C

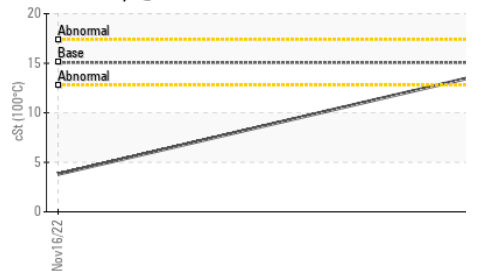


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	LIGHT	NONE
Yellow Metal	scalar	Visual*	NONE	NONE	NONE
Precipitate	scalar	Visual*	NONE	NONE	NONE
Silt	scalar	Visual*	NONE	NONE	NONE
Debris	scalar	Visual*	NONE	NONE	NONE
Sand/Dirt	scalar	Visual*	NONE	NONE	NONE
Appearance	scalar	Visual*	NORML	NORML	NORML
Odor	scalar	Visual*	NORML	NORML	NORML
Emulsified Water	scalar	Visual*	>0.2	NEG	▲ .2%
Free Water	scalar	Visual*		NEG	NEG

FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	141.0	126	144
Visc @ 100°C	cSt	ASTM D7279(m)	15.06	14.0	3.8
Viscosity Index (VI)	Scale	ASTM D2270*	108	109	---

SAMPLE IMAGES

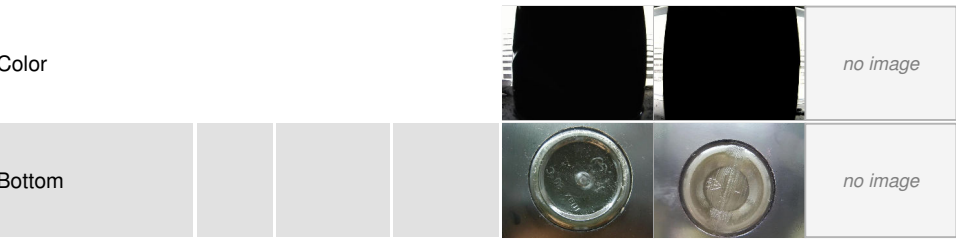

GRAPHS

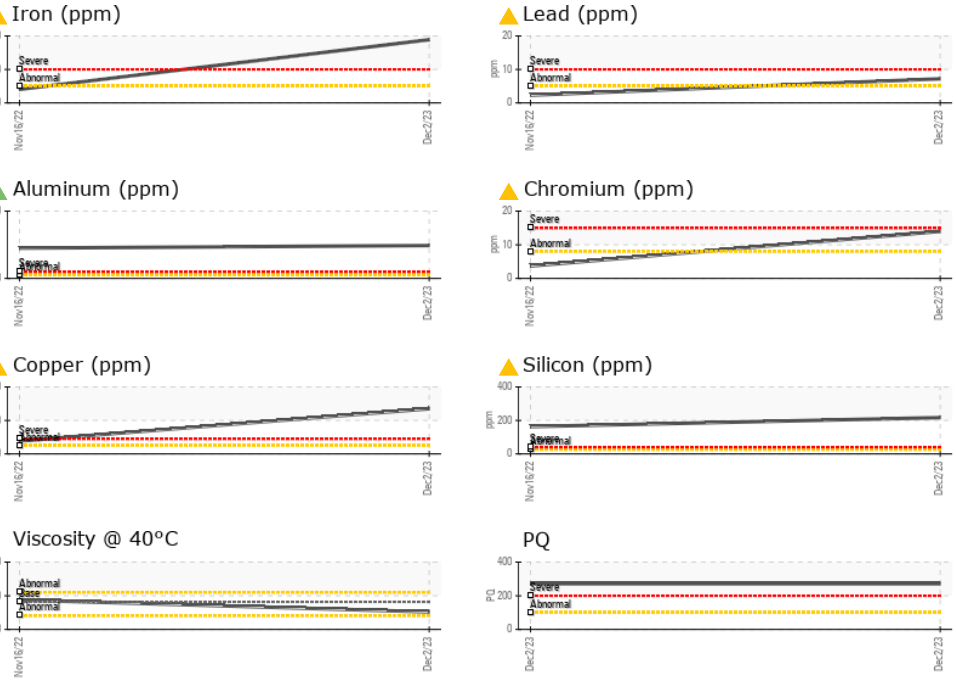

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : PC0074997 **Received** : 20 Dec 2023
Lab Number : 02604486 **Diagnosed** : 21 Dec 2023
Unique Number : 5697571 **Diagnostician** : Kevin Marson
Test Package : MOB 1 (Additional Tests: KV100, PQ, VI)

Lakeshore Gold Timmins West
 Timmins, ON
 CA
 Contact: Adam Koscielak
 adam.koscielak@HFSinclair.com
 T:
 F:

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.