


Machine Id  
**6025**

Component  
**Rear Diesel Engine**

Fluid  
**PETRO CANADA DURON HP 15W40 (18 LTR)**

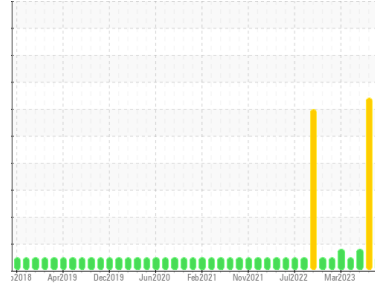

**DIAGNOSIS**

**Recommendation**  
Échantillonner de nouveau l'équipement au prochain intervalle de vidange afin d'en surveiller la condition.

**Wear**  
Les taux d'usure de tous les composants sont normaux.

**Contamination**  
Il n'y a aucun indice de contamination dans l'huile.

**Fluid Condition**  
Le résultat pour le BN indique que la réserve d'alcalinité est acceptable pour l'huile. L'état de l'huile permet d'en prolonger l'utilisation.

**SAMPLE INFORMATION**

method	limit/base	current	history1	history2
Sample Number	Client Info	<b>PC0079461</b>	PC0079821	PC0073535
Sample Date	Client Info	<b>04 Jan 2024</b>	13 Nov 2023	08 May 2023
Machine Age	kms Client Info	<b>583988</b>	575449	0
Oil Age	kms Client Info	<b>8539</b>	15022	7451
Oil Changed	Client Info	<b>Changed</b>	Changed	Not Changed
Sample Status		<b>NORMAL</b>	SEVERE	ABNORMAL

**CONTAMINATION**

method	limit/base	current	history1	history2
Fuel	WC Method >3.0	<b>&lt;1.0</b>	▲ 1.3	<1.0
Water	WC Method >0.2	<b>NEG</b>	NEG	NEG
Glycol	WC Method	<b>NEG</b>	NEG	NEG

**WEAR METALS**

method	limit/base	current	history1	history2
Iron	ppm ASTM D5185(m) >130	<b>38</b>	78	56
Chromium	ppm ASTM D5185(m) >10	<b>4</b>	▲ 13	4
Nickel	ppm ASTM D5185(m) >4	<b>&lt;1</b>	<1	1
Titanium	ppm ASTM D5185(m) >2	<b>0</b>	0	<1
Silver	ppm ASTM D5185(m) >2	<b>0</b>	0	0
Aluminum	ppm ASTM D5185(m) >20	<b>7</b>	11	▲ 27
Lead	ppm ASTM D5185(m) >20	<b>&lt;1</b>	<1	0
Copper	ppm ASTM D5185(m) >125	<b>1</b>	3	<1
Tin	ppm ASTM D5185(m) >4	<b>0</b>	0	<1
Antimony	ppm ASTM D5185(m)	<b>0</b>	0	0
Vanadium	ppm ASTM D5185(m)	<b>0</b>	0	0
Beryllium	ppm ASTM D5185(m)	<b>0</b>	0	0
Cadmium	ppm ASTM D5185(m)	<b>0</b>	0	0

**ADDITIVES**

method	limit/base	current	history1	history2
Boron	ppm ASTM D5185(m) 0	<b>3</b>	3	3
Barium	ppm ASTM D5185(m) 0	<b>0</b>	<1	0
Molybdenum	ppm ASTM D5185(m) 60	<b>55</b>	52	59
Manganese	ppm ASTM D5185(m) 0	<b>0</b>	<1	<1
Magnesium	ppm ASTM D5185(m) 1010	<b>904</b>	854	931
Calcium	ppm ASTM D5185(m) 1070	<b>1099</b>	1023	1060
Phosphorus	ppm ASTM D5185(m) 1150	<b>978</b>	938	1057
Zinc	ppm ASTM D5185(m) 1270	<b>1164</b>	1119	1153
Sulfur	ppm ASTM D5185(m) 2060	<b>2539</b>	2311	2478
Lithium	ppm ASTM D5185(m)	<b>&lt;1</b>	<1	<1




**CONTAMINANTS**

method	limit/base	current	history1	history2
Silicon	ppm ASTM D5185(m) >25	<b>16</b>	▲ 54	4
Sodium	ppm ASTM D5185(m)	<b>4</b>	14	3
Potassium	ppm ASTM D5185(m) >20	<b>1</b>	2	<1

**INFRA-RED**

method	limit/base	current	history1	history2
Soot %	% ASTM D7844* >6	<b>0.7</b>	0.8	1.6
Nitration	Abs/cm ASTM D7624* >20	<b>9.6</b>	8.6	10.6
Sulfation	Abs./1mm ASTM D7415* >30	<b>21.1</b>	21.1	22.6

# OIL ANALYSIS REPORT






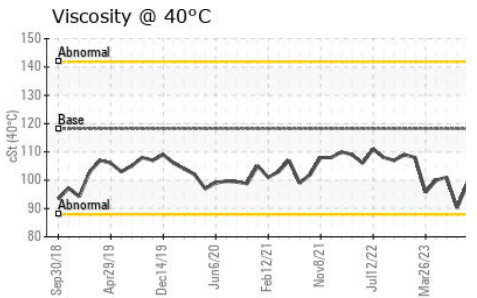
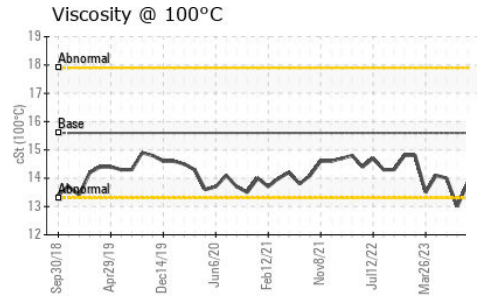
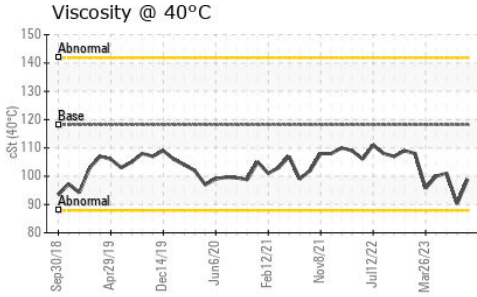


FLUID DEGRADATION		method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	ASTM D7414*	>25	<b>16.5</b>	15.6	17.8
Base Number (BN)	mg KOH/g	ASTM D2896*	9.8	<b>8.64</b>	7.10	8.07

VISUAL		method	limit/base	current	history1	history2
Emulsified Water	scalar	Visual*	>0.2	<b>NEG</b>	NEG	NEG
Free Water	scalar	Visual*		<b>NEG</b>	NEG	NEG

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	118.2	<b>98.9</b>	90.2	101
Visc @ 100°C	cSt	ASTM D7279(m)	15.6	<b>13.8</b>	13.0	14.0
Viscosity Index (VI)	Scale	ASTM D2270*	139	<b>140</b>	142	140

## GRAPHS

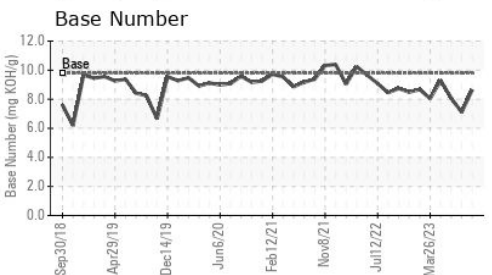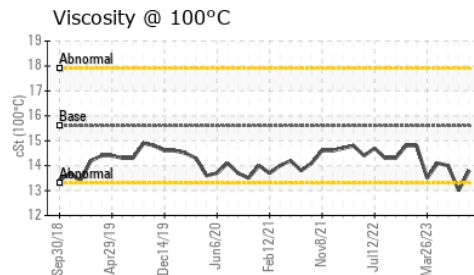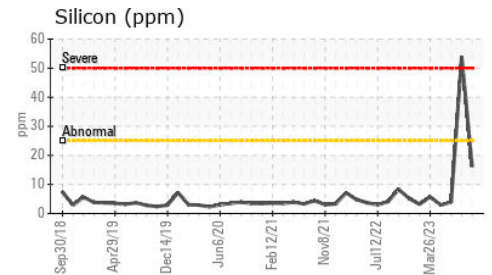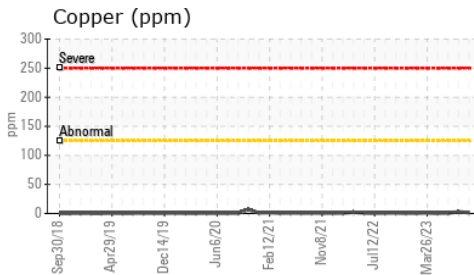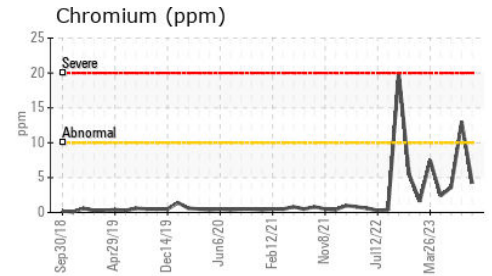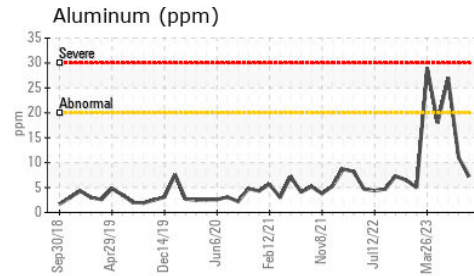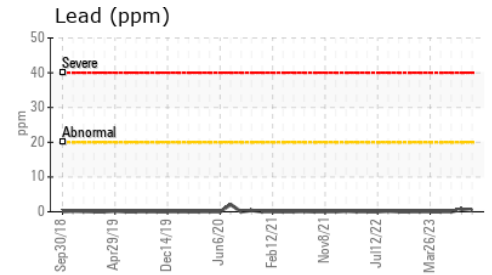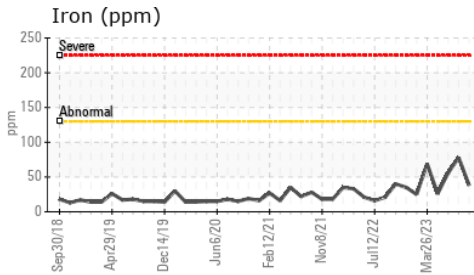

**Laboratory** : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9  
**Sample No.** : PC0079461  
**Lab Number** : **02612100**  
**Unique Number** : 5721195  
**Test Package** : MOB 2 ( Additional Tests: KV40, VI )

**TRANSDEV ST-JEAN**  
 720 TROTTER  
 ST-JEAN-SUR-RICHELIEU, QC  
 CA J3B 8T2  
 Contact: Eric Breton  
 eric.breton@transdev.com

To discuss this sample report, contact Customer Service at 1-800-268-2131.  
 Test denoted (\*) outside scope of accreditation, (m) method modified, (e) tested at external lab.  
 Validity of results and interpretation are based on the sample and information as supplied.

T:  
F: