


OIL ANALYSIS REPORT

Sample Rating Trend



NORMAL

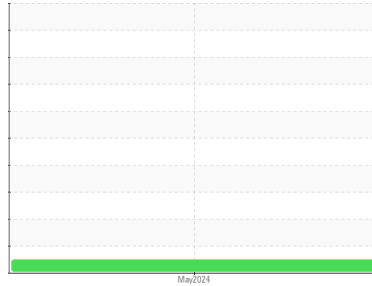

Machine Id
BENCHTANK
Component
Bottom Hydraulic System
Fluid
PETRO CANADA DURATRAN (--- LTR)

DIAGNOSIS

Recommendation

Resample at the next service interval to monitor. Please specify the component make and model with your next sample.

Wear

All component wear rates are normal.

Contamination

The system cleanliness is acceptable for your target ISO 4406 cleanliness code. The system and fluid cleanliness is acceptable.

Fluid Condition

The condition of the oil is acceptable for the time in service.

SAMPLE INFORMATION		method	limit/base	current	history1	history2
Sample Number	Client Info			PC0040964	---	---
Sample Date	Client Info			06 May 2024	---	---
Machine Age	hrs	Client Info		0	---	---
Oil Age	hrs	Client Info		0	---	---
Oil Changed	Client Info			N/A	---	---
Sample Status				NORMAL	---	---

CONTAMINATION		method	limit/base	current	history1	history2
Water	WC Method		>0.1	NEG	---	---





WEAR METALS		method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185(m)	>20	1	---	---
Chromium	ppm	ASTM D5185(m)	>10	0	---	---
Nickel	ppm	ASTM D5185(m)	>10	0	---	---
Titanium	ppm	ASTM D5185(m)		0	---	---
Silver	ppm	ASTM D5185(m)		0	---	---
Aluminum	ppm	ASTM D5185(m)	>10	1	---	---
Lead	ppm	ASTM D5185(m)	>10	0	---	---
Copper	ppm	ASTM D5185(m)	>75	0	---	---
Tin	ppm	ASTM D5185(m)	>10	0	---	---
Antimony	ppm	ASTM D5185(m)		0	---	---
Vanadium	ppm	ASTM D5185(m)		0	---	---
Beryllium	ppm	ASTM D5185(m)		0	---	---
Cadmium	ppm	ASTM D5185(m)		0	---	---

ADDITIVES		method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185(m)	110	99	---	---
Barium	ppm	ASTM D5185(m)	0.0	0	---	---
Molybdenum	ppm	ASTM D5185(m)	0.0	0	---	---
Manganese	ppm	ASTM D5185(m)	1	0	---	---
Magnesium	ppm	ASTM D5185(m)	13	21	---	---
Calcium	ppm	ASTM D5185(m)	3610	3426	---	---
Phosphorus	ppm	ASTM D5185(m)	1192	1079	---	---
Zinc	ppm	ASTM D5185(m)	1455	1344	---	---
Sulfur	ppm	ASTM D5185(m)	2641	2546	---	---
Lithium	ppm	ASTM D5185(m)		<1	---	---

CONTAMINANTS		method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185(m)	>20	9	---	---
Sodium	ppm	ASTM D5185(m)		0	---	---
Potassium	ppm	ASTM D5185(m)	>20	0	---	---

FLUID CLEANLINESS		method	limit/base	current	history1	history2
Particles >4µm		ASTM D7647	>5000	3474	---	---
Particles >6µm		ASTM D7647	>1300	1017	---	---
Particles >14µm		ASTM D7647	>160	61	---	---
Particles >21µm		ASTM D7647	>40	18	---	---
Particles >38µm		ASTM D7647	>10	3	---	---
Particles >71µm		ASTM D7647	>3	2	---	---
Oil Cleanliness		ISO 4406 (c)	>19/17/14	19/17/13	---	---

OIL ANALYSIS REPORT

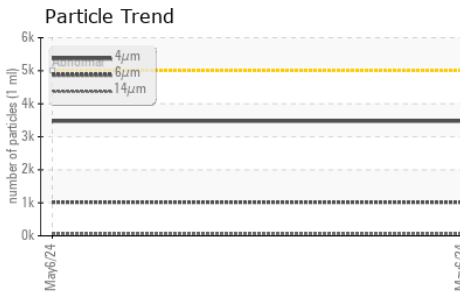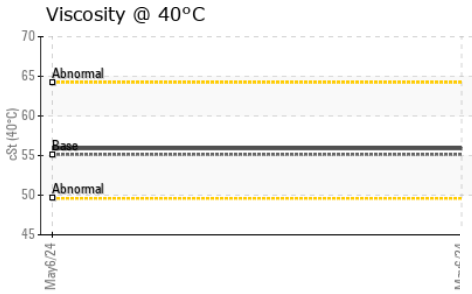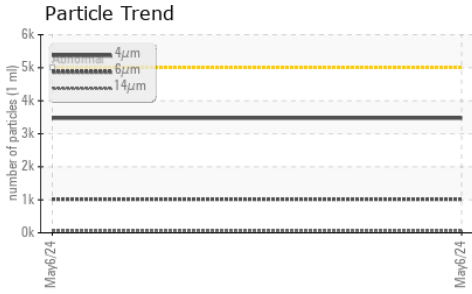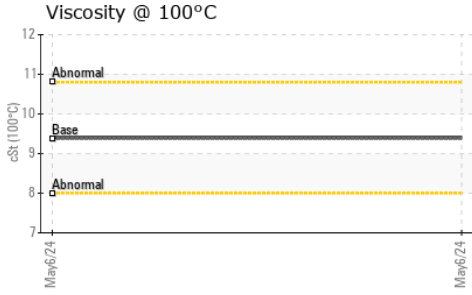





VISUAL	method	limit/base	current	history1	history2	
White Metal	scalar	Visual*	NONE	NONE	---	---
Yellow Metal	scalar	Visual*	NONE	NONE	---	---
Precipitate	scalar	Visual*	NONE	NONE	---	---
Silt	scalar	Visual*	NONE	NONE	---	---
Debris	scalar	Visual*	NONE	NONE	---	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---	---
Appearance	scalar	Visual*	NORML	NORML	---	---
Odor	scalar	Visual*	NORML	NORML	---	---
Emulsified Water	scalar	Visual*	>0.1	NEG	---	---
Free Water	scalar	Visual*		NEG	---	---

FLUID PROPERTIES	method	limit/base	current	history1	history2	
Visc @ 40°C	cSt	ASTM D7279(m)	55.14	55.9	---	---
Visc @ 100°C	cSt	ASTM D7279(m)	9.38	9.4	---	---
Viscosity Index (VI)	Scale	ASTM D2270*	153	151	---	---

SAMPLE IMAGES

	method	limit/base	current	history1	history2
Color				no image	no image
Bottom				no image	no image

GRAPHS

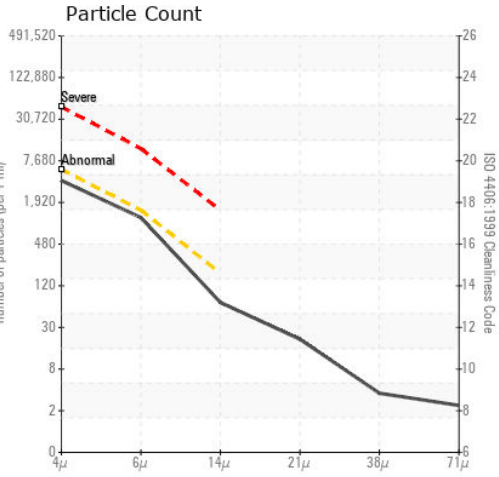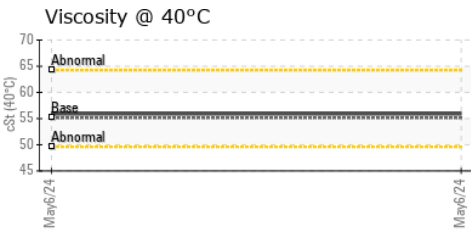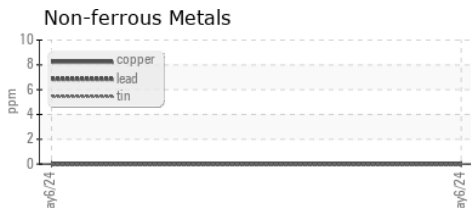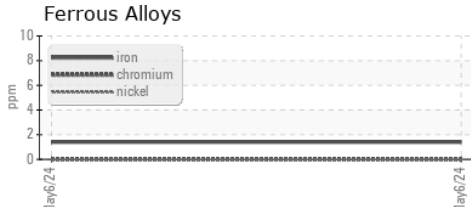

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9
Sample No. : PC0040964 **Received** : 08 May 2024
Lab Number : 02634096 **Tested** : 09 May 2024
Unique Number : 5775249 **Diagnosed** : 09 May 2024 - Kevin Marson
Test Package : MOB 2 (Additional Tests: KV100, VI)

BRENDONN HOLDINGS LTD
 24 BROADWAY STREET WEST
 YORKTON, SK
 CA S3N 0L4
 Contact: Tony Ripa
 tripa@bhldt.ca
 T: (306)783-4567
 F: (306)783-5700

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.