



OIL ANALYSIS REPORT

Sample Rating Trend



WEAR



Machine Id
MACK 914014
 Component
Diesel Engine
 Fluid
PETRO CANADA DURON HP 15W40 (--- GAL)

DIAGNOSIS

▲ Recommendation

The oil change at the time of sampling has been noted. Confirm the source of the lubricant being utilized for top-up/fill. We recommend an early resample to monitor this condition.

▲ Wear

Nickel ppm levels are abnormal. Exhaust valve wear is indicated. Component wear metal level(s) high for break in.

Contamination

Elevated aluminum (Al) and/or lead (Pb) and potassium (K) levels in your metals analysis are likely a result of solder flux release into the lubricant and is common on new equipment/components. Tests indicate that there is no fuel present in the oil. There is no indication of any contamination in the oil.

▲ Fluid Condition

Viscosity of sample indicates oil is within SAE 10W30 range, advise investigate. This plus the additive levels indicates that this is not the same brand, or type of oil as reported. The oil is no longer serviceable as a result of the abnormal and/or severe wear.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		GFL0122250	---	---
Sample Date	Client Info		17 Jun 2024	---	---
Machine Age	hrs	Client Info	1110	---	---
Oil Age	hrs	Client Info	551	---	---
Oil Changed	Client Info		Changed	---	---
Sample Status			ABNORMAL	---	---

CONTAMINATION

	method	limit/base	current	history1	history2
Water	WC Method	>0.2	NEG	---	---
Glycol	WC Method		NEG	---	---

WEAR METALS

	method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185(m)	>120	78	---	---
Chromium	ppm	ASTM D5185(m)	>20	2	---	---
Nickel	ppm	ASTM D5185(m)	>5	▲ 10	---	---
Titanium	ppm	ASTM D5185(m)	>2	<1	---	---
Silver	ppm	ASTM D5185(m)	>2	<1	---	---
Aluminum	ppm	ASTM D5185(m)	>20	7	---	---
Lead	ppm	ASTM D5185(m)	>40	<1	---	---
Copper	ppm	ASTM D5185(m)	>330	43	---	---
Tin	ppm	ASTM D5185(m)	>15	4	---	---
Antimony	ppm	ASTM D5185(m)		0	---	---
Vanadium	ppm	ASTM D5185(m)		0	---	---
Beryllium	ppm	ASTM D5185(m)		0	---	---
Cadmium	ppm	ASTM D5185(m)		0	---	---

ADDITIVES

	method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185(m)	0	54	---	---
Barium	ppm	ASTM D5185(m)	0	<1	---	---
Molybdenum	ppm	ASTM D5185(m)	60	114	---	---
Manganese	ppm	ASTM D5185(m)	0	5	---	---
Magnesium	ppm	ASTM D5185(m)	1010	684	---	---
Calcium	ppm	ASTM D5185(m)	1070	1331	---	---
Phosphorus	ppm	ASTM D5185(m)	1150	603	---	---
Zinc	ppm	ASTM D5185(m)	1270	766	---	---
Sulfur	ppm	ASTM D5185(m)	2060	1733	---	---
Lithium	ppm	ASTM D5185(m)		<1	---	---

CONTAMINANTS






	method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185(m)	>25	64	---	---
Sodium	ppm	ASTM D5185(m)		5	---	---
Potassium	ppm	ASTM D5185(m)	>20	18	---	---
Fuel	%	ASTM D7593*	>3.0	0.0	---	---

INFRA-RED

	method	limit/base	current	history1	history2	
Soot %	%	ASTM D7844*	>4	0.8	---	---
Nitration	Abs/cm	ASTM D7624*	>20	12.5	---	---
Sulfation	Abs./1mm	ASTM D7415*	>30	25.4	---	---



OIL ANALYSIS REPORT




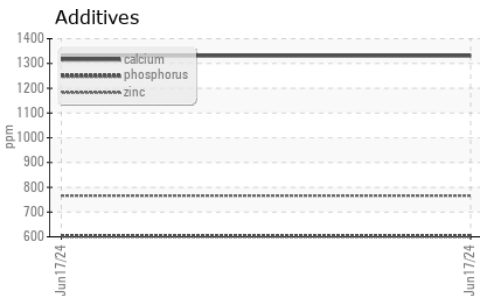
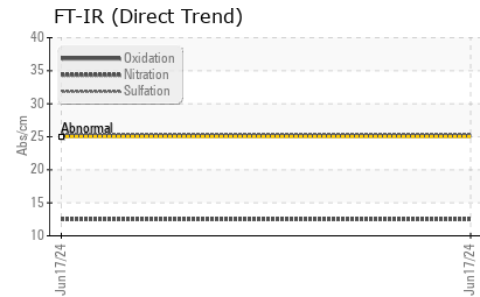
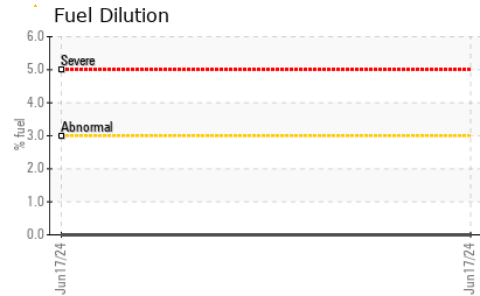
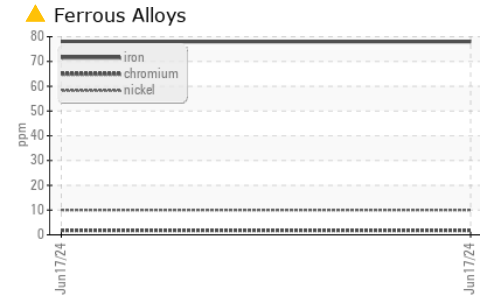
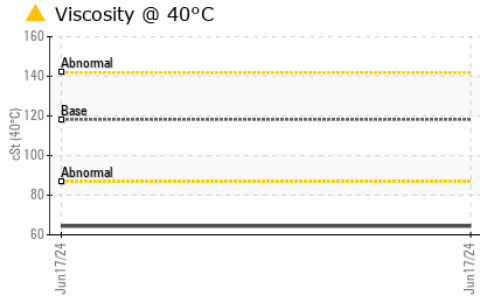


FLUID DEGRADATION		method	limit/base	current	history1	history2
Oxidation	Abs./1mm	ASTM D7414*	>25	25.1	---	---

VISUAL		method	limit/base	current	history1	history2
White Metal	scalar	Visual*	NONE	NONE	---	---
Yellow Metal	scalar	Visual*	NONE	NONE	---	---
Precipitate	scalar	Visual*	NONE	NONE	---	---
Silt	scalar	Visual*	NONE	NONE	---	---
Debris	scalar	Visual*	NONE	NONE	---	---
Sand/Dirt	scalar	Visual*	NONE	NONE	---	---
Appearance	scalar	Visual*	NORML	NORML	---	---
Odor	scalar	Visual*	NORML	NORML	---	---
Emulsified Water	scalar	Visual*	>0.2	NEG	---	---
Free Water	scalar	Visual*		NEG	---	---

FLUID PROPERTIES		method	limit/base	current	history1	history2
Visc @ 40°C	cSt	ASTM D7279(m)	118.2	▲ 64.4	---	---
Visc @ 100°C	cSt	ASTM D7279(m)	15.6	▲ 10.2	---	---
Viscosity Index (VI)	Scale	ASTM D2270*	139	144	---	---

GRAPHS

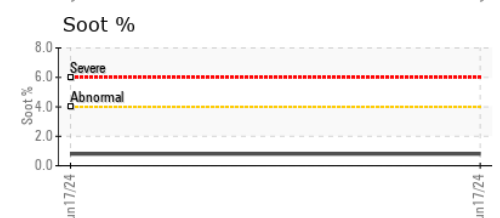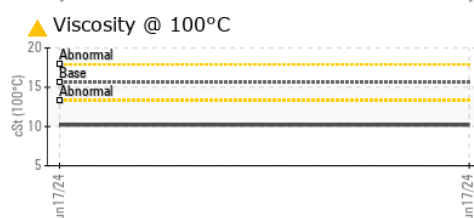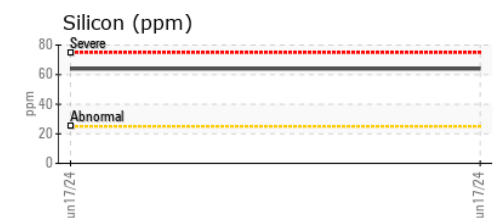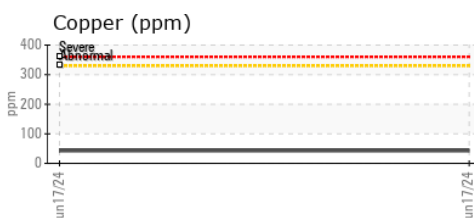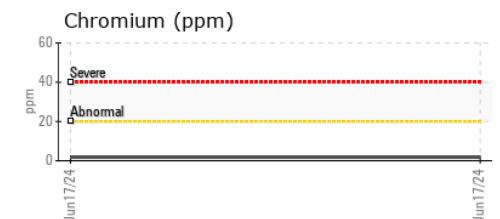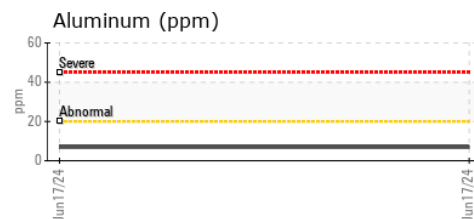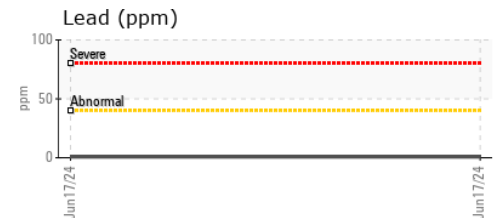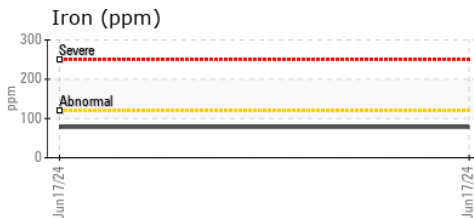

Laboratory : WearCheck - C8-1175 Appleby Line, Burlington, ON L7L 5H9 **GFL Environmental - 987 - Charlottetown**
Sample No. : GFL0122250 **Received** : 28 Jun 2024 7 Superior Crescent
Lab Number : **02644520** **Tested** : 02 Jul 2024 Charlottetown, PE
Unique Number : 5802059 **Diagnosed** : 02 Jul 2024 - Kevin Marson CA C1A 7N5
Test Package : MOB 1 (Additional Tests: FuelDilution, KV40, PercentFuel, VI, Visual) Contact: Vicki Metcalfe
vmetcalfe@gflenv.com

To discuss this sample report, contact Customer Service at 1-800-268-2131.
 Test denoted (*) outside scope of accreditation, (m) method modified, (e) tested at external lab.
 Validity of results and interpretation are based on the sample and information as supplied.

T: (782)377-5918
 F: (506)453-9490