




PROBLEM SUMMARY

Sample Rating Trend

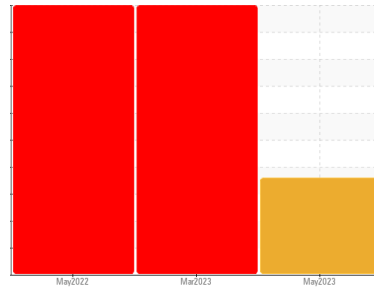

DIRT




Machine Id
821017-866

Component
Diesel Engine


Fluid
PETRO CANADA DURON SHP 15W40 (--- GAL)

COMPONENT CONDITION SUMMARY


▲ Glycol Contamination

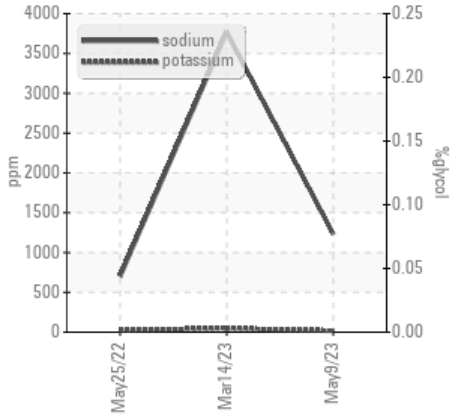

▲ Fuel Dilution

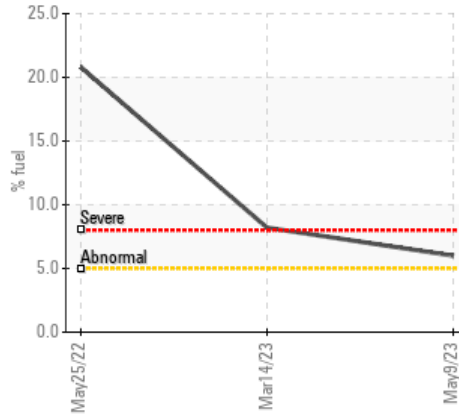

▲ Silicon (ppm)

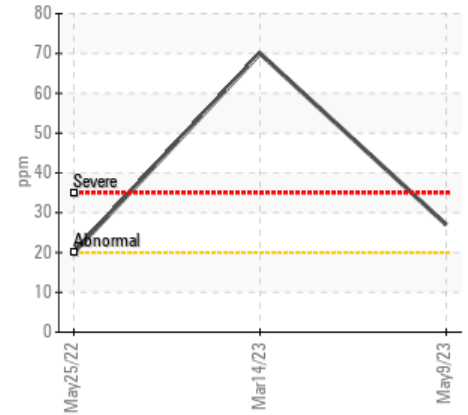

RECOMMENDATION

We advise that you check for the source of the coolant leak. Check for low coolant level. We advise that you check the fuel injection system. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

PROBLEMATIC TEST RESULTS

Sample Status				ABNORMAL	SEVERE	SEVERE
Silicon	ppm	ASTM D5185m	>20	▲ 27	● 70	▲ 20
Sodium	ppm	ASTM D5185m		▲ 1231	▲ 3764	▲ 701
Fuel	%	ASTM D3524	>5	▲ 6.0	● 8.2	● 20.8

Customer Id: GFL622
 Sample No.: GFL0078768
 Lab Number: 05846171
 Test Package: FLEET



To manage this report scan the QR code

To discuss the diagnosis or test data:
 Jonathan Hester +1 919-379-4092 x4092
jhester@wearcheckusa.com

To change component or sample information:
 Customer Service +1 1-800-237-1369
customerservice@wearcheck.com

RECOMMENDED ACTIONS

Action	Status	Date	Done By	Description
Change Fluid	---	---	?	Oil and filter change at the time of sampling has been noted.
Change Filter	---	---	?	Oil and filter change at the time of sampling has been noted.
Resample	---	---	?	We recommend an early resample to monitor this condition.
Check Fuel/injector System	---	---	?	We advise that you check the fuel injection system.
Check Glycol Access	---	---	?	We advise that you check for the source of the coolant leak.

HISTORICAL DIAGNOSIS

14 Mar 2023 Diag: Jonathan Hester

DIRT



We advise that you check for the source of the coolant leak. Check for low coolant level. We advise that you check the fuel injection system. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition. Cylinder, crank, or cam shaft wear is indicated. Sodium and/or potassium levels are high. There is a high amount of fuel present in the oil. Elemental level of silicon (Si) above normal indicating ingress of seal material. Fuel is present in the oil and is lowering the viscosity. The BN result indicates that there is suitable alkalinity remaining in the oil. The oil is no longer serviceable due to the presence of contaminants.

view report



25 May 2022 Diag: Jonathan Hester

WEAR



We advise that you check for the source of the coolant leak. Check for low coolant level. We advise that you check the fuel injection system. We advise that you check the air filter, air induction system, and any areas where dirt may enter the component. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition. Cylinder, crank, or cam shaft wear is indicated. Sodium and/or potassium levels are high. There is a high amount of fuel present in the oil. Elemental levels of silicon (Si) and aluminum (Al) indicate alumina-silicate (coarse dirt) ingress. Fuel is present in the oil and is lowering the viscosity. The BN result indicates that there is suitable alkalinity remaining in the oil. The oil is no longer serviceable due to the presence of contaminants.


view report





OIL ANALYSIS REPORT

Sample Rating Trend

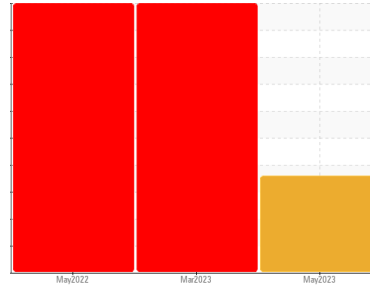

DIRT



Machine Id
821017-866

Component
Diesel Engine

Fluid
PETRO CANADA DURON SHP 15W40 (--- GAL)

DIAGNOSIS

Recommendation

We advise that you check for the source of the coolant leak. Check for low coolant level. We advise that you check the fuel injection system. Oil and filter change at the time of sampling has been noted. We recommend an early resample to monitor this condition.

Wear

All component wear rates are normal.

Contamination

Sodium and/or potassium levels are high. There is a moderate amount of fuel present in the oil. Elemental level of silicon (Si) above normal indicating ingress of seal material.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil.

SAMPLE INFORMATION

method	limit/base	current	history1	history2
Sample Number	Client Info	GFL0078768	GFL0071401	GFL0052805
Sample Date	Client Info	09 May 2023	14 Mar 2023	25 May 2022
Machine Age	hrs	15685	15544	14723
Oil Age	hrs	600	823	584
Oil Changed	Client Info	Changed	Changed	Changed
Sample Status		ABNORMAL	SEVERE	SEVERE

WEAR METALS

method	limit/base	current	history1	history2	
Iron	ppm	ASTM D5185m >80	41	▲ 132	● 140
Chromium	ppm	ASTM D5185m >5	2	6	6
Nickel	ppm	ASTM D5185m >2	<1	<1	<1
Titanium	ppm	ASTM D5185m	<1	1	<1
Silver	ppm	ASTM D5185m >3	0	0	<1
Aluminum	ppm	ASTM D5185m >30	2	6	▲ 12
Lead	ppm	ASTM D5185m >30	1	4	6
Copper	ppm	ASTM D5185m >150	2	3	8
Tin	ppm	ASTM D5185m >5	<1	<1	<1
Vanadium	ppm	ASTM D5185m	0	0	<1
Cadmium	ppm	ASTM D5185m	0	0	<1

ADDITIVES

method	limit/base	current	history1	history2	
Boron	ppm	ASTM D5185m 0	19	49	33
Barium	ppm	ASTM D5185m 0	2	0	2
Molybdenum	ppm	ASTM D5185m 60	109	216	70
Manganese	ppm	ASTM D5185m 0	<1	1	2
Magnesium	ppm	ASTM D5185m 1010	895	815	425
Calcium	ppm	ASTM D5185m 1070	1144	1138	1247
Phosphorus	ppm	ASTM D5185m 1150	993	774	736
Zinc	ppm	ASTM D5185m 1270	1203	1130	945
Sulfur	ppm	ASTM D5185m 2060	3084	3285	2189

CONTAMINANTS

method	limit/base	current	history1	history2	
Silicon	ppm	ASTM D5185m >20	▲ 27	● 70	▲ 20
Sodium	ppm	ASTM D5185m	▲ 1231	▲ 3764	▲ 701
Potassium	ppm	ASTM D5185m >20	16	▲ 47	25
Fuel	%	ASTM D3524 >5	▲ 6.0	● 8.2	● 20.8
Glycol	%	*ASTM D2982	NEG	NEG	NEG

INFRA-RED

method	limit/base	current	history1	history2	
Soot %	%	*ASTM D7844 >3	0.8	2	1.9
Nitration	Abs/cm	*ASTM D7624 >20	12.9	23.9	19.9
Sulfation	Abs/.1mm	*ASTM D7415 >30	22.4	32.9	31.9


FLUID DEGRADATION

method	limit/base	current	history1	history2	
Oxidation	Abs/.1mm	*ASTM D7414 >25	19.1	29.2	37.2
Base Number (BN)	mg KOH/g	ASTM D2896 9.8	11.0	15.0	8.1




OIL ANALYSIS REPORT


▲ Fuel Dilution

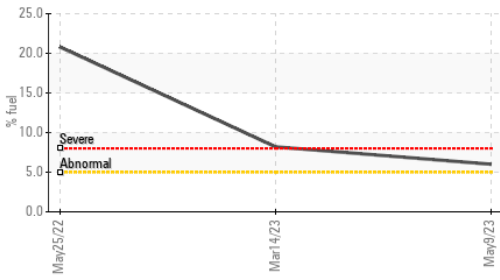


▲ Silicon (ppm)

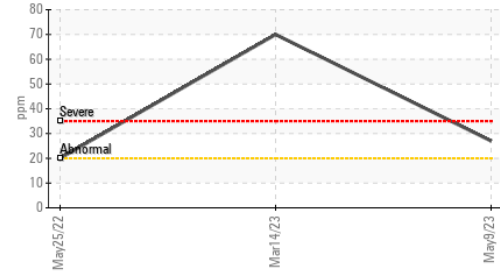


Glycol Contamination

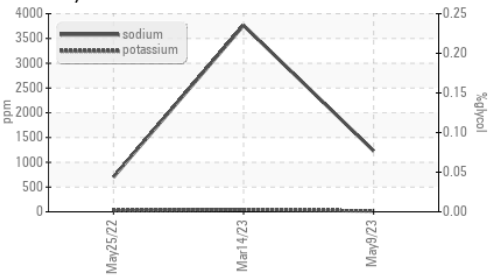

Viscosity @ 100°C

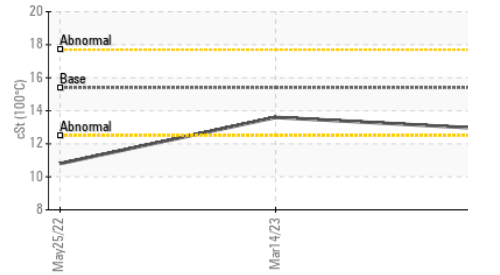

Glycol Contamination

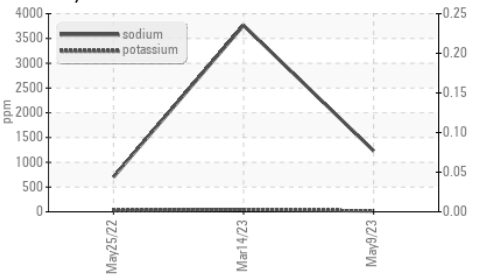


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	15.4	12.9	13.6 ▲ 10.8

GRAPHS


Ferrous Alloys

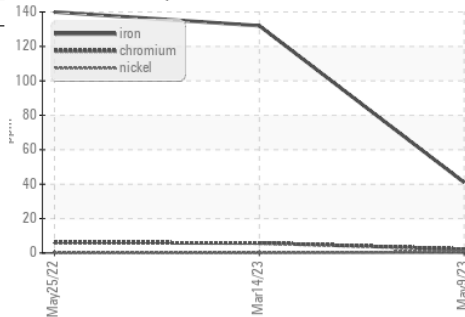


Non-ferrous Metals

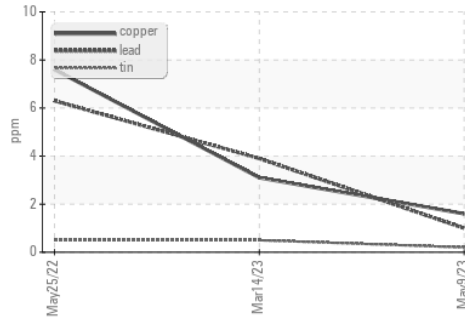

Viscosity @ 100°C

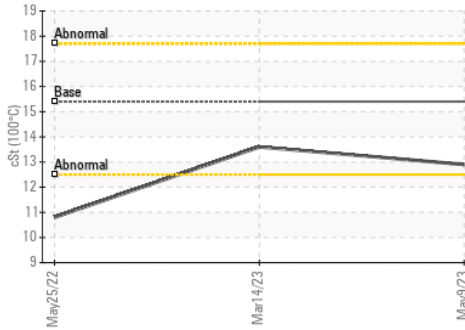

Base Number

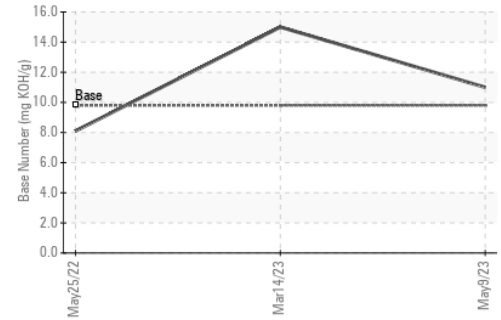

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : GFL0078768 **Received** : 12 May 2023
Lab Number : 05846171 **Diagnosed** : 17 May 2023
Unique Number : 10470278 **Diagnostician** : Jonathan Hester
Test Package : FLEET (Additional Tests: Glycol, PercentFuel)

GFL Environmental - 622 - Traverse City Hauling
 160 Hughes Dr
 Traverse City, MI
 US 49686
 Contact: GARY BREWER

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:
F: