


OIL ANALYSIS REPORT

Sample Rating Trend



WEAR

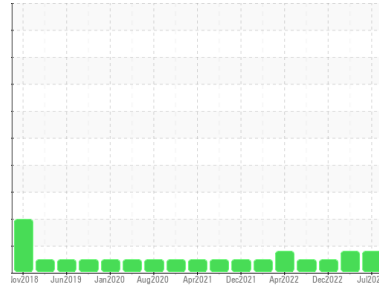

Machine Id
684389

Component
Diesel Engine

Fluid
PETRO CANADA DURON SHP 10W30 (--- QTS)

DIAGNOSIS

Recommendation

No corrective action is recommended at this time. Resample at the next service interval to monitor.

Wear

The aluminum level is abnormal. All other component wear rates are normal.

Contamination

There is no indication of any contamination in the oil.

Fluid Condition

The BN result indicates that there is suitable alkalinity remaining in the oil. The condition of the oil is suitable for further service.

SAMPLE INFORMATION

	method	limit/base	current	history1	history2
Sample Number	Client Info		PCA0101368	PCA0094288	PCA0088116
Sample Date	Client Info		14 Jul 2023	24 Mar 2023	03 Dec 2022
Machine Age	mls	Client Info	286998	269379	254029
Oil Age	mls	Client Info	0	0	0
Oil Changed	Client Info		Not Chngd	Not Chngd	Not Chngd
Sample Status			ABNORMAL	ABNORMAL	NORMAL

CONTAMINATION

	method	limit/base	current	history1	history2
Fuel	WC Method	>5	<1.0	<1.0	<1.0
Glycol	WC Method		NEG	NEG	NEG

WEAR METALS

	method	limit/base	current	history1	history2
Iron	ppm	ASTM D5185m >100	60	33	28
Chromium	ppm	ASTM D5185m >20	4	2	2
Nickel	ppm	ASTM D5185m >4	<1	0	0
Titanium	ppm	ASTM D5185m	<1	<1	<1
Silver	ppm	ASTM D5185m >3	0	0	0
Aluminum	ppm	ASTM D5185m >20	▲ 38	▲ 22	15
Lead	ppm	ASTM D5185m >40	0	0	<1
Copper	ppm	ASTM D5185m >330	17	11	12
Tin	ppm	ASTM D5185m >15	3	2	0
Vanadium	ppm	ASTM D5185m	0	0	0
Cadmium	ppm	ASTM D5185m	0	0	0

ADDITIVES

	method	limit/base	current	history1	history2
Boron	ppm	ASTM D5185m 2	0	4	0
Barium	ppm	ASTM D5185m 0	0	0	1
Molybdenum	ppm	ASTM D5185m 50	111	92	112
Manganese	ppm	ASTM D5185m 0	2	1	<1
Magnesium	ppm	ASTM D5185m 950	1023	930	901
Calcium	ppm	ASTM D5185m 1050	1221	1162	1108
Phosphorus	ppm	ASTM D5185m 995	1046	855	935
Zinc	ppm	ASTM D5185m 1180	1377	1272	1200
Sulfur	ppm	ASTM D5185m 2600	3109	2522	2907

CONTAMINANTS

	method	limit/base	current	history1	history2
Silicon	ppm	ASTM D5185m >25	22	11	7
Sodium	ppm	ASTM D5185m	6	4	3
Potassium	ppm	ASTM D5185m >20	21	20	21

INFRA-RED


	method	limit/base	current	history1	history2
Soot %	%	*ASTM D7844 >3	2.3	1.7	1.6
Nitration	Abs/cm	*ASTM D7624 >20	13.0	10.9	11.1
Sulfation	Abs/.1mm	*ASTM D7415 >30	27.0	24.2	24.9

FLUID DEGRADATION


	method	limit/base	current	history1	history2
Oxidation	Abs/.1mm	*ASTM D7414 >25	22.0	19.1	19.8
Base Number (BN)	mg KOH/g	ASTM D2896	4.4	5.6	6.9

OIL ANALYSIS REPORT


▲ Aluminum (ppm)

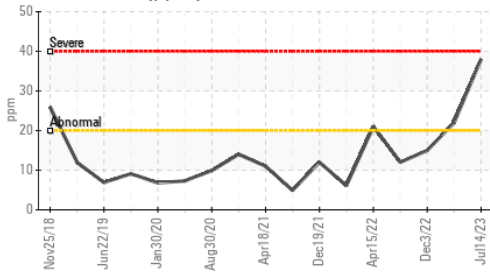

Base Number

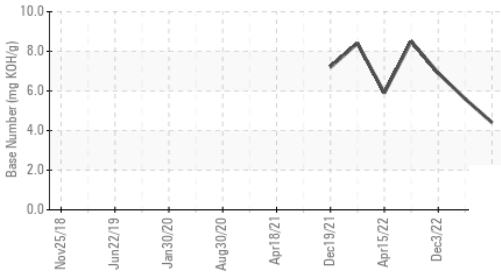

Viscosity @ 100°C

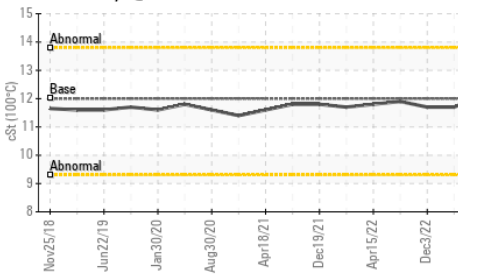


VISUAL	method	limit/base	current	history1	history2
White Metal	scalar	*Visual	NONE	NONE	NONE
Yellow Metal	scalar	*Visual	NONE	NONE	NONE
Precipitate	scalar	*Visual	NONE	NONE	NONE
Silt	scalar	*Visual	NONE	NONE	NONE
Debris	scalar	*Visual	NONE	NONE	NONE
Sand/Dirt	scalar	*Visual	NONE	NONE	NONE
Appearance	scalar	*Visual	NORML	NORML	NORML
Odor	scalar	*Visual	NORML	NORML	NORML
Emulsified Water	scalar	*Visual	>0.2	NEG	NEG
Free Water	scalar	*Visual		NEG	NEG


FLUID PROPERTIES	method	limit/base	current	history1	history2
Visc @ 100°C	cSt	ASTM D445	12.00	12.1	11.7

GRAPHS


Iron (ppm)

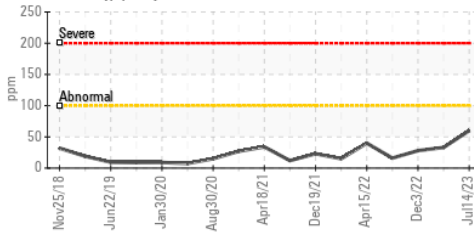


Lead (ppm)

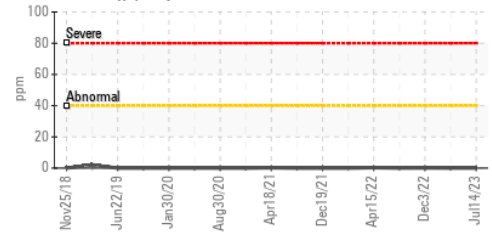


▲ Aluminum (ppm)

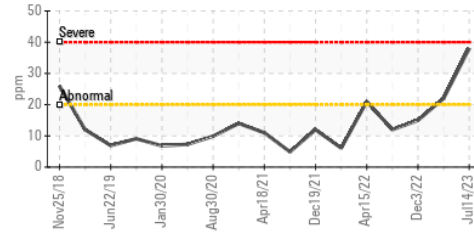


Chromium (ppm)

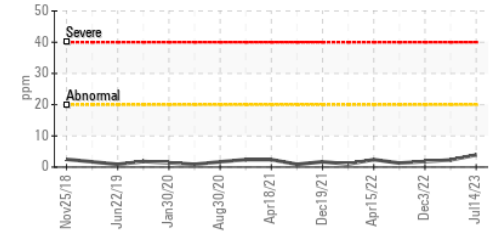


Copper (ppm)

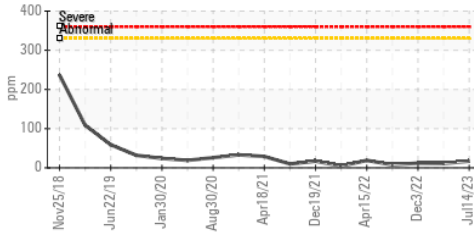


Silicon (ppm)

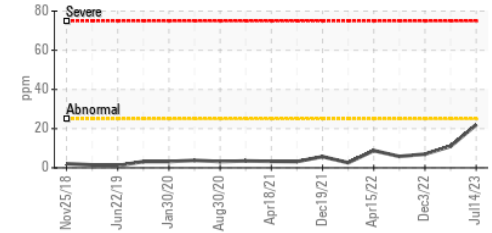

Viscosity @ 100°C

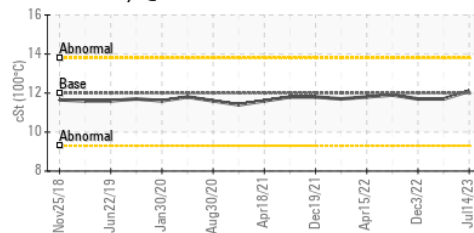

Base Number

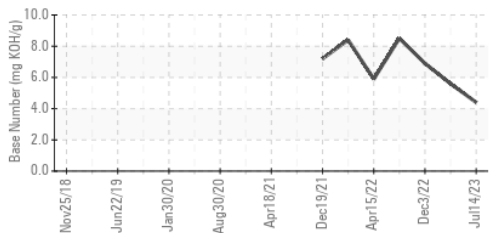

Certificate L2367

Laboratory : WearCheck USA - 501 Madison Ave., Cary, NC 27513
Sample No. : PCA0101368 **Received** : 20 Jul 2023
Lab Number : 05903058 **Diagnosed** : 21 Jul 2023
Unique Number : 10564414 **Diagnostician** : Don Baldrige
Test Package : MOB 1 (Additional Tests: TBN)

MILLER TRUCK LEASING #119
 39 INDUSTRIAL AVE
 HASBROUCK HEIGHTS, NJ
 US 07604
 Contact: MIKE LONGETTE
 mlongette@millertransgroup.com

To discuss this sample report, contact Customer Service at 1-800-237-1369.

* - Denotes test methods that are outside of the ISO 17025 scope of accreditation.

Statements of conformity to specifications are based on the simple acceptance decision rule (JCGM 106:2012)

T:
F: (201)528-7053